

## LETTER

### The solubility of H<sub>2</sub>O in peralkaline and peraluminous granitic melts

D.B. DINGWELL,<sup>1</sup> F. HOLTZ,<sup>2</sup> AND H. BEHRENS<sup>3</sup>

<sup>1</sup>Bayerisches Geoinstitut, Universität Bayreuth, 95440 Bayreuth, Germany

<sup>2</sup>CRSCM-CNRS, 1a rue de la Férollerie, 45071 Orléans, France

<sup>3</sup>Institut für Mineralogie, Universität Hannover, Welfengarten 1, 30167 Hannover, Germany

#### ABSTRACT

The solubility of H<sub>2</sub>O in a series of 13 melts based on a haplogranitic composition (HPG8) have been determined for the conditions of 500–5000 bar pressure and 800–1000 °C. The compositions represent the additions of individual components (Cs<sub>2</sub>O, Rb<sub>2</sub>O, K<sub>2</sub>O, Na<sub>2</sub>O, Li<sub>2</sub>O, and Al<sub>2</sub>O<sub>3</sub>) to HPG8 (in wt% 78.6 SiO<sub>2</sub>, 12.5 Al<sub>2</sub>O<sub>3</sub>, 4.6 Na<sub>2</sub>O, 4.2 K<sub>2</sub>O; see Knoche et al. 1995) to generate peralkaline and peraluminous compositions, respectively. The H<sub>2</sub>O-saturated melts were generated by hydrothermal fusion of dry glassy starting materials in an internally heated pressure vessel. The quenched products of the hydration experiments were analyzed by Karl-Fischer titration for bulk H<sub>2</sub>O contents.

H<sub>2</sub>O solubility increases with added excess alkali oxide. Compared on a weight percent basis, the solubility of H<sub>2</sub>O for a given degree of peralkalinity increases in the order Cs, Rb < K < Na < Li. On a molar equivalent basis the effects of excess Cs, Rb, K, and Na on increasing the solubility of H<sub>2</sub>O are the same, whereas the effect of Li<sub>2</sub>O is somewhat lower. This contrasts with the relatively high solubility of H<sub>2</sub>O in LiAlSi<sub>3</sub>O<sub>8</sub> melt relative to albite and orthoclase melts and implies that excess Li<sub>2</sub>O is not contributing to the content of nonbridging O atoms in the melt as efficiently as the other alkalis.

For the peraluminous compositions, the solubility of H<sub>2</sub>O decreases with the addition of 2 wt% Al<sub>2</sub>O<sub>3</sub> to the HPG8 composition, then increases strongly with the further addition of excess Al<sub>2</sub>O<sub>3</sub>, so that a solubility minimum exists not at the 1:1 alkali-Al ratio of melt composition but at a slightly peraluminous melt composition. The solubility of H<sub>2</sub>O in the melt with 5 wt% excess Al<sub>2</sub>O<sub>3</sub> is significantly larger than that in HPG8. If the peraluminous composition with the minimum solubility of H<sub>2</sub>O is taken as a basis for estimating the influence of nonbridging O atoms associated with “excess” alkalis or Al in the melt structure then the effects of excess Al and alkalis (Cs, Rb, K, Na) are comparable on the basis of the number of nonbridging O atoms added to the slightly peraluminous base.

The addition of Na<sub>2</sub>O up to levels of peralkalinity commonly encountered in glassy magmatic eruptive rocks of peralkaline volcanic provinces leads to an almost doubling of the low pressure (500 bar) solubility of H<sub>2</sub>O in the melt. Evidence for an H<sub>2</sub>O-rich history of glassy peralkaline obsidians from melt inclusions or from stable isotopes may indicate much shallower depths of saturation than previously thought possible.

#### INTRODUCTION

The alkali-Al ratio of alkali aluminosilicate melts is a compositional parameter influencing several melt properties, including viscosity, density, diffusivities, and gas solubilities. The influence of the alkali-Al ratio on the solubility of H<sub>2</sub>O in granitic melts is a subject of considerable interest regarding the evolution of H<sub>2</sub>O-rich granitic magmas from undersaturated to saturated conditions during the late stages of igneous fractionation. Preliminary evaluation of the effect of the alkali-Al ratio on the

solubility of H<sub>2</sub>O in such melts is available from several previous studies. The early phase-equilibrium studies of Morey and coworkers (Morey and Fenner 1917; Morey and Ingerson 1938; Morey and Hesselgesser 1952) in Al-free alkali silicate systems indicates that solubility of alkali silicate phases is very high in H<sub>2</sub>O. Clear chemographic indication of enhanced solubility of H<sub>2</sub>O in peralkaline melts is also available from Mustart (1972) and this general trend was confirmed by analytical determination of H<sub>2</sub>O solubility by Dingwell et al. (1984). The

present experimental study was conducted to evaluate systematically the influence of the alkali-Al ratio on the solubility of H<sub>2</sub>O in granitic melts.

## METHODS

Several experimental and analytical procedures were used in the last decades to determine H<sub>2</sub>O solubilities in silicate melts (see discussions in Ihinger et al. 1994, Behrens 1995). In this study, the experimental technique consisted of using anhydrous, bubble-free blocks of glass, sealed in a noble-metal capsule with an amount of water sufficient to reach H<sub>2</sub>O saturation. After hydration of the samples at high *P* and *T*, H<sub>2</sub>O contents in the quenched glasses were determined by Karl Fischer titration. A detailed description of both experimental and analytical procedures used to determine H<sub>2</sub>O solubilities in this study has been given already by Behrens (1995) and Holtz et al. (1995). It is emphasized that these procedures can be used successfully to determine H<sub>2</sub>O solubilities in aluminosilicate melts containing 1 to 10–14 wt% H<sub>2</sub>O (Behrens 1995).

The starting compositions were synthesized to represent the additions of individual components to a haplogranitic base composition near the 2 kbar H<sub>2</sub>O-saturated ternary minimum composition in the KAlSi<sub>3</sub>O<sub>8</sub>-NaAlSi<sub>3</sub>O<sub>8</sub>-SiO<sub>2</sub> system, labelled HPG8 (see composition above). These glasses were used in several studies to determine the physical properties of melts (Hess et al. 1995, Knoche et al. 1995) and were prepared from powders of carbonates (Li, Na, K, Rb, Cs) and oxides (Al, Si) placed in platinum crucibles inside a MoSi<sub>2</sub> box furnace. The partially fused products were transferred to a viscometer furnace, fused again, and stirred from hours to days until melts were bubble-free (see procedure in Knoche et al. 1995). The compositions of the dry glasses were determined by ICP-AES methods and have been presented by Knoche et al. (1995).

Glass cylinders of 40–70 mg were sealed together with doubly distilled water in gold capsules. The proportions of H<sub>2</sub>O were 5–6, 10–12, and 15–17 wt% for experiments carried out at 0.5, 2, and 5 kbar, respectively. Experiments were conducted in internally heated pressure vessels working horizontally (0.5 kbar) or vertically (2–5 kbar, see Roux and Lefèvre 1992 for descriptions). Experimental durations were 12–17 d at 0.5 kbar (1000 °C), 7–9 d at 2, 4, and 5 kbar (800–900 °C). These durations were long enough to allow compete homogenization of H<sub>2</sub>O through the sample (for diffusion coefficients of H<sub>2</sub>O in haplogranitic or feldspar melts, see review in Watson 1994). Isobaric quenching was performed for 0.5 and 2 kbar experiments, but not for the 4 and 5 kbar experiments (for technical reasons). Most quenched experimental glasses were clear and bubble free. Two peraluminous glasses (+5Al) contained mullite needles (Table 1) after the quench. Some glasses synthesized at 5 kbar were cloudy as a result of the formation of bubbles during the quench. However, because we used a bulk analytical technique (Karl-Fischer titration) for the determination of

TABLE 1. Experimental data for water solubility

Sample	<i>P</i> (kbar)	<i>T</i> (°C)	Water analysis (KFT)	Solubility
HPG8	0.5	1000	2.28, (2.35–2.45)*	2.44
	2	800	5.94*	6.04
	5	900	9.34, 9.38	9.46
+2Al	0.5	1000	2.11, 2.13	2.22
	2	800	6.07	6.17
	5	900	9.71	9.81
+5Al	0.5	1000	2.70 (cr)	
	2	800	6.12 (cr)	
	5	900	(9.91–9.82)	9.96
–2Al	0.5	1000	2.44, 2.48	2.56
	2	800	6.10, 6.18	6.24
	5	900	10.21	10.31
–5Al	0.5	900	2.89, 2.93	3.01
	2	800	6.67, 6.77	6.82
	4	800	11.22	11.32
	5	900	11.91, 12.19	12.15
5Li	0.5	1000	3.31	3.41
	2	800	8.12	8.22
	4	800	12.15	12.25
10Li	0.5	1000	3.70	3.80
5Na	0.5	1000	3.08	3.18
10Na	0.5	1000	3.57	3.67
5K	0.5	1000	2.83	2.93
5Rb	0.5	1000	2.54	2.64
	2	800	6.56	6.66
10Rb	0.5	1000	2.76	2.86
5Cs	0.5	1000	2.45	2.55

Note: The different water contents determined by Karl-Fischer titration (KFT) for a given composition and given *P*-*T* conditions are obtained from samples synthesized in different experiments. Analyses given in parentheses were duplicated for the same sample. Water solubilities were calculated from average values obtained by KFT and by adding 0.1 wt% H<sub>2</sub>O (see Behrens 1995).

\* Data are taken from Holtz et al. (1995, 1992). The presence of mullite is indicated by (cr).

H<sub>2</sub>O in the glasses, the presence of bubbles containing H<sub>2</sub>O is not expected to affect the determined H<sub>2</sub>O solubility, as demonstrated by Holtz et al. (1995, see table p. 98).

H<sub>2</sub>O contents were determined by Karl Fischer titration with the use of an extraction line coupled with a high-frequency generator (Behrens et al. 1996). H<sub>2</sub>O is extracted from the hydrous glass sample by heating the sample placed in an induction coil up to 1300 °C. The H<sub>2</sub>O is carried toward the titration cell by a flow of dry argon. Typical heating rates are given by Behrens (1995) and Holtz et al. (1995). For glass samples of 10 mg or more (weight of the samples analyzed in this study), these authors have calculated a precision of the determined H<sub>2</sub>O contents of ±0.15 wt% H<sub>2</sub>O.

## RESULTS

The results are presented in Table 1 as a function of the amount of oxide added to HPG8. A trend of increasing H<sub>2</sub>O solubility with increasing alkali oxide content is clearly evident. Also clear is that the solubility of H<sub>2</sub>O in the peralkaline melts, compared at a constant weight percent of added alkali oxide, increases in the order Cs, Rb < K < Na < Li. Most of the results presented in Table 1 were obtained at 0.5 kbar. Although few data are avail-

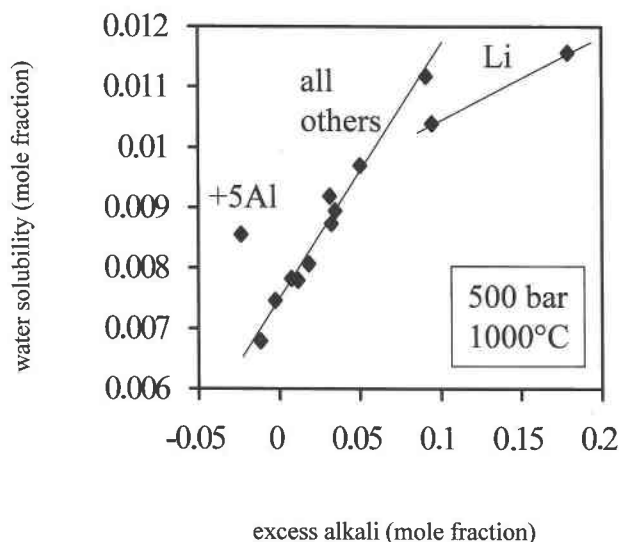


FIGURE 1. The effect of excess alkalis on the solubility of H<sub>2</sub>O in granitic melts at 500 bar and 1000 °C. The excess alkali content is defined as the difference between the total mole fraction of alkalis and that of Al. The solubility data for H<sub>2</sub>O in melts with excess alkalis all lie on a single curve with the exception of the two data points for excess Li on the right and one for excess Al on the left. The line defining the bulk trend does not pass through a minimum at 0 but rather at a slightly peraluminous composition. See text for a discussion of the relevance of these trends.

able at higher pressure, the comparison of data obtained for 5Li, -2Al and -5Al compositions indicates that the same behavior can be expected at pressures up to 5 kbar. Clearly a small weight percent addition of excess Li<sub>2</sub>O in a peralkaline melt can generate a significant increase in H<sub>2</sub>O solubility. Similarly, the maximum geologically reasonable levels of excess Na<sub>2</sub>O in peralkaline volcanics can lead to large increases in the solubility of H<sub>2</sub>O in such melts.

The effect of excess Al<sub>2</sub>O<sub>3</sub> on H<sub>2</sub>O solubility is also included in Table 1. Starting from peralkaline compositions, increasing the Al<sub>2</sub>O<sub>3</sub> content of the melts produces a decrease of the H<sub>2</sub>O solubility down to a minimum and then an increase of the H<sub>2</sub>O solubility in strongly peraluminous compositions. The minimum is close to the subaluminous composition (HPG8) at 2 and 5 kbar. However, at 0.5 kbar the H<sub>2</sub>O solubility minimum is shifted toward the peraluminous compositions.

It should be noted that the minimum H<sub>2</sub>O solubility that is found in this study near Al/(Na + K) = 1 is in good agreement with the data of Dingwell et al. (1984) at 1 kbar and 800 °C. An excellent agreement is also observed with the data of Linnen et al. (1996) obtained at 850 °C and 2 kbar (in this study, data are obtained at 800 °C and 2 kbar). In these two previous studies, the compositions investigated are haplogranitic or correspond to the peralkaline and peraluminous equivalents of haplogranitic compositions (compositions belong to the system SiO<sub>2</sub>-

Al<sub>2</sub>O<sub>3</sub>-Na<sub>2</sub>O-K<sub>2</sub>O). Qualitatively, a good agreement with the H<sub>2</sub>O solubilities determined by Oxtoby and Hamilton (1978) at  $P < 2$  kbar and Behrens (1995) between 0.5 and 5 kbar for a subaluminous albite composition and equivalent peralkaline compositions is observed (the H<sub>2</sub>O-solubility data determined are higher than in this study, as a result of changing normative feldspar and quartz proportions). At higher pressures, Oxtoby and Hamilton (1978) observe a crossover of the solubility curves (higher solubility in albite melts than in the equivalent peralkaline composition) but it has been shown that the analytical procedure used to determine the H<sub>2</sub>O contents dissolved in the glasses used by Oxtoby and Hamilton (1978) is not suited for glasses with high H<sub>2</sub>O contents (Behrens 1995). At pressures higher than 1 kbar, the minimum H<sub>2</sub>O solubility is clearly at Al/(Na + K) = 1, which contrasts with our results obtained at low pressure (0.5 kbar).

Figure 1 compares the influence of the individual alkali oxides on the solubility of H<sub>2</sub>O on the basis of moles of added oxide. This molar comparison reveals that the molar effect of peralkalinity is identical for all the alkali oxides with the exception of Li<sub>2</sub>O. The lower enhancement of H<sub>2</sub>O solubility with the addition of Li<sub>2</sub>O can be taken to imply that excess Li<sub>2</sub>O does not generate non-bridging O atoms in the peralkaline melt structure that are accessible for coordination by hydrous species. This contrasts with the enhancement of solubility in LiAlSi<sub>3</sub>O<sub>8</sub> melt compared with albite and orthoclase melts at 2 kbar and 800 °C. Whether the inference can be drawn that the coordination of Li deviates from the rest of the alkalis to a lower value of mean coordination number remains open.

## DISCUSSION

If the minimum in H<sub>2</sub>O solubility shifts in position from 0.5 kbar (in melts with approximately 2 wt% H<sub>2</sub>O) to 2 and 5 kbar, this might imply that the other properties of hydrous subaluminous and peraluminous melts change at low pressure (at low melt-H<sub>2</sub>O content) when compared with high pressure (high melt-H<sub>2</sub>O content). In particular, it might reflect an change in Al activity in these melts and the stability of aluminosilicate phases as well as phase relationships. For example, the effects of excess Al<sub>2</sub>O<sub>3</sub> on phase relationships in the Qz-Ab-Or system at low pressure may be qualitatively different from those determined by Holtz et al. (1992) and Joyce and Voigt (1994) at 2 kbar.

From Figure 1, increasing Na, K, or Na + K produces the same increase in H<sub>2</sub>O solubility. This suggests that the effect of the exchange of these two alkalis on H<sub>2</sub>O solubility is very low at 0.5 kbar. At 0.5 kbar, Holtz et al. (1995) also observed a very weak change in H<sub>2</sub>O solubility for changing Na/K in haplogranitic melts (subaluminous compositions). Thus, our data confirm that the Na/K ratio in melts at 0.5 kbar has very little effect on the H<sub>2</sub>O solubility mechanisms, in subaluminous melts as well as in peralkaline to peraluminous compositions. This

contrasts with the data of Oxtoby and Hamilton (1978, at  $P < 2$  kbar), Holtz et al. (1992, 1995), Behrens (1995), and Romano et al. (1996) showing a significant effect of the alkalis at 1–5 kbar in alkali feldspar melts. Unfortunately, we have no data at higher pressure to confirm that the alkali effect also exists in peraluminous to peralkaline melts, but it is emphasized that the thermodynamic and empirical models proposed to calculate H<sub>2</sub>O solubilities (e.g., Burnham and Nekvasil 1986, Burnham 1994, Moore et al. 1995) do not account for that effect. Although this alkali effect observed at  $P > 1$  kbar becomes less important (but not negligible) if solubilities are calculated for natural compositions, it should be taken into account in future models for the incorporation and solubility mechanisms of H<sub>2</sub>O in aluminosilicate melts.

The simplest considerations of the implications for the solubility minimum in the petrogenesis of granitic magmas involves the variations in the timing of boiling in such systems because of crystallization of liquidus phases with an alkali-Al ratio different from that of the melt composition. Crystallization of feldspars from slightly peraluminous melts can be expected to drive the liquid composition more rapidly toward boiling as the H<sub>2</sub>O solubility drops significantly with increasing peraluminosity. This could act as a potential barrier to developing peraluminous melts in nature with more than a few percent normative corundum. Such melts are indeed not very common.

#### ACKNOWLEDGMENTS

D.B.D. wishes to acknowledge the hospitality of the CRSCM during preparation of this work. The research has been supported by Procope (Bayreuth-Orleans).

#### REFERENCES CITED

- Behrens, H. (1995) Determination of water solubilities in high-viscosity melts: An experimental study on NaAlSi<sub>3</sub>O<sub>8</sub> and KAlSi<sub>3</sub>O<sub>8</sub> melts. *European Journal of Mineralogy*, 7, 905–920.
- Behrens, H., Romano, C., Nowak, M., Holtz, F., and Dingwell, D.B. (1996) Near infrared spectroscopic determination of water species in glasses of the system MAISi<sub>3</sub>O<sub>8</sub> (M = Li, Na, K): an interlaboratory study. *Chemical Geology*, 128, 41–63.
- Burnham, C.W. (1994) Development of the Burnham model for prediction of H<sub>2</sub>O solubility in magmas. In *Mineralogical Society of America Reviews in Mineralogy*, 30, 123–129.
- Burnham, C.W., and Nekvasil, H. (1986) Equilibrium properties of granitic pegmatite magmas. *American Mineralogist*, 71, 239–263.
- Dingwell, D.B., Harris, D.M., and Scarfe, C.M. (1984) The solubility of H<sub>2</sub>O in melts in the system SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>-Na<sub>2</sub>O-K<sub>2</sub>O at 1 to 2 kbars. *Journal of Geology*, 92, 387–395.
- Hess, K.-U., Dingwell, D.B., and Webb, S.L. (1995) The influence of excess alkalis on the viscosity of a haplogranitic melt. *American Mineralogist*, 80, 297–304.
- Holtz, F., Behrens, H., Dingwell, D.B., and Taylor, R.P. (1992) Water solubility in aluminosilicate melts of haplogranitic compositions at 2 kbars. *Chemical Geology*, 96, 289–302.
- Holtz, F., Behrens, H., Dingwell, D.B., and Johannes, W. (1995) H<sub>2</sub>O solubility in haplogranitic melts: compositional, pressure and temperature dependence. *American Mineralogist*, 80, 94–108.
- Ihinger, P.D., Hervig, R.L., and McMillan, P.F. (1994) Analytical Methods for volatiles in glasses. In *Mineralogical Society of America Reviews in Mineralogy*, 30, 67–112.
- Joyce, D.B., and Voigt, D.E. (1994) A phase equilibrium study in the system KAlSi<sub>3</sub>O<sub>8</sub>-NaAlSi<sub>3</sub>O<sub>8</sub>-SiO<sub>2</sub>-Al<sub>2</sub>SiO<sub>5</sub>-H<sub>2</sub>O and petrogenetic implications. *American Mineralogist*, 79, 504–512.
- Knoche, R., Dingwell, D.B., and Webb, S.L. (1995) Leucogranitic and pegmatitic melt densities: partial molar volumes for SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, Na<sub>2</sub>O, K<sub>2</sub>O, Rb<sub>2</sub>O, Cs<sub>2</sub>O, Li<sub>2</sub>O, BaO, SrO, CaO, MgO, TiO<sub>2</sub>, B<sub>2</sub>O<sub>3</sub>, P<sub>2</sub>O<sub>5</sub>, F<sub>2</sub>O<sub>3</sub>, Ta<sub>2</sub>O<sub>5</sub>, Nb<sub>2</sub>O<sub>5</sub> and WO<sub>3</sub>. *Geochimica et Cosmochimica Acta*, 59, 4645–4652.
- Linnen, R.L., Pichavant, M., and Holtz, F. (1996) The combined effects of fO<sub>2</sub> and melt composition on SnO<sub>2</sub> solubility and tin diffusivity in haplogranitic melts. *Geochimica et Cosmochimica Acta*, 60, 4965–4976.
- Moore, G., Vennemann, T., and Carmichael, I.S.E. (1995) Solubility of water in magmas to 2 kbar. *Geology*, 23, 1099–1102.
- Morey, G.W., and Fenner, C.N. (1917) The ternary system H<sub>2</sub>O-K<sub>2</sub>SiO<sub>3</sub>-SiO<sub>2</sub>. *Journal of the American Chemical Society*, 39, 1173–1229.
- Morey, G.W., and Ingerson, E. (1938) The system Water-Sodium Disilicate. *American Journal of Science*, V 35-A, 217–225.
- Morey, G.W., and Hesselgesser, J.M. (1952) The system H<sub>2</sub>O-Na<sub>2</sub>O-SiO<sub>2</sub> at 400 °C. *American Journal of Science-Bowen Volume*, 343–371.
- Mustart, D.A. (1972) Phase relations in the peralkaline portion of the system Na<sub>2</sub>O-Al<sub>2</sub>O<sub>3</sub>-SiO<sub>2</sub>-H<sub>2</sub>O. Ph.D. thesis, Stanford University, Berkeley, California.
- Oxtoby, S., and Hamilton, D.L. (1978) The discrete association of water with Na<sub>2</sub>O and SiO<sub>2</sub> in NaAl silicate melts. *Contributions to Mineralogy and Petrology*, 66, 185–188.
- Romano, C., Dingwell, D.B., Behrens, H., and Dolfi, D. (1996) Compositional dependence of H<sub>2</sub>O solubility along the joins NaAlSi<sub>3</sub>O<sub>8</sub>-KAlSi<sub>3</sub>O<sub>8</sub>, NaAlSi<sub>3</sub>O<sub>8</sub>-LiAlSi<sub>3</sub>O<sub>8</sub>, KAlSi<sub>3</sub>O<sub>8</sub>-LiAlSi<sub>3</sub>O<sub>8</sub>. *American Mineralogist*, 81, 452–461.
- Roux, J., and Lefevre, A. (1992) A fast quench device for internally heated pressure vessels. *European Journal of Mineralogy*, 4, 279–281.
- Watson, E.B. (1994) Diffusion in volatile-bearing magmas. In *Mineralogical Society of America Reviews in Mineralogy*, 30, 371–411.

MANUSCRIPT SUBMITTED AUGUST 14, 1996

MANUSCRIPT ACCEPTED JANUARY 17, 1997