

Acta Crystallographica Section C

**Crystal Structure
Communications**

ISSN 0108-2701

Editor: **George Ferguson**

Tyrellite, $\text{Cu}(\text{Co}_{0.68}\text{Ni}_{0.32})_2\text{Se}_4$, isostructural with spinel

Hexiong Yang, David K. Hubler, Barbara Lavina, Robert T. Downs and Gelu Costin

Copyright © International Union of Crystallography

Author(s) of this paper may load this reprint on their own web site or institutional repository provided that this cover page is retained. Republication of this article or its storage in electronic databases other than as specified above is not permitted without prior permission in writing from the IUCr.

For further information see <http://journals.iucr.org/services/authorrights.html>

Tyrrellite, $\text{Cu}(\text{Co}_{0.68}\text{Ni}_{0.32})_2\text{Se}_4$, isostructural with spinel

Hexiong Yang,^{a*} David K. Hubler,^a Barbara Lavina,^b
Robert T. Downs^a and Gelu Costin^a

^aDepartment of Geosciences, University of Arizona, 1040 East 4th Street, Tucson, AZ 85721-0077, USA, and ^bGSECARS-APS Building 434A, Argonne National Laboratory, 9700 South Cass Avenue, Argonne, IL 60439, USA
Correspondence e-mail: hyang@u.arizona.edu

Received 11 May 2007

Accepted 22 June 2007

Online 26 July 2007

Tyrrellite, a naturally occurring Co–Ni–Cu selenide, has been studied by single-crystal X-ray diffraction. It possesses the normal spinel-type structure, with Cu occupying the tetrahedral site and (Co+Ni) the octahedral site. The average Cu–Se distance of 2.3688 (2) Å is close to that of 2.3703 (8) Å in CuCr_2Se_4 , whereas the average (Co+Ni)–Se distance of 2.3840 (1) Å appears to be slightly shorter than most octahedral Co–Se or Ni–Se distances (~2.40–2.50 Å) in other selenides. The refined structure provides a basis for a redefinition of the ideal chemical formula of tyrrellite, which should be $\text{Cu}(\text{Co},\text{Ni})_2\text{Se}_4$, rather than the previously suggested $(\text{Cu},\text{Co},\text{Ni})_3\text{Se}_4$.

Comment

Selenide materials with the spinel-type structure, $AB_2\text{Se}_4$, where *A* and *B* are tetrahedrally and octahedrally coordinated sites, respectively, have been the subject of numerous studies because of their magnetic and semiconducting properties (see, for example, Juszczuk & Gogolowicz, 1991; Kim *et al.*, 2006; Skrzypek *et al.*, 2006; Noh *et al.*, 2007). Of particular interest is the distribution of various cations between the *A* and *B* sites, as such structural variations could significantly alter many physical properties of these materials (see, for example, Hazen & Yang, 1999; Okońska-Kozłowska *et al.*, 2001). Tyrrellite, a Co–Ni–Cu selenide, was first described by Robinson & Brooker (1952) to have a face-centered cubic lattice (*Fm*3*m*), with *a* = 10.005–10.042 Å and a chemical formula $\text{Co}_{3.0}\text{Ni}_{2.0}\text{Cu}_{3.5}\text{Se}_{9.5}$. However, Machatschki & Stradner (1952) pointed out that the X-ray powder pattern of tyrrellite resembled that of spinel minerals and the calculated intensities, assuming a spinel-type structure, agree well with the probable formula of $(\text{Co},\text{Cu},\text{Ni})_3\text{Se}_4$. Harris (1970) used a single-crystal X-ray diffractometer to examine the original tyrrellite material separated by Robinson & Brooker (1952) and found that all the fragments gave split reflections and were unsuitable for

structure determination. No further structural investigation has been reported since then. This study presents the first structure refinement of tyrrellite based on single-crystal X-ray diffraction data and provides a basis for a redefinition of its ideal chemical formula.

Tyrrellite is isostructural with spinel, with Cu and (Co+Ni), respectively, occupying the tetrahedral *A* and octahedral *B* sites in the cubic close-packed array of Se atoms (Fig. 1). The preference of Cu for the tetrahedral site has been observed for other spinel-type selenides and sulfides, such as CuCr_2Se_4 (Okońska-Kozłowska *et al.*, 1993), $\text{Cu}_{1-x}\text{Co}_x\text{Cr}_2\text{Se}_4$ (Okońska-Kozłowska *et al.*, 2001), $\text{Cu}_{1-x}\text{Ni}_x\text{Cr}_2\text{Se}_4$ and $\text{CuCr}_{2-x}\text{Ni}_x\text{Se}_4$ (Jendrzewska, 2000), CuCo_2S_4 (Williamson & Grimes, 1974), and $\text{Cu}(\text{Ni}_{0.25}\text{Sn}_{0.75})_2\text{S}_4$ (Garg *et al.*, 2001). The Cu–Se distance of 2.3688 (2) Å in tyrrellite is comparable with the range of 2.3664–2.3740 Å in spinel-type CuCr_2Se_4 (Okońska-Kozłowska *et al.*, 1993; Payer *et al.*, 1993; Rodic *et al.*, 1998), whereas the average (Co+Ni)–Se distance of 2.3840 (1) Å appears to be shorter than most Co–Se or Ni–Se distances (~2.40–2.50 Å) for six-coordinated Co or Ni in other selenides (see, for example, Furuseth *et al.*, 1969; Kamat Dalal *et al.*, 1971; Foecker & Jeitschko, 2001; Garcia-Garcia *et al.*, 2004).

Unlike oxide spinels, the valence of ions in selenide spinels has been a matter of discussion. For example, three models of electronic structure have been proposed for CuCr_2Se_4 : $\text{Cu}^{2+}\text{Cr}_2^{3+}\text{Se}_4^{2-}$ (Goodenough, 1967), $\text{Cu}^+[\text{Cr}^{3+}\text{Cr}^{4+}]\text{Se}_4^{2-}$ (Lotgering, 1964), and $\text{Cu}^+\text{Cr}_2^{3+}[\text{Se}_3^{2-}\text{Se}^-]$ (Lotgering & Van Staple, 1967). Although there is still some disagreement regarding the valence of Cr and Se, experimental results from X-ray photoelectron spectroscopy and neutron diffraction have demonstrated the presence of Cu^+ , rather than Cu^{2+} , in CuCr_2Se_4 (Hollander *et al.*, 1974; Yamashita *et al.*, 1979; Payer *et al.*, 1990; Rodic *et al.*, 1998). Since the Cu–Se bond length in

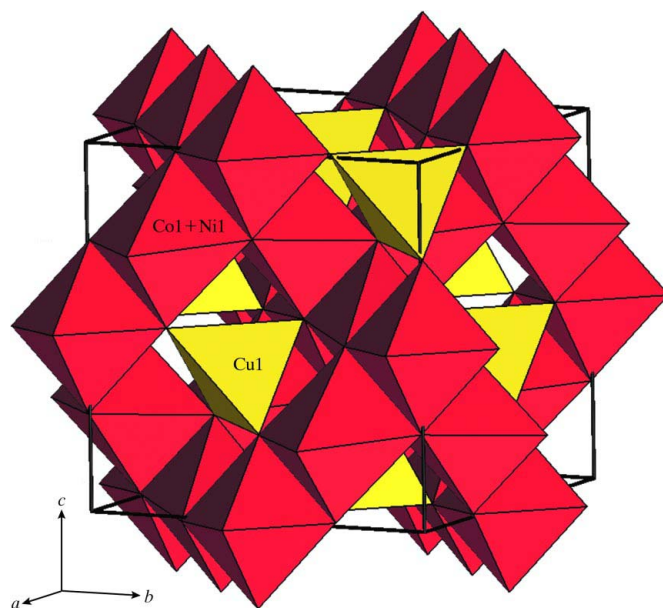


Figure 1
A polyhedral view of the crystal structure of tyrrellite.

tyrrellite agrees very well with that in CuCr_2Se_4 , presumably Cu in tyrrellite is also monovalent. Noteworthy, nevertheless, is the appreciably short (Co+Ni)—Se bond distance in tyrrellite compared with the Cr—Se distances (2.508–2.512 Å) in CuCr_2Se_4 (Okońska-Kozłowska *et al.*, 1993; Payer *et al.*, 1993; Rodic *et al.*, 1998). If we assume that the chemical bond between Se and the octahedrally coordinated cation is predominately ionic (Juszczuk & Gogolowicz, 1991; Rodic *et al.*, 1998), the calculation of the bond-valence sum using the parameters given by Brese & O’Keeffe (1991) yields a value of 3.77 valence units for (Co+Ni), suggesting that some Co or/and Ni in tyrrellite might exist in a formal charge greater than 3+.

Experimental

The tyrrellite specimen used in this study is from the type locality Eagle Claims, Beaverlodge Lake area, Saskatchewan, Canada, and is in the collection of the RRUFF project (deposition No. R060481; <http://rruff.info>). The specimen was described by Robinson & Brooker (1952) and Harris (1970). The average chemical composition (15 point analyses), $\text{Cu}_{0.99}(\text{Co}_{0.69}\text{Ni}_{0.31})_2\text{Se}_4$, was determined with a CAMECA SX50 electron microprobe.

Crystal data

$\text{Co}_{1.36}\text{CuNi}_{0.64}\text{Se}_4$	$Z = 8$
$M_r = 497.06$	Mo $K\alpha$ radiation
Cubic, $Fd\bar{3}m$	$\mu = 40.12 \text{ mm}^{-1}$
$a = 9.9885 (1) \text{ \AA}$	$T = 293 (2) \text{ K}$
$V = 996.55 (2) \text{ \AA}^3$	$0.07 \times 0.07 \times 0.06 \text{ mm}$

Data collection

Bruker APEXII CCD area-detector diffractometer	2566 measured reflections
Absorption correction: multi-scan (SADABS; Sheldrick, 2005)	227 independent reflections
$T_{\min} = 0.123$, $T_{\max} = 0.142$ (expected range = 0.078–0.090)	206 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.030$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.014$	9 parameters
$wR(F^2) = 0.028$	$\Delta\rho_{\max} = 0.79 \text{ e \AA}^{-3}$
$S = 1.12$	$\Delta\rho_{\min} = -1.27 \text{ e \AA}^{-3}$
227 reflections	

The A site was assumed to be fully occupied by Cu during the refinement. The Co:Ni ratio in the B site was allowed to vary and yielded occupancies of 0.68 (6) for Co and 0.32 (6) for Ni.

Data collection: APEX2 (Bruker, 2003); cell refinement: SAINT (Bruker, 2005); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 1997); program(s) used to refine structure: SHELXL97 (Sheldrick, 1997); molecular graphics: Xtal-Draw (Downs & Hall-Wallace, 2003); software used to prepare material for publication: SHELXTL (Bruker, 1997).

The authors gratefully acknowledge the support of this study from the RRUFF project and the National Science Foundation (grant No. EAR-0609906). The sample was donated to the project by Michael Scott.

Supplementary data for this paper are available from the IUCr electronic archives (Reference: BC3052). Services for accessing these data are described at the back of the journal.

References

- Brese, N. E. & O’Keeffe, M. (1991). *Acta Cryst.* **B47**, 192–197.
- Bruker (1997). *SHELXTL*. Version 5.10. Bruker AXS Inc., Madison, Wisconsin, USA.
- Bruker (2003). *SMART*. Version 6.0. Bruker AXS Inc., Madison, Wisconsin, USA.
- Bruker (2005). *SAINTE*. Version 6.0. Bruker AXS Inc., Madison, Wisconsin, USA.
- Downs, R. T. & Hall-Wallace, M. (2003). *Am. Mineral.* **88**, 247–250.
- Foecker, A. J. & Jeitschko, W. (2001). *J. Solid State Chem.* **162**, 69–78.
- Furuseth, S., Kjekshus, A. & Andersen, A. F. (1969). *Acta Chem. Scand.* **23**, 2325–2334.
- Garcia-Garcia, F. J., Larsson, A.-K., Noren, L. & Withers, R. L. (2004). *Solid State Sci.* **6**, 725–733.
- Garg, G., Bobev, S. & Ganguli, A. K. (2001). *J. Alloys Compd.* **327**, 113–115.
- Goodenough, J. B. (1967). *Solid State Commun.* **5**, 577–580.
- Harris, D. C. (1970). *Can. Mineral.* **10**, 731–736.
- Hazen, R. M. & Yang, H. (1999). *Am. Mineral.* **84**, 1956–1960.
- Hollander, J. C. Th., Sawatzky, G. & Haas, C. (1974). *Solid State Commun.* **15**, 747–751.
- Jendrzewska, I. (2000). *J. Alloys Compd.* **305**, 90–92.
- Juszczuk, S. & Gogolowicz, M. (1991). *J. Magn. Magn. Mater.* **92**, 388–396.
- Kamat Dalal, V. N., Keer, H. V. & Biswas, A. B. (1971). *J. Inorg. Nucl. Chem.* **33**, 2839–2845.
- Kim, D., Gedanken, A., Tver’yanovich, Y. S., Lee, D. W. & Kim, B. K. (2006). *Mater. Lett.* **60**, 2807–2809.
- Lotgering, F. K. (1964). *Solid State Commun.* **2**, 55–56.
- Lotgering, F. K. & Van Staple, R. P. (1967). *Solid State Commun.* **5**, 143–146.
- Machatschki, F. & Stradner, E. (1952). *Anz. Oesterr. Akad. Wiss. Math. Naturwiss. Kl.* **89**, 211–213.
- Noh, H.-J., Kang, J.-S., Lee, S. S., Kim, G., Han, S.-W., Oh, S. J., Kim, J.-Y., Lee, H.-G., Yeo, S., Guha, S. & Cheong, S.-W. (2007). *Europhys. Lett.* **78**, 27004.
- Okońska-Kozłowska, I., Kopyczok, J., Lutz, H. D. & Stingl, T. (1993). *Acta Cryst.* **C49**, 1448–1449.
- Okońska-Kozłowska, I., Malicka, E., Waskowska, A., Heimann, J. & Mydlarz, T. (2001). *J. Solid State Chem.* **158**, 34–39.
- Payer, A., Schmalz, M., Schollhorn, R., Schlogl, R. & Ritter, C. (1990). *Mater. Res. Bull.* **25**, 515–522.
- Payer, A., Schollhorn, R., Ritter, C. & Paulus, W. (1993). *J. Alloys Compd.* **191**, 37–42.
- Robinson, S. C. & Brooker, E. J. (1952). *Am. Mineral.* **37**, 542–544.
- Rodic, D., Antic, B., Tellgren, R., Rundlof, H. & Blanus, J. (1998). *J. Magn. Magn. Mater.* **187**, 88–92.
- Sheldrick, G. M. (1997). *SHELXS97* and *SHELXL97*. University of Göttingen, Germany.
- Sheldrick, G. M. (2005). *SADABS*. Version 2.10. University of Göttingen, Germany.
- Skrzypek, D., Malicka, E., Waskowska, A., Widuch, S., Cichon, A. & Mydlarz, T. (2006). *J. Cryst. Growth.* **297**, 419–425.
- Williamson, D. P. & Grimes, N. W. (1974). *J. Phys. D Appl. Phys.* **7**, 1–6.
- Yamashita, O., Yamaguchi, Y., Nakatani, I. & Watanabe, H. & Masumoto, K. (1979). *J. Phys. Soc. Jpn.* **46**, 1145–1152.