

Negevite, the pyrite-type NiP<sub>2</sub>, a new terrestrial phosphide

SERGEY N. BRITVIN<sup>1,2,\*</sup>, MICHAEL N. MURASHKO<sup>1</sup>, YEVGENY VAPNIK<sup>3</sup>, YURY S. POLEKHOVSKY<sup>1,†</sup>,  
SERGEY V. KRIVOVICHEV<sup>1,2</sup>, OLEG S. VERESHCHAGIN<sup>1,‡</sup>, VLADIMIR V. SHILOVSKIKH<sup>1,4,§</sup>,  
AND MARIA G. KRZHIZHANOVSKAYA<sup>1</sup>

<sup>1</sup>St. Petersburg State University, Universitetskaya Nab. 7/9, 199034 St. Petersburg, Russia

<sup>2</sup>Kola Science Center, Russian Academy of Sciences, Fersman Str. 14, 184209 Apatity, Russia

<sup>3</sup>Department of Geological and Environmental Sciences, Ben-Gurion University of the Negev, P.O.B. 653, Beer-Sheva 84105, Israel

<sup>4</sup>Institute of Mineralogy, Urals Branch of Russian Academy of Science, Miass 456317, Russia

## ABSTRACT

Negevite, ideally NiP<sub>2</sub>, is a new phosphide mineral from pyrometamorphic complex of the Hatrurim Formation (the Mottled Zone), Southern Levant. It is found in phosphide assemblages of the Hatrurim Basin, south Negev Desert, Israel, and Daba-Siwaqa complex, Jordan. The mineral occurs as tiny isometric grains reaching 15 μm in size and forms intimate intergrowths with other phosphides related to the Fe-Ni-P system. In reflected light, negevite is white with yellowish tint and isotropic. Reflectance values for COM recommended wavelengths [*R* (%), λ (nm)] are as follows: 54.6 (470), 55.0 (546), 55.3 (589), 55.6 (650). Chemical composition of the holotype specimen (electron microprobe, wt<sup>9</sup>%): Ni 42.57, Co 3.40, Fe 2.87, P 42.93, S 8.33, total 100.10, corresponding to the empirical formula (Ni<sub>0.88</sub>Co<sub>0.07</sub>Fe<sub>0.06</sub>)Σ1.01(P<sub>1.68</sub>S<sub>0.31</sub>)Σ1.99. The crystal structure of negevite was solved and refined to *R*<sub>1</sub> = 1.73% based on 52 independent observed [*I* > 2σ(*I*)] reflections. The mineral is cubic, space group *Pa* $\bar{3}$ , *a* = 5.4816(5) Å, *V* = 164.71(3) Å<sup>3</sup>, and *Z* = 4. *D*<sub>x</sub> = 4.881(1) g/cm<sup>3</sup> calculated on the basis of the empirical formula. Negevite is a first natural phosphide belonging to the pyrite structure type. It is a chemical and structural analog of vaesite, NiS<sub>2</sub>, krutovite, NiAs<sub>2</sub>, and penroseite, NiSe<sub>2</sub>. The well-explored catalytic and photocatalytic properties of a synthetic counterpart of negevite could provide new insights into the possible role of higher phosphides as a source of low-valent phosphorus in prebiotic phosphorylation processes.

**Keywords:** NiP<sub>2</sub>, negevite, nickel phosphide, Fe-Ni-P system, pyrite, crystal structure, pyrometamorphism, prebiotic phosphorylation, meteorite

## INTRODUCTION

Since the discovery of first phosphide mineral, schreibersite (Fe,Ni)<sub>3</sub>P (Berzelius 1832), natural iron-nickel phosphides were recognized as mandatory accessory constituents of different meteorite groups (Buchwald 1975; Papike 1998). This mineral family is suggested to play an important role in the highly reduced assemblages of deep planetary interiors (Scott et al. 2007; Dera et al. 2008; Gu et al. 2011, 2012, 2014). Meanwhile, occurrences of terrestrial phosphides of non-anthropogenic origin are quite rare and confined to a few localities worldwide (e.g., Britvin et al. 2015); the most notable one is schreibersite in native iron from basalts of Disko Island, Greenland (Pauly 1969). The practical absence of phosphides in the present-day lithosphere cannot be accounted just for highly reducing conditions required for their formation. A possible explanation might imply oxidative decomposition of phosphides at the early stages of Earth evolution, leading to a release of low-valent phosphorus

required for initiation of prebiotic phosphorylation processes (Pasek et al. 2017; Kitadai and Maruyama 2018; Gibard et al. 2019). The recent discovery of rich phosphide assemblages preserved in geologically juvenile pyrometamorphic complex of the Mottled Zone (Hatrurim Formation) supports this point of view (Britvin et al. 2015).

Of 12 phosphide minerals related to the Fe-Ni-P system, nine are currently reported from the Hatrurim Formation (Table 1). We herein present the results of a study of a new mineral negevite, NiP<sub>2</sub>—the first natural phosphide that crystallizes in a pyrite

**TABLE 1.** Natural phosphides related to the Fe-Ni-P system

Mineral	End-member	Structure type	Occurrence	Reference
Schreibersite	Fe <sub>3</sub> P	Fe <sub>3</sub> P ( <i>I</i> $\bar{4}$ )	M T	Berzelius (1832)
Barringerite	Fe <sub>2</sub> P	Fe <sub>2</sub> P ( <i>P</i> 62 <i>m</i> )	M T	Buseck (1969); Britvin et al. (2017)
Allabogdanite	Fe <sub>2</sub> P	Co <sub>2</sub> Si ( <i>Pnma</i> )	M	Britvin et al. (2002)
Murashkoite	FeP	MnP ( <i>Pnma</i> )	T	Britvin et al. (2019b)
Zuktamrurite	FeP <sub>2</sub>	Marcasite ( <i>Pnmm</i> )	T	Britvin et al. (2019a)
Melliniite	(Ni,Fe) <sub>4</sub> P	Au <sub>4</sub> Al ( <i>P</i> 2 <sub>1</sub> 3)	M	Pratesi et al. (2006)
Nickelphosphide	Ni <sub>3</sub> P	Fe <sub>3</sub> P ( <i>I</i> $\bar{4}$ )	M	Britvin et al. (1999)
Nazarovite	Ni <sub>12</sub> P <sub>5</sub>	Ni <sub>12</sub> P <sub>5</sub> ( <i>I</i> 4/ <i>m</i> )	M T	Britvin et al. (2019c)
Transjordanite	Ni <sub>2</sub> P	Fe <sub>2</sub> P ( <i>P</i> 62 <i>m</i> )	T	Britvin et al. (2020a)
Orishchinite	Ni <sub>2</sub> P	Co <sub>2</sub> Si ( <i>Pnma</i> )	T	Britvin et al. (2019d)
Halamishite	Ni <sub>5</sub> P <sub>4</sub>	Ni <sub>5</sub> P <sub>4</sub> ( <i>P</i> 6 <sub>3</sub> <i>mc</i> )	T	Britvin et al. (2020b)
Negevite	NiP <sub>2</sub>	Pyrite ( <i>Pa</i> $\bar{3}$ )	T	This work

*Note:* Occurrence: M = meteoritic; T = terrestrial (the Hatrurim Formation).

\* E-mail: sergei.britvin@spbu.ru

† Deceased: September 29, 2018.

‡ Orcid 0000-0002-4811-2269

§ Orcid 0000-0003-2326-700X

structure type. Negevite is named for its type locality in the Negev Desert, Israel; both the mineral and the name have been approved by the Commission on New Minerals, Nomenclature and Classification of International Mineralogical Association (IMA 2013-104). The holotype specimen of negevite is deposited in the collections of the Mineralogical Museum of the Department of Mineralogy, St. Petersburg State University, Russia, catalog number 19604.

### OCCURRENCE AND GENERAL APPEARANCE


The Mottled Zone is the world's widest area of sedimentary rocks affected by combustion metamorphism, which is the suite of processes leading to high-temperature annealing and melting of surficial sediments (Sokol et al. 2005). Outcrops of the Mottled Zone are scattered across the territory of 150 × 200 km<sup>2</sup> in Southern Levant in the surroundings of the Dead Sea. The detailed description of the geological setting along with the hypotheses explaining the origin of the Mottled Zone are given in previous works (Gross 1977; Burg et al. 1991; Vapnik et al. 2007; Geller et al. 2012; Novikov et al. 2013). Metamorphic processes were followed by pronounced hydrothermal alteration and weathering stage (Gross 1977; Kolodny et al. 2014), that resulted in emergence of unique mineral assemblages, combining ultrahigh-temperature minerals (Weber and Bischoff 1994; Murashko et al. 2010; Sharygin et al. 2013; Galuskina et al. 2014; Khoury et al. 2016) and secondary phases corresponding to Earth's extreme oxidative and/or alkaline environment (Hauff et al. 1983; Sokol

et al. 2011; Galuskin et al. 2013, 2014).


Negevite was discovered in phosphide assemblages found along the upper stream of the Halamish Wadi, Hatrurim Basin, Southern Negev desert, Israel (Britvin et al. 2015). The mineral forms irregular minute grains up to 15 μm in size intimately intergrown with murashkoite, zuktamrurite, transjordanite, or halamishite (Fig. 1). Phosphide assemblages often occur together with magnetite, pyrrhotite, and andradite in diopside microbreccia that is severely altered by hydrothermal and weathering processes (Fig. 1). Secondary minerals are comprised of calcite and unidentified X-ray amorphous Ca-Fe hydrous silicates and phosphates. The Hatrurim Basin is a type locality for negevite. Later, the mineral was identified in one sample of weathered pyrometamorphic paralavas of the Daba-Siwaqa complex (Um Al-Rasas Sub-District, 80 km SSE of Amman, Jordan, 31° 21'52" N, 36° 10'55" E) where it forms micrometer-sized aggregates of irregularly fractured grains often intergrown with transjordanite and zuktamrurite (Fig. 2).

### PHYSICAL PROPERTIES AND CHEMICAL COMPOSITION

In reflected light, negevite has a white color with bluish tint (Supplemental<sup>1</sup> Fig. 1A). It is optically isotropic and has no internal reflections. Reflectance values (Supplemental<sup>1</sup> Table S1) were measured in air by means of a MSF-21 spectrophotometer (LOMO, St. Petersburg, Russia) using monochromator slit of 0.4 mm and beam diameter of 0.1 mm, against a WTiC standard. The mineral has no observable cleavage. Due to the small size

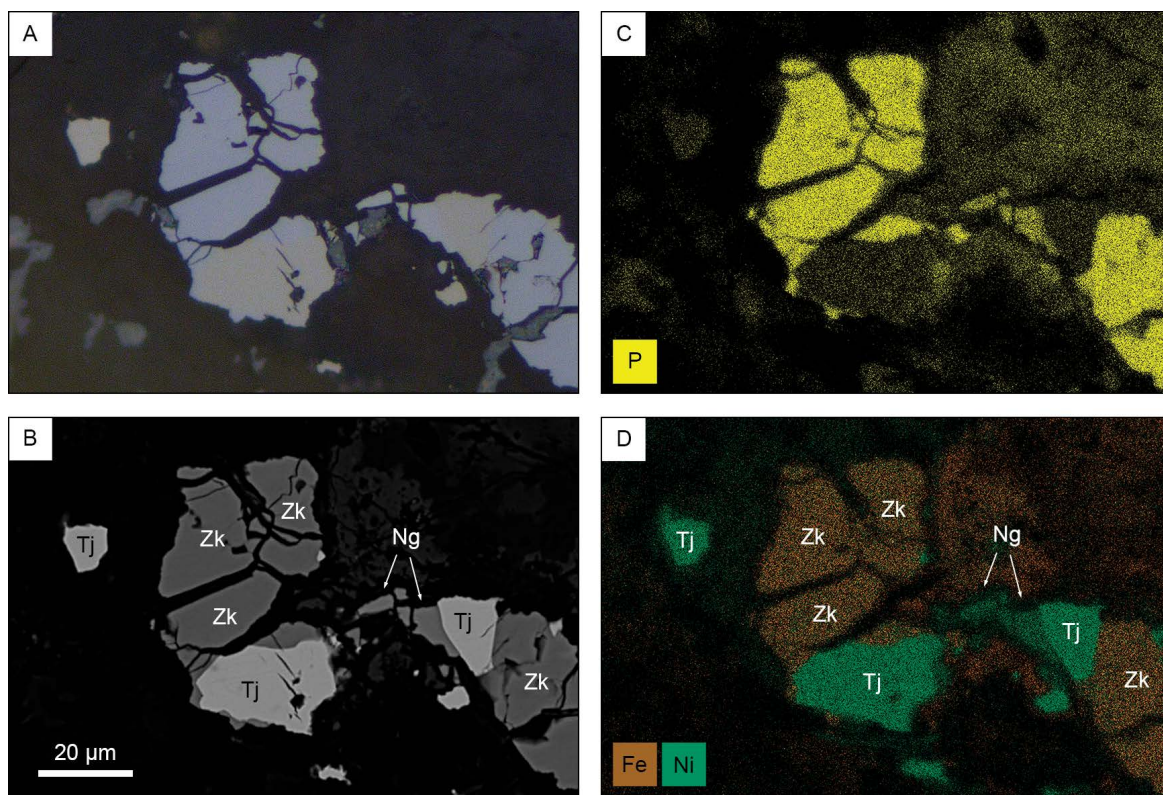

**FIGURE 1.** Negevite in phosphide assemblages of the Halamish wadi, Hatrurim Basin, Southern Negev Desert, Israel. (a) Photomicrograph in reflected light. (b) The same area, SEM BSE image. (c) Element distribution map for phosphorus. (d) Element distribution map for iron and nickel. Abbreviations: Ng = negevite (NiP<sub>2</sub>); Zk = zuktamrurite (FeP<sub>2</sub>); Tj = transjordanite (Ni<sub>2</sub>P). (Color online.).

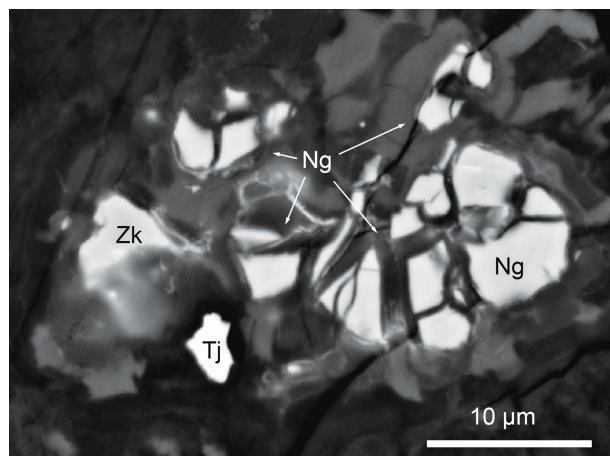

**FIGURE 2.** Fractured grain of Ag-bearing negevite among secondary Ca-Fe-silicates in altered pyroxene-anorthite paralava. Note grains of Ag-free transjordanite and zuktamrurite associated with negevite. Daba-Siwaqa complex, Transjordan plateau, Jordan. SEM BSE image. Abbreviations: Ng = negevite (NiP<sub>2</sub>); Zk = zuktamrurite (FeP<sub>2</sub>); Tj = transjordanite (Ni<sub>2</sub>P).

of the grains available, microindentation hardness could not be measured. The calculated density of the holotype specimen calculated for an empirical formula is 4.881(1) g/cm<sup>3</sup>. Negevite is insoluble in cool 10% HCl. Chemical composition of negevite and associated phosphides were studied in carbon-coated polished thick sections by means of a Hitachi S-3400N scanning electron microscope equipped with (1) an Oxford Instruments AzTec Energy X-Max 20 energy-dispersive (EDX) spectrometer and (2) an INCA WAVE 500 wavelength-dispersive (WDX) spectrometer. Preliminary screening of chemical composition and elemental mapping (Figs. 1c and 1d) was carried out in EDX mode, whereas quantitative data (Table 1) were obtained with WDX spectrometer using the following analytical standards: GaP (PKα), pyrite (FeKα, SKα), PbSe (SeLα), metallic Co (CoKα), Ni (NiKα), Mo (MoLα), Ag (AgLα). The measurement conditions were: 20 kV accelerating voltage, 15 nA beam current, peak counting time, 20 s peak counting time, 10 s background counting time. Chemical composition of the holotype negevite (Table 2) corresponds to the empirical formula (Ni<sub>0.88</sub>Co<sub>0.07</sub>Fe<sub>0.06</sub>)Σ1.01 (P<sub>1.68</sub>S<sub>0.31</sub>)Σ1.99 leading to the ideal formula NiP<sub>2</sub>.

### X-RAY SINGLE-CRYSTAL STUDY

To establish and refine the crystal structure of negevite, a ~10 μm single-crystal grain of the mineral was extracted from the polished section, mounted onto the glass fiber and subjected to a conventional X-ray single-crystal data collection by means of a Bruker APEX Kappa DUO CCD diffractometer. Data processing and integration routines were performed using a Bruker AXS instrument built-in software (Bruker 2003). The crystal structure of negevite was solved by direct methods and refined assuming NiP<sub>2</sub> formula, by means of SHELX-2018 software (Sheldrick 2015) incorporated into an Olex2 program environment (Dolomanov et al. 2009). The essential parameters of data collection and structure refinement are summarized in Supplemental<sup>1</sup> Table S2; the complete structural information can

be retrieved from the CIF file in the Supplementary Data (see also CSD entry 1936174). The insufficient amount of substance precluded obtaining experimental X-ray powder diffraction data for the mineral. Therefore, the powder diffraction pattern of negevite was calculated for CuKα<sub>1</sub> radiation on the basis of refined atomic coordinates and unit-cell metrics, using ATOMS v.5.0 software (Dowty 2006) (Supplemental<sup>1</sup> Table S3).

### DISCUSSION

Negevite is the first natural phosphide related to a pyrite structure type (Fig. 3). From the crystal-chemical point of view, the mineral can be regarded as phosphide analog of either vaesite, NiS<sub>2</sub>, krutaite, NiAs<sub>2</sub>, and penroseite, NiSe<sub>2</sub> (Table 3). Though the ideal formula of negevite is NiP<sub>2</sub>, its real composition shows substantial (up to 0.48 atoms per MX<sub>2</sub> formula) contents of sulfur (Table 2), suggesting the occurrence of at least partial isomorphism along the join NiP<sub>2</sub>–NiS<sub>2</sub>. Substitution of P for S correlates with an increase of the unit-cell parameter of negevite as compared to pure NiP<sub>2</sub> (Table 3).

Contrary to the synthetic marcasite-type FeP<sub>2</sub> and its natural analog, zuktamrurite (Table 1), NiP<sub>2</sub> can exist in two polymorphic modifications, both of which are stable under ambient conditions: (1) cubic, pyrite-type one (Donohue et al. 1968) and (2) monoclinic polymorph (space group C2/c) that has no sulfide or phosphide structural analogs (Larsson 1965; Orishchin et al. 2000). Synthetic pyrite-type NiP<sub>2</sub> was first synthesized under a high-pressure–high-temperature environment and thus was considered to be metastable, high-pressure polymorph of NiP<sub>2</sub> (Donohue et al. 1968). However, further studies revealed that this modification can be obtained using different methods at atmospheric pressure: via solid-state synthesis (Barry and Gillan 2009) and even by “soft chemistry” solvothermal techniques (Barry and Gillan 2008). Because NiP<sub>2</sub> was found to be promising material in modern electrochemical and catalytic applications (Gillot et al. 2005; Jiang et al. 2014), its chemical and physical character-

**TABLE 2.** Chemical composition of negevite and associated phosphides

Mineral	Ng	Ng	Ng	Tj	Zk	Ng	Zk	Tj
Locality	HB	HB	HB	HB	HB	DS	DS	DS
Notes	Holotype							
	wt%							
Ni	42.57	38.25	37.77	71.95	8.83	38.79	15.66	74.80
Co	3.40	2.92	3.44	0.30	1.24	3.40	0.37	0.15
Fe	2.87	6.15	6.41	6.26	36.74	5.12	30.87	3.30
Ag	–	–	–	–	–	1.01	–	–
P	42.93	40.05	40.07	21.14	52.25	39.51	51.43	21.09
S	8.33	12.12	12.78	0.00	1.51	10.82	0.00	0.00
Se	–	–	0.24	–	–	–	–	–
Total	100.10	99.49	100.71	99.65	100.57	98.65	98.33	99.34
	Formula amounts (3 apfu)							
Ni	0.88	0.79	0.77	1.82	0.18	0.82	0.32	1.90
Co	0.07	0.06	0.07	0.01	0.02	0.07	0.01	0.00
Fe	0.06	0.13	0.14	0.17	0.77	0.11	0.67	0.09
Ag	–	–	–	–	–	0.01	–	–
Σ	1.01	0.98	0.98	2.00	0.97	1.01	1.00	1.99
P	1.68	1.56	1.55	1.01	1.97	1.57	2.00	1.01
S	0.31	0.46	0.48	–	0.06	0.42	–	–
Se	–	–	0.004	–	–	–	–	–
Σ	1.99	2.02	2.03	1.01	2.03	1.99	2.00	1.01

Notes: Abbreviations: Ng = negevite; Tj = transjordanite; Zk = zuktamrurite. Localities: HB = Hatrurim Basin, Israel; DS = Daba-Siwaqa complex, Jordan. The bar “–” denotes below detection limit (<0.05 wt%).



istics were studied in detail. In particular, it was determined that pyrite-type NiP<sub>2</sub> is a low-temperature modification stable below 600 °C (Owens-Baird et al. 2019). Moreover, it was shown that transformation of cubic NiP<sub>2</sub> into the monoclinic modification is irreversible, implying that the presence of cubic NiP<sub>2</sub> in a given assemblage shows that the temperature has never passed the level of cubic-to-monoclinic transition (Owens-Baird et al. 2019). These results could be helpful in understanding the formation conditions of natural phosphide assemblages of the Mottled Zone (Britvin et al. 2015). However, the presence of sulfur in the composition of natural negevite (Table 2) might stabilize its pyrite-type structure toward higher transition temperatures.


An interesting feature of negevite from the Daba-Siwaqa complex in Jordan is its relative enrichment in Ag (Table 2). It becomes even more attractive taking into account the absence of Ag in closely associated zuktamurrite, FeP<sub>2</sub>, and transjordanite,

Ni<sub>2</sub>P (Fig. 2, Table 2). Ag is an element that is structurally incompatible with Ni. Synthetic phosphide AgP<sub>2</sub> is known though it is not isostructural with negevite (Möller and Jeitschko 1982). Recent investigation of Ag-doped synthetic pyrite demonstrated that it might contain up to 0.4 wt% (3820 ppm) Ag incorporated via mechanism of lattice-scale structural defects (Li and Ghahreman 2018). Therefore, one can assume that minor (0.01 atoms per formula unit) incorporation of Ag into negevite is also permissible.

**TABLE 3.** Unit-cell parameters of negevite and related minerals and compounds

Mineral	Negevite	Synthetic	Vaesite	Krutovite	Penroseite
Ideal formula	NiP <sub>2</sub>	NiP <sub>2</sub>	NiS <sub>2</sub>	NiAs <sub>2</sub>	NiSe <sub>2</sub>
<i>a</i> (Å)	5.4816	5.4475	5.6679	5.7634	5.988
Reference	[1]	[2]	[3]	[4]	[5]

Notes: [1] This work; [2] Owens-Baird et al. (2019); [3] Kerr (1945); [4] Donohue et al. (1968); Vinogradova et al. (1976); [5] Bindi et al. (2008).

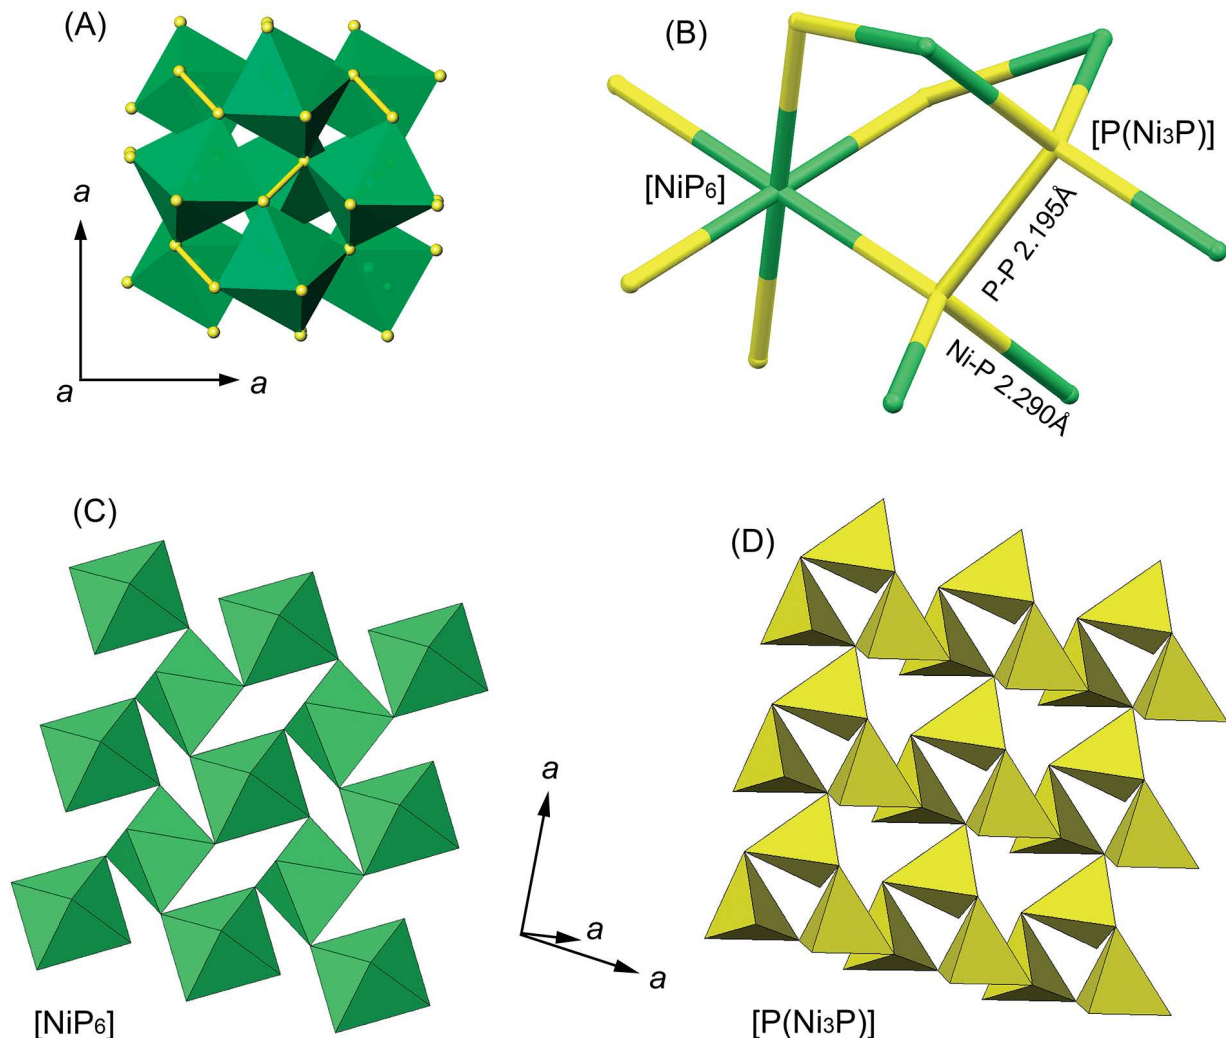

**FIGURE 3.** Crystal structure of negevite (pyrite structure type). (a) General view: corner-sharing [NiP<sub>6</sub>] octahedra (green) linked by P–P “dumbbell” bonds (yellow) characteristic of the pyrite structure. (b) Skeletal view of [NiP<sub>6</sub>] octahedron connected to [P(Ni<sub>3</sub>P)] tetrahedra. (c) Slice of substructure framework composed of corner-sharing [NiP<sub>6</sub>] octahedra. (d) Slice composed of [P(Ni<sub>3</sub>P)] tetrahedra. Legend: green = Ni [4*a*; 0, 0]; yellow = P [8*c*; 0.3844(1), *x*, *x*]. (Color online.)

## IMPLICATIONS

Discovery of negevite, naturally occurring NiP<sub>2</sub>, might have promising implications considering the general role of phosphides as a source of phosphorus required for phosphorylation processes. It was shown that gentle aquatic oxidation of schreibersite, (Fe,Ni)<sub>3</sub>P, results in a release of diverse water-soluble phosphorus compounds that could serve as building blocks during prebiotic phosphorylation at the early stages of Earth evolution (Pasek et al. 2017; Kitadai and Maruyama 2018; Gibard et al. 2019). Other phosphides related to the Fe-Ni-P system (Table 1) were not considered for that role. However, our recent findings demonstrate that these minerals could be formed in a reducing environment of Archean era as well (Britvin et al. 2015). In that respect, unique catalytic and electrochemical properties of the synthetic counterpart of negevite, including its ability to photo-induced water splitting under soft conditions and hydrogenation activity (Gillot et al. 2005; Jiang et al. 2014), could provide new routes for further exploration of possible natural phosphorylation pathways. The discovery of negevite-bearing phosphide assemblages of the Mottled Zone undoubtedly implies the extremely reducing (“super-reducing”) environment occurred during their crystallization. This enigma of the Hatrurim Formation is not yet resolved and requires the gathering of further evidence.

## ACKNOWLEDGMENTS AND FUNDING

This research was funded by Russian Science Foundation, grant 18-17-00079. We thank the referees, Evgeny Galuskin and Inna Lykova, for the helpful comments and discussion of the manuscript. Associate Editor Fabrizio Nestola is thanked for handling of the review process. The authors thank X-ray Diffraction Centre, “Geomodel” Resource Centre and Nanophotonics Resource Centre of St. Petersburg State University for providing instrumental and computational resources.

## REFERENCES CITED

- Barry, B.M., and Gillan, E.G. (2008) Low-temperature solvothermal synthesis of phosphorus-rich transition-metal phosphides. *Chemistry of Materials*, 20, 2618–2620.
- (2009) A general and flexible synthesis of transition-metal polyphosphides via PCl<sub>3</sub> elimination. *Chemistry of Materials*, 21, 4454–4461.
- Berzelius, J.J. (1832) Undersökning af en vid Bohumiliz i Böhmen funnen jernmassa. *Kongelige Svenska Vetenskaps-Academiens Handlingar*, 106–119.
- Bindi, L., Cipriani, C., Pratesi, G., and Trosti-Ferroni, R. (2008) The role of isomorphous substitutions in natural selenides belonging to the pyrite group. *Journal of Alloys and Compounds*, 459, 553–556.
- Britvin, S.N., Kolomensky, V.D., Boldyreva, M.M., Bogdanova, A.N., Kretser, Yu.L., Boldyreva, O.N., and Rudashevskii, N.S. (1999) Nickelphosphide, (Ni,Fe)<sub>3</sub>P, the nickel analog of schreibersite. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, 128, 64–72 (in Russian).
- Britvin, S.N., Rudashevsky, N.S., Krivovichev, S.V., Burns, P.C., and Polekhovskiy, Y.S. (2002) Allabogdanite, (Fe,Ni)<sub>2</sub>P, a new mineral from the Onello meteorite: The occurrence and crystal structure. *American Mineralogist*, 87, 1245–1249.
- Britvin, S.N., Murashko, M.N., Vapnik, Ye., Polekhovskiy, Yu.S., and Krivovichev, S.V. (2015) Earth's phosphides in Levant and insights into the source of Archean prebiotic phosphorus. *Scientific Reports*, 5, 8355.
- Britvin, S.N., Murashko, M.N., Vapnik, E., Polekhovskiy, Yu.S., Krivovichev, S.V. (2017) Barringerite Fe<sub>2</sub>P from pyrometamorphic rocks of the Hatrurim Formation, Israel. *Geology of Ore Deposits*, 59, 619–625.
- Britvin, S.N., Murashko, M.N., Vapnik, Ye., Polekhovskiy, Yu.S., Krivovichev, S.V., Vereshchagin, O.S., Vlasenko, N.S., Shilovskikh, V.V., and Zaitsev, A.N. (2019a) Zuktamurite, FeP<sub>2</sub>, a new mineral, the phosphide analogue of löllingite, FeAs<sub>2</sub>. *Physics and Chemistry of Minerals*, 46, 361–369.
- Britvin, S.N., Vapnik, Ye., Polekhovskiy, Yu.S., and Krivovichev, S.V., Krzhizhanovskaya, M.G., Gorelova, L.A., Vereshchagin, O.S., Shilovskikh, V.V., and Zaitsev, A.N. (2019b) Murashkoite, FeP, a new terrestrial phosphide from pyrometamorphic rocks of the Hatrurim Formation, Southern Levant. *Mineralogy and Petrology*, 113, 237–248.
- Britvin, S.N., Murashko, M.N., Krzhizhanovskaya, M.G., Vereshchagin, O.S., Vapnik, Y., Shilovskikh, V.V., and Lozhkin, M.S. (2019c) Nazarovite, IMA 2019-013. *CNMNC Newsletter No. 50*; *Mineralogical Magazine*, 83, doi: 10.1180/mgm.2019.46.
- Britvin, S.N., Murashko, M.N., Vapnik, Y., Zaitsev, A.N., Shilovskikh, V.V., Vasiliev, E.A., Krzhizhanovskaya, M.G., and Vlasenko, N.S. (2019d) IMA 2019-039. *CNMNC Newsletter No. 51*; *European Journal of Mineralogy*, 31, doi: 10.1127/ejm/2019/0031-2894.
- Britvin, S.N., Murashko, M.N., Vapnik, Ye., Polekhovskiy, Yu.S., Krivovichev, S.V., Krzhizhanovskaya, M.G., Vereshchagin, O.S., Shilovskikh, V.V., and Vlasenko, N.S. (2020a) Transjordanite, Ni<sub>2</sub>P, a new terrestrial and meteoritic phosphide, and natural solid solutions barringerite–transjordanite (hexagonal Fe<sub>2</sub>P–Ni<sub>2</sub>P). *American Mineralogist*, 105, doi: 10.2138/am-2020-7275.
- Britvin, S.N., Murashko, M.N., Vapnik, Ye., Polekhovskiy, Yu.S., Krivovichev, S.V., Vereshchagin, O.S., Shilovskikh, V.V., Vlasenko, N.S., and Krzhizhanovskaya, M.G. (2020b) Halamishite, Ni<sub>3</sub>P, a new terrestrial phosphide in the Ni–P system. *Physics and Chemistry of Minerals*, doi: 10.1007/s00269-019-01073-7.
- Bruker (2003) SAINT (ver. 7.60A). Bruker AXS Inc., Madison, Wisconsin.
- Buchwald, V.F. (1975) *Handbook of iron meteorites*. University of California Press, Berkeley, Los Angeles.
- Burg, A., Starinsky, A., Bartov, Y., and Kolodny, Ye. (1991) Geology of the Hatrurim Formation (“Mottled Zone”) in the Hatrurim basin. *Israel Journal of Earth Sciences*, 40, 107–124.
- Buseck, P.R. (1969) Phosphide from meteorites: Barringerite, a new iron-nickel mineral. *Science*, 165, 169–171.
- Dera, P., Lavina, B., Borkowski, L.A., Prakapenka, V.B., Sutton, S.R., Rivers, M.L., Downs, R.T., Boctor, N.Z., and Prewitt, C.T. (2008) High-pressure polymorphism of Fe<sub>2</sub>P and its implications for meteorites and Earth's core. *Geophysical Research Letters*, 35, L10301.
- Dolomanov, O.V., Bourhis, L.J., Gildea, R.J., Howard, J.A., and Puschmann, H. (2009) OLEX2: a complete structure solution, refinement and analysis program. *Journal of Applied Crystallography*, 42, 339–341.
- Donohue, P.C., Bither, T.A., and Young, H.S. (1968) High-pressure synthesis of pyrite-type nickel diphosphide and nickel diarsenide. *Inorganic Chemistry*, 7, 998–1001.
- Dowty, E. (2006) *ATOMS for Windows*. Shape Software, Kingsport, Tennessee.
- Galuskin, E.V., Kusz, J., Armbruster, T., Galuskina, I.O., Marzec, K., Vapnik, Ye., and Murashko, M. (2013) Vorlanite, (CaU<sup>6+</sup>)O<sub>4</sub>, from Jabal Harmun, Palestinian Autonomy, Israel. *American Mineralogist*, 98, 1938–1942.
- Galuskin, E.V., Galuskina, I.O., Kusz, J., Armbruster, T., Marzec, K., Dzierzanowski, P., and Murashko, M. (2014) Vapnikite Ca<sub>2</sub>UO<sub>6</sub>—a new double perovskite mineral from pyrometamorphic larnite rocks of the Jabal Harmun, Palestine Autonomy, Israel. *Mineralogical Magazine*, 78, 571–581.
- Galuskina, I.O., Vapnik, Y., Lazić, B., Armbruster, T., Murashko, M., and Galuskin, E.V. (2014) Harmunite CaFe<sub>2</sub>O<sub>4</sub>: a new mineral from the Jabal Harmun, West Bank, Palestinian Autonomy, Israel. *American Mineralogist*, 99, 965–975.
- Geller, Y.I., Burg, A., Halicz, L., and Kolodny, Y. (2012) System closure during the combustion metamorphic “Mottled Zone” event, Israel. *Chemical Geology*, 334, 25–36.
- Gibard, C., Gorrell, I.B., Jimenez, E.I., Kee, T.P., Pasek, M.A., and Krishnamurthy, R. (2019) Geochemical sources and availability of amidophosphates on the early Earth. *Angewandte Chemie, International Edition*, 58, 8151–8155.
- Gross, S. (1977) The mineralogy of the Hatrurim Formation, Israel. *Geological Survey of Israel Bulletin*, 70, 1–80.
- Gillot, F., Boyanov, S., Dupont, L., Doublet, M.-L., Morcrette, M., Monconduit, L., and Tarascon, J.-M. (2005) Electrochemical reactivity and design of NiP<sub>2</sub> negative electrodes for secondary Li-ion batteries. *Chemistry of Materials*, 17, 6327–6337.
- Gu, T., Wu, X., Qin, S., and Dubrovinsky, L. (2011) In situ high-pressure study of FeP: Implications for planetary cores. *Physics of the Earth and Planetary Interiors*, 184, 154–159.
- Gu, T., Wu, X., Qin, S., Liu, J., Li, Y., and Zhang, Y. (2012) High-pressure and high-temperature in situ X-ray diffraction study of FeP<sub>2</sub> up to 70 GPa. *Chinese Physics Letters*, 29, 026102.
- Gu, T., Fei, Y., Wu, X., and Qin, S. (2014) High-pressure behavior of Fe<sub>2</sub>P and the role of phosphorus in planetary cores. *Earth and Planetary Science Letters*, 390, 296–303.
- Hauff, P.L., Foord, E.E., Rosenblum, S., and Hakkı, W. (1983) Hashemite, Ba(Cr,Si)O<sub>4</sub>, a new mineral from Jordan. *American Mineralogist*, 68, 1223–1225.
- Jiang, P., Liu, Q., and Sun, X. (2014) NiP<sub>2</sub> nanosheet arrays supported on carbon cloth: an efficient 3D hydrogen evolution cathode in both acidic and alkaline solutions. *Nanoscale*, 6, 13440–13445.
- Kerr, P.F. (1945) Cattierite and vaesite: New Co-Ni minerals from the Belgian Congo. *American Mineralogist*, 30, 483–497.
- Khoury, H.N., Sokol, E.V., Kokh, S.N. Seryotkin, Yu.V., Kozmenko, O.A., Goryainov, S.V., and Clark, I.D. (2016) Intermediate members of the lime-monteponite solid solutions (Ca<sub>1-x</sub>Cd<sub>x</sub>O, x = 0.36–0.55): Discovery in natural occurrence. *American Mineralogist*, 101, 146–161.
- Kitadai, N., and Maruyama, S. (2018) Origins of building blocks of life: A review. *Geoscience Frontiers*, 9, 1117–1153.
- Kolodny, Y., Burg, A., Geller, Y.I., Halicz, L., and Zakon, Y. (2014) Veins in the combusted metamorphic rocks, Israel; Weathering or a retrograde event? *Chemical Geology*, 385, 140–155.

- Larsson, E. (1965) An X-ray investigation of the Ni-P system and the crystal structures of NiP and NiP<sub>2</sub>. *Arkiv för Kemi*, 23, 335–365.
- Li, L., and Ghahreman, A. (2018) The synergistic effect of Cu<sup>2+</sup>–Fe<sup>2+</sup>–Fe<sup>3+</sup> acidic system on the oxidation kinetics of Ag-doped pyrite. *The Journal of Physical Chemistry C*, 122, 26897–26909.
- Möller, M.H., and Jeitschko, W. (1982) Darstellung, Eigenschaften und Kristallstruktur von Cu<sub>2</sub>P<sub>7</sub> und Strukturverfeinerungen von CuP<sub>2</sub> und AgP<sub>2</sub>. *Zeitschrift für Anorganische und Allgemeine Chemie*, 491, 225–236.
- Murashko, M.N., Chukanov, N.V., Mukhanova, A.A., Vapnik, E., Britvin, S.N., Krivovichev, S.V., Polekhovskiy, Yu.S., and Ivakin, Yu.D. (2010) Barioferrite BaFe<sub>12</sub>O<sub>19</sub>, a new magnetoplumbite-group mineral from Hatrurim Formation, Israel. *Geology of Ore Deposits*, 53(7), 558–563.
- Novikov, I., Vapnik, Ye., and Safonova, I. (2013) Mud volcano origin of the Mottled Zone, Southern Levant. *Geoscience Frontiers*, 4, 597–619.
- Orishchin, S.V., Babizhet'sky, V.S., and Kuz'ma, Yu.B. (2000) Reinvestigation of the NiP<sub>2</sub> structure. *Crystallography Reports*, 45, 894–895.
- Owens-Baird, B., Xu, J., Petrovykh, D.Y., Bondarchuk, O., Ziouani, Y., González-Ballesteros, N., Yox, P., Sapountzi, F.M., Niemantsverdriet, H., Kolen'ko, Yu.V., and Kovnir, K. (2019) NiP<sub>2</sub>: a story of two divergent polymorphic multifunctional materials. *Chemistry of Materials*, 31, 3407–3418.
- Papike, J.J., Ed. (1998) *Planetary Materials*, 36, 1052 p. Reviews in Mineralogy, Mineralogical Society of America, Chantilly, Virginia.
- Pasek, M.A., Gull, M., and Herschy, B. (2017) Phosphorylation on the early Earth. *Chemical Geology*, 475, 149–170.
- Pauly, H. (1969) White cast iron with cohenite, schreibersite, and sulphides from Tertiary basalts on Disko, Greenland. *Bulletin of the Geological Society of Denmark*, 19, 8–26.
- Pratesi, G., Bindi, L., and Moggi-Ceccati, V. (2006) Icosahedral coordination of phosphorus in the crystal structure of melliniite, a new phosphide mineral from the Northwest Africa 1054 acapulcoite. *American Mineralogist*, 91, 451–454.
- Scott, H.P., Huggins, S., Frank, M.R., Maglio, S.J., Martin, C.D., Meng, Y., Santillán, J., and Williams, Q. (2007) Equation of state and high-pressure stability of Fe<sub>3</sub>P-schreibersite: Implications for phosphorus storage in planetary cores. *Geophysical Research Letters*, 34, L06302.
- Sharygin, V.V., Lazic, B., Armbruster, T.M., Murashko, M.N., Wirth, R., Galuskina, I., Galuskin, E.V., Vapnik, Ye., Britvin, N., and Logvinova, A.M. (2013) Shulamitite Ca<sub>2</sub>TiFe<sup>3+</sup>AlO<sub>8</sub>—a new pyroxene-related mineral from Hatrurim Basin, Israel. *European Journal of Mineralogy*, 25, 97–111.
- Sheldrick, G.M. (2015) Crystal structure refinement with *SHELXL*. *Acta Crystallographica*, C71, 3–8.
- Sokol, E.V., Maksimova, N.V., Nigmatulina, E.N., Sharygin, V.V., and Kalugin, V.M. (2005) *Combustion Metamorphism*, 284 p. Publishing House of the Siberian Branch of the Russian Academy of Science, Novosibirsk (in Russian).
- Sokol, E.V., Gaskova, O.L., Kokh, S.N., Kozmenko, O.A., Seryotkin, Y.V., Vapnik, Y., Murashko, M.N. (2011) Chromatite and its Cr<sup>3+</sup>- and Cr<sup>6+</sup>-bearing precursor minerals from the Nabi Musa Mottled Zone complex, Judean Desert. *American Mineralogist*, 96, 659–674.
- Vapnik, Y., Sharygin, V.V., Sokol, E.V., and Shagam, R. (2007) Paralavas in a combustion metamorphic complex: Hatrurim Basin, Israel. *The Geological Society of America, Reviews in Engineering Geology*, 18, 133–153.
- Vinogradova, R.A., Rudashevskii, N.S., Bud'ko, I.A., Boček, L.I., Kaspar, P., and Padera, K. (1976) Krutovite—a new cubic nickel diarsenide. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, 105, 59–71 (in Russian).
- Weber, D., and Bischoff, A. (1994) Grossite (CaAl<sub>4</sub>O<sub>7</sub>)—a rare phase in terrestrial and extraterrestrial rocks. *European Journal of Mineralogy*, 6, 591–594.

MANUSCRIPT RECEIVED JULY 3, 2019

MANUSCRIPT ACCEPTED OCTOBER 31, 2019

MANUSCRIPT HANDLED BY FABRIZIO NESTOLA

### Endnote:

<sup>1</sup>Deposit item AM-20-37192, CIF. Deposit items are free to all readers and found on the MSA website, via the specific issue's Table of Contents (go to [http://www.minsocam.org/MSA/AmMin/TOC/2020/Mar2020\\_data/Mar2020\\_data.html](http://www.minsocam.org/MSA/AmMin/TOC/2020/Mar2020_data/Mar2020_data.html)).