

A chemical and structural re-examination of fettelite samples from the type locality, Odenwald, southwest Germany

L. BINDI^{1,2,*}, R. T. DOWNS³, P. G. SPRY⁴, W. W. PINCH⁵ AND S. MENCHETTI¹

¹ Dipartimento di Scienze della Terra, Università degli Studi di Firenze, Via G. La Pira 4, I-50121 Firenze, Italy

² CNR – Istituto di Geoscienze e Georisorse, Sezione di Firenze, Via G. La Pira 4, I-50121 Firenze, Italy

³ Department of Geosciences, University of Arizona, Tucson, Arizona 85721-0077, USA

⁴ Department of Geological and Atmospheric Sciences, 253 Science I, Iowa State University, Ames, Iowa 50011-3212, USA

⁵ 19 Stonebridge Lane, Pittsford, New York 14534, USA

[Received 20 November 2011; Accepted 22 February 2012; Associate Editor: Allan Pring]

ABSTRACT

The crystal structure and chemical composition of two samples of fettelite from the type locality, including a portion of the holotype material, was investigated to verify if a previously proposed revision of the chemical formula was applicable, and to study the role of cation substitution for Hg that would suggest new members of the fettelite family. The crystal structure of fettelite from the type locality was found to be equivalent to that reported previously for the Chilean occurrence, and consists of an alternation of two kinds of layers along *c*: layer *A* with general composition $[\text{Ag}_6\text{As}_2\text{S}_7]^{2-}$ and layer *B* with general composition $[\text{Ag}_{10}\text{HgAs}_2\text{S}_8]^{2+}$. In this structure, the Ag atoms occur in various coordination configurations, varying from quasi-linear to quasi-tetrahedral, the AsS_3 groups form pyramids as are typically observed in sulfosalts, and Hg links two sulfur atoms in a linear coordination. The refined compositions for the crystals in this study, $[\text{Ag}_6\text{As}_2\text{S}_7][\text{Ag}_{10}(\text{Fe}_{0.53}\text{Hg}_{0.47})\text{As}_2\text{S}_8]$ (R100124) and $[\text{Ag}_6\text{As}_2\text{S}_7][\text{Ag}_{10}(\text{Hg}_{0.79}\text{Cu}_{0.21})\text{As}_2\text{S}_8]$ (R110042), clearly indicate that new mineral species related to fettelite are likely to be found in nature.

KEYWORDS: fettelite, Hg-sulfosalts, pearceite, polybasite, crystal structure, Glasberg quarry, Odenwald, Germany.

Introduction

FETTELITE is a rare Hg-bearing sulfosalt that was first identified as a new mineral species by Wang and Paniagua (1996) during a study of silver minerals from the Glasberg quarry, Nieder-Beerbach, Odenwald, southwest Germany. Based on microprobe data, they reported an ideal chemical formula of $\text{Ag}_{24}\text{HgAs}_5\text{S}_{20}$. The crystal

structure of fettelite was later solved and refined using intensity data collected from a twinned crystal from Chañarcillo, Copiapó Province, Chile, both at room temperature (Bindi *et al.*, 2009) and at high temperature (Bindi and Menchetti, 2011). The structural study at room temperature revealed that, in spite of strong hexagonal pseudosymmetry, the mineral is monoclinic (space group *C2*), intimately twinned with six twin domains, with $a = 26.0388(10)$, $b = 15.0651(8)$, $c = 15.5361(8)$ Å, $\beta = 90.48(1)^\circ$ and $V = 6094.2(5)$ Å³. On the basis of the information gained from this characterization, Bindi *et al.* (2009) revised the crystal-chemical formula to

* E-mail: luca.bindi@unifi.it

DOI: 10.1180/minmag.2012.076.3.07

$[\text{Ag}_6\text{As}_2\text{S}_7][\text{Ag}_{10}\text{HgAs}_2\text{S}_8]$ ($Z = 8$) and discussed the relationships between the data obtained from the Chilean fettelite and those reported previously for the mineral from the type locality, concluding that a difference in chemical composition (especially the Ag/Hg ratio) could explain the dissimilarities observed in the unit-cell values. However, as Wang and Paniagua (1996) did not carry out a precise X-ray study on the type specimen of fettelite, questions remain as to whether or not there are different members of the fettelite family in nature. Recently, a new sample from the type locality (Glasberg quarry, Nieder-Beerbach, Odenwald, southwest Germany) was donated to the RRUFF collection (sample R100124) by one of the authors (WWP). This sample shows an anomalous enrichment in iron, which suggests that there may be a possible new Fe-rich endmember. Motivated by this observation and by the possibility that there could be different fettelite-like minerals, we requested a portion of the holotype specimen, which is housed in the mineral collection of the Institute of Mineralogy at the University of Heidelberg.

Here we present a structural and chemical characterization of two samples of fettelite from the type locality in order to verify whether the revised chemical formula proposed by Bind *et al.* (2009) is applicable to the type fettelite sample, and to study the role of cation substitution for Hg, which might indicate new fettelite-like minerals.

Occurrence and physical and optical properties

The two samples studied here were not found *in situ*, but originate from the RRUFF Project collection (rruff.info/R100124, Fig. 1), and from a small portion (rruff.info/R110042, Fig. 2) of the holotype specimen, which is deposited in the Institute of Mineralogy at the University of Heidelberg. Both the fettelite samples come from the Glasberg quarry.

Fettelite from samples R100124 and R110042 is dark red to grey-black with a dark grey streak. It is opaque in transmitted light and has a metallic lustre. The crystals are brittle with perfect {001} cleavage and the fracture is uneven to subconchoidal. Micro-indentation measurements carried out with a VHN load of 20 g give a mean value of 122 kg mm^{-2} (range 111–131) and 143 kg mm^{-2} (range 131–150) for R100124 and R110042, respectively, corresponding to a Mohs hardness of about 3½.



FIG. 1. One of the samples (R100124) containing dark red fettelite.

In plane-polarized incident light, fettelite from both samples is greyish white in colour, with moderate bireflectance (from white to brownish grey). Between crossed polars, it shows weak anisotropy, with relatively strong red internal reflections. Reflectance measurements were performed in air using a Zeiss MPM-200 microphotometer equipped with a MSP-20 system processor on a Zeiss Axioplan ore microscope. The filament temperature was approximately 3350 K. Four wavelengths (471.1, 548.3, 586.6, and 652.3 nm) produced by an interference filter were used for the measurements, which were obtained from the specimen and calibrated using an SiC standard in the same focus conditions. The diameter of the circular area

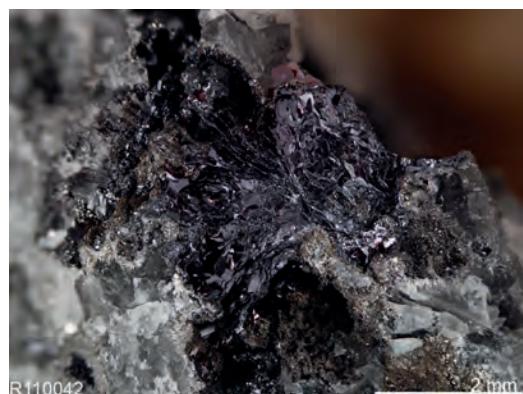


FIG. 2. Part of the holotype sample, R110042 containing dark red fettelite.

that was measured was 0.1 mm. Reflectance percentages for R_{\min} and R_{\max} are 28.2, 29.4 (471.1 nm), 25.0, 26.3 (548.3 nm), 22.9, 23.5 (586.6 nm), 20.9, 21.2 (652.3 nm), and 28.8, 29.9 (471.1 nm), 25.8, 27.0 (548.3 nm), 24.8, 25.6 (586.6 nm), 22.9, 23.7 (652.3 nm), for R100124 and R110042, respectively. Both of the fettelite samples from the type locality are slightly less reflective than fettelite from Chañarcillo (Bindi *et al.*, 2009).

Chemical composition

The chemical composition was determined using wavelength-dispersive spectrometry (WDS) by means of a JEOL JXA-8200 electron microprobe (sample R100124 and R110042) and a Cameca SX100 electron microprobe (sample R100124). Concentrations of major and minor elements were determined at an accelerating voltage of 15 kV and a beam current of 15 nA, with a 20 s counting time (spot size 1 μ m). For the WDS analyses the following lines were used (for both the instru-

ments): SK α , FeK α , CuK α , AsL α , AgL α , SbL β , PbM α and HgL α . The standards employed were pure metals for Cu and Ag, galena for Pb, pyrite for Fe and S, cinnabar for Hg, synthetic Sb₂S₃ for Sb, and synthetic As₂S₃ for As. The fettelite fragments were homogeneous to within analytical error. The average chemical compositions and the atomic ratios on the basis of 36 atoms are reported in Table 1, together with the chemical data given by Wang and Paniagua (1996) for type fettelite, and those reported by Bindi *et al.* (2009) for Chilean fettelite. On the basis of 36 atoms (see the structure description), the formulae can be written as $\text{Ag}_{16.45}(\text{Fe}_{0.89}\text{Hg}_{0.37}\text{Cu}_{0.01})_{\Sigma=1.27}(\text{As}_{4.03}\text{Sb}_{0.04})_{\Sigma=4.07}\text{S}_{14.21}$ and $\text{Ag}_{16.08}(\text{Hg}_{0.71}\text{Cu}_{0.13}\text{Fe}_{0.01})_{\Sigma=0.85}\text{As}_{3.80}\text{S}_{15.27}$, for R100124 and R110042, respectively. It appears therefore that the chemical formulae are rather far from ideal [e.g. $\Sigma S = 15$ a.p.f.u., $\Sigma(\text{As} + \text{Sb}) = 4$ a.p.f.u., Ag = 16 a.p.f.u.]. It should be noted, however, that fettelite from the type locality is strongly sensitive to the electron beam, which makes it difficult to obtain precise and accurate

TABLE 1. Electron microprobe data (wt.% elements) and atomic ratios for fettelite.

	This study (R100124)	Type locality This study (R110042)	Wang and Paniagua (1996)	Chañarcillo, Chile Bindi <i>et al.</i> (2009)
Ag	66.77	64.75	67.55	62.78
Cu	0.02	0.30	0.07	0.09
Pb	0.02	0.01	0.07	0.15
Tl	n.a.	n.a.	0.13	0.07
Fe	1.88	0.02	0.04	0.02
Hg	2.76	5.34	5.21	7.19
As	11.35	10.62	9.8	10.01
Sb	0.18	0.00	0.23	1.56
S	17.14	18.29	16.79	17.60
Total	100.12	99.33	99.89	99.47
Atomic ratio on the basis of 36 atoms				
Ag	16.45	16.08	17.19	15.92
Cu	0.01	0.13	0.03	0.04
Pb	0.00	0.00	0.01	0.02
Tl	—	—	0.02	0.01
Fe	0.89	0.01	0.02	0.01
Hg	0.37	0.71	0.71	0.98
As	4.03	3.80	3.59	3.65
Sb	0.04	0.00	0.05	0.35
S	14.21	15.27	14.38	15.02
Total	36.00	36.00	36.00	36.00

n.a.: not analysed.

microprobe data. Indeed, for most of the crystals, the electron beam caused Hg to vaporize from the sample and we observed a gradual reduction in the Hg content with time and corresponding damage to the sample surface. To minimize the beam damage, we reduced the beam current to 15 nA for the analyses listed in Table 1. It should be noted that Bindi *et al.* (2009) did not observe beam damage on the samples of fettelite from Chile. In that study, an accelerating voltage of 20 kV and a beam current of 40 nA were used. The reason for this difference is probably linked to the quality and the size of the crystals, which are larger and more homogeneous at the Chilean occurrence in comparison to the type locality (Figs 1 and 2; Wang and Paniagua, 1996).

X-ray crystallography

Two crystals were extracted from the polished microprobe sections produced from samples R100124 and R110042 and analysed using an Oxford Diffraction Xcalibur 3 diffractometer ($\text{MoK}\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$) fitted with a Sapphire 2 CCD detector (see Table 2 for details). As fettelite is commonly twinned, a full diffraction sphere of diffraction data was collected from both crystals. Intensity integration and standard Lorentz-polarization corrections were done with the *CrysAlis RED* (Oxford Diffraction, 2006) software package. The *ABSPACK* program, which is part of *CrysAlis RED* (Oxford Diffraction, 2006), was used to make absorption corrections. Subsequent calculations were conducted using the *JANA2006* program suite (Petříček *et al.*, 2006).

The crystal structures were refined in space group *C2* starting from the atom coordinates given by Bindi *et al.* (2009) for Chilean fettelite and taking into account the twin law that makes the twinned lattice appear to be hexagonal (i.e. twinning by metric merohedry; see Nespolo, 2004, and references therein). Refinement of the occupancy factors for all the Ag (Ag vs. Cu) atoms and for all the As (As vs. Sb) atoms for R100124 and R110042 produced site-scattering values consistent with pure Ag and As, respectively, but the Hg positions were partially occupied by a lighter element. In view of the WDS data, we chose to refine Hg vs. Fe for R100124, and Hg vs. Cu for R110042 (Table 3). At this stage, the residual values converged from $R = 0.065$ to $R = 0.058$ for R100124, and from $R = 0.072$ to $R = 0.069$ for R110042 [$2\sigma(I)$ level],

including all the collected reflections in the refinements. Based on these refinements, analyses of the difference Fourier synthesis maps suggested an additional twofold twin axis perpendicular to the previously determined threefold axis, leading to a second-degree twin. The introduction of only three new parameters (the new twin volume ratios) lowered the R values to 0.045 (R100124) and 0.057 (R110042), although the new domains were rather small in size (Table 2). At the last stage, using anisotropic displacement parameters for all atoms and no constraints, the residual values settled at $R = 0.031$ for 8136 independent observed reflections [$2\sigma(I)$ level] and 659 parameters and at $R = 0.034$ for all 16,981 independent reflections for R100124, and at $R = 0.043$ for 7445 independent observed reflections [$2\sigma(I)$ level] and 659 parameters and at $R = 0.049$ for all 17,368 independent reflections for R110042.

Table 2 contains further details of the refinement. Fractional atom coordinates and isotropic displacement parameters are given in Table 3. Bond distances are listed in Table 4. Anisotropic displacement parameters and the structure factors for R100124 and R110042 (in Supplementary Tables 5, 6 and 7, respectively) have been deposited with the Principal Editors of *Mineralogical Magazine* and are available at http://www.minersoc.org/pages/e_journals/dep_mat.html.

Description of the structure and discussion

The crystal structure of fettelite from the type locality is equivalent to that previously reported by Bindi *et al.* (2009) from the Chilean occurrence. Briefly, the structure can be described as the alternation of two kinds of layers along c (Fig. 3): layer *A* with a general composition $[\text{Ag}_6\text{As}_2\text{S}_7]^{2-}$ and layer *B* with a general composition $[\text{Ag}_{10}\text{HgAs}_2\text{S}_8]^{2+}$. In this structure, the Ag atoms occur in various coordination configurations, varying from quasi-linear to quasi-tetrahedral, the AsS_3 groups form pyramids as are typically observed in sulfosalts, and the Hg atom links two sulfur atoms in a linear coordination (Table 4). The bond distances observed are consistent with those found for Chilean fettelite (Bindi *et al.*, 2009) and for other Ag-bearing sulfosalts (e.g. proustite, pyrargyrite, pearceite, polybasite and stephanite). Fettelite has a module layer with a composition $[\text{Ag}_6\text{As}_2\text{S}_7]^{2-}$ (i.e. the *A* layer), which is identical to that in

CHEMICAL AND STRUCTURAL RE-EXAMINATION OF FETTELITE

TABLE 2. Details pertaining to the single-crystal X-ray data collections and structure refinements of the two fettelite crystals.

	Sample R100124	Sample R110042
Crystal data		
Formula	[Ag ₆ As ₂ S ₇][Ag ₁₀ (Fe _{0.53} Hg _{0.47})As ₂ S ₈]	[Ag ₆ As ₂ S ₇][Ag ₁₀ (Hg _{0.79} Cu _{0.21})As ₂ S ₈]
Crystal size (mm)	0.078 × 0.072 × 0.011	0.058 × 0.069 × 0.010
Form	platy	platy
Colour	dark red	dark red
Crystal system	monoclinic	monoclinic
Space group	C2	C2
a (Å)	26.011(2)	26.030(2)
b (Å)	15.048(1)	15.059(1)
c (Å)	15.513(1)	15.524(1)
β (°)	90.40(1)	90.45(1)
V (Å ³)	6071.9(7)	6085.0(7)
Z	8	8
Instrumental collection		
Instrument	Oxford Diffraction Excalibur 3	Oxford Diffraction Excalibur 3
Radiation type	MoKα ($\lambda = 0.71073$)	MoKα ($\lambda = 0.71073$)
Temperature (K)	298(3)	298(3)
Detector to sample distance (cm)	5	5
Number of frames	3127	3110
Measuring time (s)	185	200
Maximum 2θ (°)	69.68	69.58
Absorption correction	multi-scan (ABSPACK; Oxford Diffraction 2006)	multi-scan (ABSPACK; Oxford Diffraction 2006)
Collected reflections	70,024	69,857
Unique reflections	16,981	17,368
Reflections with $F_o > 4 \sigma(F_o)$	8136	7445
R_{int}	0.0423	0.0389
R_σ	0.0398	0.0362
Range h, k, l	$-40 \leq h \leq 41, -23 \leq k \leq 23, -24 \leq l \leq 24$	$-40 \leq h \leq 41, -23 \leq k \leq 23, -24 \leq l \leq 24$
Refinement		
Refinement	Full-matrix least squares on F^2	Full-matrix least squares on F^2
Twin matrices	$\begin{bmatrix} 1 & 0 & 0 \\ 0 & 1 & 0 \\ 0 & 0 & 1 \end{bmatrix}, \begin{bmatrix} -0.5 & -0.5 & 0 \\ 1.5 & -0.5 & 0 \\ 0 & 0 & 1 \end{bmatrix}, \begin{bmatrix} -0.5 & 0.5 & 0 \\ -1.5 & -0.5 & 0 \\ 0 & 0 & 1 \end{bmatrix}$	$\begin{bmatrix} 1 & 0 & 0 \\ 0 & 1 & 0 \\ 0 & 0 & 1 \end{bmatrix}, \begin{bmatrix} -0.5 & -0.5 & 0 \\ 1.5 & -0.5 & 0 \\ 0 & 0 & 1 \end{bmatrix}, \begin{bmatrix} -0.5 & 0.5 & 0 \\ -1.5 & -0.5 & 0 \\ 0 & 0 & 1 \end{bmatrix}$
Twin volume fractions	0.3965(9), 0.3875(7), 0.1002(8) 0.0425(4), 0.0305(3), 0.0428(4)	0.4125(7), 0.3798(7), 0.0987(8) 0.0385(4), 0.0284(3), 0.0421(4)
Final R [$I > 2 \sigma(I)$]	0.0314	0.0430
Final R (all data)	0.0341	0.0489
Number of least squares parameters	659	659
$\Delta\rho_{\text{max}}$ (e Å ⁻³)	1.13	3.96
$\Delta\rho_{\text{min}}$ (e Å ⁻³)	-1.40	-1.23

Note that $R = \Sigma |F_o| - |F_c| / \Sigma |F_o|$; $wR^2 = [\sum w (|F_o|^2 - |F_c|^2)^2 / \sum w (|F_o|^4)]^{1/2}$.

TABLE 3. Wyckoff positions, site occupancy factors, fractional atom coordinates, and equivalent isotropic displacement parameters (\AA^2) for the selected fettelite crystals.

Atom	Wyckoff	S. O. F.	x/a	y/b	z/c	U_{iso}
R100124						
Fe1	4c	0.546(2)	0.12290(1)	0.10428(2)	0.50143(2)	0.0175(1)
Hg1	4c	0.454	0.12290(1)	0.10428(2)	0.50143(2)	0.0175(1)
Fe2	4c	0.506(2)	0.13030(1)	0.61018(2)	0.50011(2)	0.0173(1)
Hg2	4c	0.494	0.13030(1)	0.61018(2)	0.50011(2)	0.0173(1)
Ag1	4c	1.00	0.28021(2)	0.83512(3)	0.91440(3)	0.0259(1)
Ag2	4c	1.00	0.07835(2)	0.46559(3)	0.08702(3)	0.0247(1)
Ag3	4c	1.00	0.04773(2)	0.61816(3)	-0.09586(2)	0.02018(9)
Ag4	4c	1.00	-0.02857(2)	0.38326(2)	0.08976(2)	0.01871(8)
Ag5	4c	1.00	-0.03304(2)	-0.11835(3)	0.08981(2)	0.01957(8)
Ag6	4c	1.00	0.07675(2)	-0.02592(3)	0.08682(3)	0.02065(9)
Ag7	4c	1.00	0.04689(2)	0.11624(3)	0.90526(2)	0.01833(8)
Ag8	4c	1.00	0.16703(2)	0.24525(2)	0.91108(2)	0.01903(8)
Ag9	4c	1.00	0.20499(2)	0.09411(3)	0.09844(3)	0.0254(1)
Ag10	4c	1.00	0.28137(2)	0.32277(3)	0.91184(3)	0.02240(9)
Ag11	4c	1.00	0.17836(2)	0.74447(2)	0.91295(2)	0.01897(8)
Ag12	4c	1.00	0.20062(2)	0.60923(3)	0.09394(2)	0.02076(8)
Ag13	4c	1.00	0.12902(2)	-0.12902(3)	0.71083(3)	0.02133(8)
Ag14	4c	1.00	0.11669(2)	0.62581(3)	0.30174(3)	0.02276(9)
Ag15	4c	1.00	0.01731(2)	0.72843(2)	0.30764(2)	0.01605(8)
Ag16	4c	1.00	0.01448(2)	0.22697(2)	0.29593(2)	0.01684(7)
Ag17	4c	1.00	0.13161(2)	0.37402(3)	0.70735(2)	0.02002(8)
Ag18	4c	1.00	0.23521(2)	0.48299(3)	0.69742(2)	0.01990(9)
Ag19	4c	1.00	0.11995(2)	0.12830(3)	0.30838(3)	0.02386(9)
Ag20	2b	1.00	0	0.75526(4)	$\frac{1}{2}$	0.0189(1)
Ag21	4c	1.00	0.13656(2)	0.07341(2)	0.69020(2)	0.01554(7)
Ag22	4c	1.00	0.18300(2)	0.29319(2)	0.50033(2)	0.01686(8)
Ag23	4c	1.00	0.13753(2)	0.57402(3)	0.69499(2)	0.01912(8)
Ag24	4c	1.00	0.11434(2)	0.32675(3)	0.29817(3)	0.02107(8)
Ag25	4c	1.00	0.17829(2)	0.80086(3)	0.49719(2)	0.02178(9)
Ag26	4c	1.00	0.23462(2)	-0.01597(2)	0.69520(2)	0.01659(8)
Ag27	4c	1.00	0.06952(2)	-0.08556(3)	0.50162(2)	0.01937(8)
Ag28	4c	1.00	0.11663(2)	0.83269(3)	0.29454(3)	0.02098(9)
Ag29	4c	1.00	0.24802(1)	0.13711(3)	0.50137(1)	0.01682(9)
Ag30	2b	1.00	0	0.28369(4)	$\frac{1}{2}$	0.0191(1)
Ag31	4c	1.00	0.24856(1)	0.45515(3)	0.50208(1)	0.01653(9)
Ag32	2b	1.00	0	0.09672(4)	$\frac{1}{2}$	0.0240(1)
Ag33	4c	1.00	0.07230(2)	0.41941(3)	0.50040(2)	0.02052(8)
Ag34	2b	1.00	0	0.56031(4)	$\frac{1}{2}$	0.01567(9)
As1	4c	1.00	0.08444(3)	0.22513(4)	0.07232(4)	0.0220(1)
As2	4c	1.00	0.08084(3)	0.72355(4)	0.07285(3)	0.0203(1)
As3	4c	1.00	0.16626(3)	0.48536(4)	0.92769(3)	0.0184(1)
As4	4c	1.00	0.16989(3)	-0.01196(4)	0.92668(4)	0.0216(1)
As5	4c	1.00	0.24901(2)	0.73297(3)	0.28512(3)	0.0170(1)
As6	4c	1.00	0.00013(2)	0.47190(4)	0.28488(3)	0.0180(1)
As7	4c	1.00	0.00114(2)	-0.02438(3)	0.71439(3)	0.0142(1)
As8	4c	1.00	0.25028(2)	0.23298(3)	0.28479(3)	0.0150(1)
S1	4c	1.00	0.00661(6)	0.74554(9)	0.15107(8)	0.0223(3)
S2	4c	1.00	0.11788(6)	0.11159(10)	0.15381(8)	0.0249(3)
S3	4c	1.00	0.24226(6)	0.46568(8)	0.85759(7)	0.0178(2)
S4	4c	1.00	0.13515(5)	0.60325(7)	0.85525(7)	0.0140(2)
S5	4c	1.00	0.01035(5)	0.24233(7)	0.13887(7)	0.0168(2)
S6	4c	1.00	0.12487(6)	-0.11805(8)	0.87426(8)	0.0203(3)

CHEMICAL AND STRUCTURAL RE-EXAMINATION OF FETTELITE

TABLE 3 (contd.)

Atom	Wyckoff	S. O. F.	<i>x/a</i>	<i>y/b</i>	<i>z/c</i>	<i>U</i> _{iso}
S7	4c	1.00	0.12064(6)	0.37808(8)	0.86105(8)	0.0198(3)
S8	4c	1.00	0.12282(5)	0.83964(7)	0.12975(7)	0.0143(2)
S9	4c	1.00	0.11306(6)	0.61056(9)	0.14685(7)	0.0191(2)
S10	4c	1.00	0.12580(6)	0.33539(10)	0.13245(8)	0.0220(3)
S11	4c	1.00	0.24145(6)	-0.02660(8)	0.85481(7)	0.0167(2)
S12	4c	1.00	0.25443(5)	0.69873(9)	-0.00351(5)	0.0190(3)
S13	4c	1.00	0.13136(5)	0.09774(7)	0.85122(6)	0.0129(2)
S14	2a	1.00	0	0.51168(9)	0	0.0130(3)
S15	2a	1.00	0	0.01297(11)	0	0.0200(3)
S16	4c	1.00	0.21319(6)	0.84667(8)	0.35884(7)	0.0160(2)
S17	4c	1.00	0.07400(5)	-0.02650(7)	0.35289(7)	0.0158(2)
S18	4c	1.00	0.08550(5)	0.73689(7)	0.46472(6)	0.0156(2)
S19	4c	1.00	0.08326(5)	0.22844(7)	0.44726(7)	0.0172(2)
S20	4c	1.00	0.16669(4)	-0.02623(6)	0.53039(6)	0.0131(2)
S21	4c	1.00	0.21299(6)	0.61444(7)	0.35125(7)	0.0147(2)
S22	4c	1.00	0.07369(5)	0.47227(7)	0.35161(6)	0.0116(2)
S23	4c	1.00	0.04260(6)	-0.13486(8)	0.65087(8)	0.0180(2)
S24	4c	1.00	-0.03842(6)	0.36196(8)	0.34823(7)	0.0147(2)
S25	4c	1.00	-0.03742(6)	0.58788(7)	0.35383(7)	0.0155(2)
S26	4c	1.00	0.17414(5)	0.23817(7)	0.64448(7)	0.0145(2)
S27	4c	1.00	0.21099(5)	0.34744(6)	0.35752(6)	0.0106(2)
S28	4c	1.00	0.28549(6)	0.61957(8)	0.65009(7)	0.0159(2)
S29	4c	1.00	-0.03374(5)	0.08965(6)	0.36107(6)	0.0110(2)
S30	4c	1.00	0.16878(6)	0.72989(8)	0.64438(7)	0.0178(2)
S31	4c	1.00	0.16113(4)	0.47849(5)	0.55879(5)	0.0104(2)
R110042						
Hg1	4c	0.811(4)	0.12317(5)	0.10741(6)	0.50142(7)	0.0259(3)
Cu1	4c	0.189	0.12317(5)	0.10741(6)	0.50142(7)	0.0259(3)
Hg2	4c	0.762(4)	0.13044(4)	0.61371(6)	0.50032(7)	0.0245(3)
Cu2	4c	0.238	0.13044(4)	0.61371(6)	0.50032(7)	0.0245(3)
Ag1	4c	1.00	0.27942(7)	0.83547(9)	0.9149(1)	0.0303(4)
Ag2	4c	1.00	0.07787(7)	0.46518(8)	0.0867(1)	0.0231(4)
Ag3	4c	1.00	0.04799(6)	0.61918(9)	-0.09576(9)	0.0207(3)
Ag4	4c	1.00	-0.02886(7)	0.38295(9)	0.0896(1)	0.0276(4)
Ag5	4c	1.00	-0.03282(7)	-0.11871(9)	0.0902(1)	0.0269(4)
Ag6	4c	1.00	0.07739(7)	-0.02527(8)	0.0867(1)	0.0240(4)
Ag7	4c	1.00	0.04706(7)	0.1177(1)	0.9050(1)	0.0304(4)
Ag8	4c	1.00	0.16718(7)	0.24399(8)	0.9108(1)	0.0240(4)
Ag9	4c	1.00	0.20512(7)	0.09588(9)	0.0978(1)	0.0301(4)
Ag10	4c	1.00	0.28159(6)	0.32376(8)	0.9115(1)	0.0234(4)
Ag11	4c	1.00	0.17838(7)	0.74481(9)	0.9122(1)	0.0287(4)
Ag12	4c	1.00	0.20066(7)	0.6100(1)	0.0936(1)	0.0330(4)
Ag13	4c	1.00	0.12931(6)	-0.12908(8)	0.7113(1)	0.0227(3)
Ag14	4c	1.00	0.11725(6)	0.62574(9)	0.3026(1)	0.0288(4)
Ag15	4c	1.00	0.01748(7)	0.72701(9)	0.3082(1)	0.0262(4)
Ag16	4c	1.00	0.01481(7)	0.2264(1)	0.2965(1)	0.0304(4)
Ag17	4c	1.00	0.13132(6)	0.37339(8)	0.70689(9)	0.0196(3)
Ag18	4c	1.00	0.23574(7)	0.48206(8)	0.6980(1)	0.0248(4)
Ag19	4c	1.00	0.12004(6)	0.12922(9)	0.3083(1)	0.0264(4)
Ag20	2b	1.00	0	0.7316(1)	½	0.0302(5)
Ag21	4c	1.00	0.13640(6)	0.07349(9)	0.6898(1)	0.0239(3)
Ag22	4c	1.00	0.18294(6)	0.29352(9)	0.5007(1)	0.0268(4)
Ag23	4c	1.00	0.13781(7)	0.57552(9)	0.6945(1)	0.0282(4)

TABLE 3 (contd.)

Atom	Wyckoff	S. O. F.	<i>x/a</i>	<i>y/b</i>	<i>z/c</i>	<i>U</i> _{iso}
Ag24	4c	1.00	0.11447(6)	0.32572(8)	0.29886(9)	0.0221(3)
Ag25	4c	1.00	0.17866(6)	0.80057(9)	0.4976(1)	0.0258(4)
Ag26	4c	1.00	0.23458(7)	-0.01717(8)	0.6953(1)	0.0269(4)
Ag27	4c	1.00	0.06951(6)	-0.08579(8)	0.50236(9)	0.0211(3)
Ag28	4c	1.00	0.11660(7)	0.83255(9)	0.2937(1)	0.0283(4)
Ag29	4c	1.00	0.24810(6)	0.13996(7)	0.50085(9)	0.0220(3)
Ag30	2b	1.00	0	0.2874(1)	$\frac{1}{2}$	0.0230(5)
Ag31	4c	1.00	0.24918(7)	0.44863(8)	0.5017(1)	0.0234(3)
Ag32	2b	1.00	0	0.0945(1)	$\frac{1}{2}$	0.0262(5)
Ag33	4c	1.00	0.07276(6)	0.41872(9)	0.50135(9)	0.0222(4)
Ag34	2b	1.00	0	0.5762(1)	$\frac{1}{2}$	0.0217(5)
As1	4c	1.00	0.08490(9)	0.2250(1)	0.07298(13)	0.0233(5)
As2	4c	1.00	0.0806(1)	0.7248(1)	0.0741(1)	0.0257(6)
As3	4c	1.00	0.16697(9)	0.4856(1)	0.9289(1)	0.0211(6)
As4	4c	1.00	0.16915(9)	-0.0125(1)	0.9266(1)	0.0194(5)
As5	4c	1.00	0.24888(9)	0.7325(1)	0.2850(1)	0.0207(5)
As6	4c	1.00	0.00058(9)	0.4716(1)	0.2860(1)	0.0208(5)
As7	4c	1.00	0.00114(9)	-0.0244(1)	0.7149(1)	0.0209(5)
As8	4c	1.00	0.25080(9)	0.2328(1)	0.2849(1)	0.0200(5)
S1	4c	1.00	0.0061(2)	0.7417(3)	0.1519(4)	0.033(1)
S2	4c	1.00	0.1173(3)	0.1103(3)	0.1532(4)	0.039(2)
S3	4c	1.00	0.2440(3)	0.4662(3)	0.8581(4)	0.039(2)
S4	4c	1.00	0.1353(2)	0.6030(3)	0.8549(4)	0.030(1)
S5	4c	1.00	0.0105(3)	0.2421(4)	0.1396(4)	0.042(2)
S6	4c	1.00	0.1261(2)	-0.1170(3)	0.8736(3)	0.031(1)
S7	4c	1.00	0.1212(2)	0.3769(3)	0.8620(4)	0.029(1)
S8	4c	1.00	0.1228(2)	0.8401(3)	0.1300(4)	0.035(2)
S9	4c	1.00	0.1128(2)	0.6095(3)	0.1467(4)	0.034(1)
S10	4c	1.00	0.1258(3)	0.3348(3)	0.1339(4)	0.037(2)
S11	4c	1.00	0.2417(3)	-0.0276(3)	0.8567(4)	0.042(2)
S12	4c	1.00	0.2542(2)	0.7008(3)	-0.0032(3)	0.034(1)
S13	4c	1.00	0.1325(3)	0.0953(3)	0.8512(4)	0.037(2)
S14	2a	1.00	0	0.5141(5)	0	0.040(2)
S15	2a	1.00	0	0.0140(4)	0	0.032(2)
S16	4c	1.00	0.2133(3)	0.8494(3)	0.3597(4)	0.038(2)
S17	4c	1.00	0.0755(3)	-0.0261(3)	0.3536(4)	0.037(2)
S18	4c	1.00	0.0857(2)	0.7403(3)	0.4531(4)	0.032(1)
S19	4c	1.00	0.0828(3)	0.2305(3)	0.4414(4)	0.038(2)
S20	4c	1.00	0.1668(3)	-0.0242(3)	0.5465(4)	0.034(2)
S21	4c	1.00	0.2126(2)	0.6145(3)	0.3510(4)	0.036(1)
S22	4c	1.00	0.0742(3)	0.4732(3)	0.3511(4)	0.037(2)
S23	4c	1.00	0.0431(3)	-0.1346(3)	0.6504(4)	0.034(1)
S24	4c	1.00	-0.0376(3)	0.3610(3)	0.3509(4)	0.034(2)
S25	4c	1.00	-0.0358(2)	0.5870(3)	0.3551(4)	0.031(1)
S26	4c	1.00	0.1733(2)	0.2390(3)	0.6447(4)	0.033(2)
S27	4c	1.00	0.2113(3)	0.3491(3)	0.3564(4)	0.033(2)
S28	4c	1.00	0.2857(2)	0.6165(4)	0.6493(4)	0.036(1)
S29	4c	1.00	-0.0336(2)	0.0893(3)	0.3612(4)	0.033(1)
S30	4c	1.00	0.1692(3)	0.7296(3)	0.6442(4)	0.038(2)
S31	4c	1.00	0.1605(3)	0.4818(3)	0.5593(4)	0.033(2)

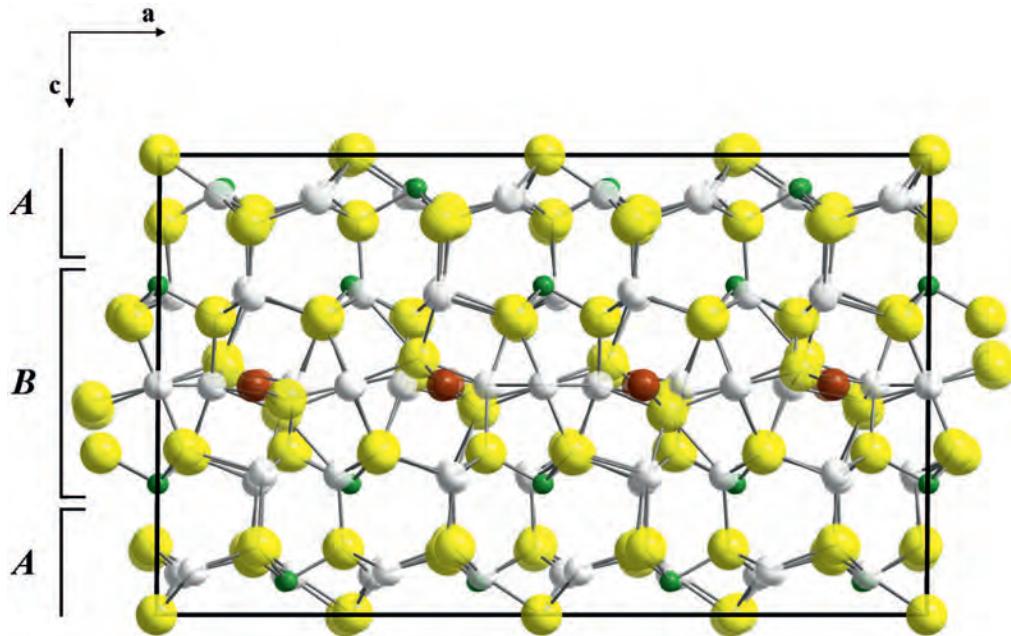


FIG. 3. A projection of the fettelite structure along the monoclinic b axis, emphasizing the succession of the $[\text{Ag}_6\text{As}_2\text{S}_7]^{2-}$ A and $[\text{Ag}_{10}\text{HgAs}_2\text{S}_8]^{2+}$ B module layers. White, green, brown and yellow circles indicate Ag, As, Hg and S atoms, respectively. The unit cell is outlined.

pearceite–polybasite (Bindi *et al.*, 2007a and references therein).

The crystal-structure refinement of fettelite R100124 showed that the Hg structural positions in the B module layer are largely occupied by iron (Table 3). Iron is the dominant cation on the basis of both X-ray structural formula (Tables 2, 3) and the electron microprobe data (Table 1). The $\text{Fe} \leftrightarrow \text{Hg}$ substitution is also indicated if the mean bond distances of the two Hg positions are considered (Table 4). The $\langle \text{Hg–S} \rangle$ distances are shorter in R100124 than those found for sites that are fully occupied by Hg (Bindi *et al.*, 2009). Nevertheless, given the discrepancies between the formulae obtained using the two techniques, i.e. $\text{Ag}_{16.45}(\text{Fe}_{0.89}\text{Hg}_{0.37}\text{Cu}_{0.01})_{\Sigma=1.27}(\text{As}_{4.03}\text{Sb}_{0.04})_{\Sigma=4.07}\text{S}_{14.21}$ (WDS) and $\text{Ag}_{16}(\text{Fe}_{0.53}\text{Hg}_{0.47})_{\Sigma=1.00}\text{As}_4\text{S}_{15}$ (single-crystal XRD), we prefer not to propose R100124 as a new mineral to the IMA-CNMNC at this time. Unfortunately, the lack of published data for a structure having a linearly coordinated structural site fully occupied by Fe also precludes the possibility of making crystal-chemical considerations for the Hg–Fe join of fettelite (the dotted line in Fig. 4).

Some observations can be made on type fettelite (R110042). The structure refinement for this crystal shows that the Hg positions contain a significant amount of Cu (Table 3). The resulting mean bond distances for these positions, linearly coordinated by sulfur atoms, are 2.355 and 2.335 Å, respectively (Table 4). Taking into account all the Hg–S distances in the structure of Chilean fettelite (Bindi *et al.*, 2009) and those observed for members of the pearceite–polybasite group (Bindi *et al.*, 2006, 2007b, 2007c; Evain *et al.*, 2006), which have Cu in a similar crystal-chemical environment (linearly coordinated by two sulfur atoms), the following equation is obtained:

$$\langle \text{Hg–S} \rangle (\text{\AA}) = 2.159(2) + 0.238(4)\text{Hg (a.p.f.u.)}$$

This is shown as a dashed line in Fig. 4, and it indicates that if a mean bond distance that is of less than 2.276 Å is measured (calculated with $\text{Hg} = 0.49$ a.p.f.u.) for the Hg positions, and $\text{Cu} \leftrightarrow \text{Hg}$ is the only cation substitution occurring at the Hg sites, the mineral could be a Cu-dominant analogue of fettelite. It is obvious that a $\text{Cu} \leftrightarrow \text{Hg}$ substitution at the Hg sites would not be the

TABLE 4. The principal interatomic distances (\AA) and their standard deviations (in parentheses) for the selected fettelite crystals.

R100124					
$[\text{Ag}_6\text{As}_2\text{S}_7]^{2-} \text{ A layer}$					
As1–S10	2.183(2)	As2–S9	2.213(2)		
–S5	2.208(1)	–S8	2.238(2)		
–S2	2.293(2)	–S1	2.311(1)		
<As1–S>	2.228	<As2–S>	2.254		
As3–S4	2.248(1)	As4–S6	2.137(2)		
–S7	2.251(2)	–S11	2.188(1)		
–S3	2.282(1)	–S13	2.255(1)		
<As1–S>	2.260	<As1–S>	2.193		
Ag1–S11	2.488(1)	Ag2–S10	2.418(2)	Ag3–S4	2.413(1)
–S12	2.509(1)	–S14	2.5334(7)	–S14	2.5191(9)
–S10	2.555(2)	–S9	2.535(2)	–S1	2.528(1)
<Ag1–S>	2.517	<Ag2–S>	2.495	<Ag3–S>	2.487
Ag4–S5	2.468(1)	Ag5–S6	2.457(2)	Ag6–S8	2.442(1)
–S14	2.498(1)	–S1	2.480(2)	–S15	2.4707(7)
–S7	2.520(1)	–S15	2.569(1)	–S2	2.548(2)
<Ag4–S>	2.495	<Ag5–S>	2.502	<Ag6–S>	2.487
Ag7–S13	2.374(1)	Ag8–S7	2.458(1)	Ag9–S12	2.405(1)
–S15	2.467(1)	–S13	2.577(1)	–S2	2.443(2)
–S5	2.504(1)	–S12	2.584(1)	–S3	2.464(1)
<Ag7–S>	2.448	<Ag8–S>	2.540	<Ag9–S>	2.437
Ag10–S3	2.521(1)	Ag11–S12	2.456(1)	Ag12–S9	2.426(1)
–S12	2.528(1)	–S6	2.562(1)	–S12	2.467(1)
–S8	2.591(1)	–S4	2.563(1)	–S11	2.658(1)
<Ag10–S>	2.547	<Ag11–S>	2.527	<Ag12–S>	2.517
$[\text{Ag}_{10}(\text{Fe},\text{Hg})\text{As}_2\text{S}_8]^{2+} \text{ B layer}$					
As5–S16	2.262(1)	As6–S22	2.169(1)		
–S21	2.264(1)	–S24	2.173(1)		
–S26	2.273(2)	–S25	2.271(1)		
<As5–S>	2.266	<As6–S>	2.204		
As7–S17	2.210(2)	As8–S28	2.194(1)		
–S23	2.216(1)	–S27	2.302(1)		
–S29	2.247(1)	–S30	2.369(2)		
<As7–S>	2.224	<As8–S>	2.288		
Fe1/Hg1–S19	2.291(1)	Fe2/Hg2–S18	2.299(1)		
–S20	2.313(1)	–S31	2.3213(9)		
<Fe1/Hg1–S>	2.302	<Fe2/Hg2–S>	2.310		
Ag20–S18	2.311(1)	Ag29–S28	2.514(1)	Ag32–S29	2.324(1)
–S18	2.311(1)	–S21	2.518(1)	–S29	2.324(1)
<Ag20–S>	2.311	<Ag29–S>	2.516	<Ag32–S>	2.324
Ag34–S25	2.496(1)	Ag33–S22	2.442(1)	Ag13–S23	2.428(2)
–S25	2.496(1)	–S31	2.631(1)	–S6	2.544(1)
<Ag34–S>	2.496	<Ag33–S>	2.567	<Ag13–S>	2.517
Ag14–S9	2.415(1)	Ag15–S1	2.456(1)	Ag21–S13	2.529(1)
–S21	2.620(2)	–S25	2.651(1)	–S26	2.760(1)
–S22	2.683(1)	–S23	2.663(1)	–S29	2.796(2)
<Ag14–S>	2.573	<Ag15–S>	2.590	<Ag21–S>	2.695

CHEMICAL AND STRUCTURAL RE-EXAMINATION OF FETTELITE

Ag22—S26	2.397(1)	Ag26—S11	2.486(1)	Ag28—S17	2.560(1)
—S27	2.4753(9)	—S21	2.498(1)	—S8	2.565(1)
—S19	2.886(2)	—S27	2.629(1)	—S16	2.704(2)
<Ag22—S>	2.586	<Ag26—S>	2.538	<Ag28—S>	2.610
Ag16—S5	2.449(1)	Ag17—S7	2.404(1)	Ag18—S3	2.504(1)
—S24	2.587(1)	—S26	2.524(1)	—S28	2.547(1)
—S29	2.623(1)	—S24	2.573(2)	—S16	2.605(1)
—S19	2.942(2)	—S31	2.8978(9)	—S31	2.878(1)
<Ag16—S>	2.650	<Ag17—S>	2.600	<Ag18—S>	2.634
Ag19—S2	2.411(1)	Ag23—S4	2.526(1)	Ag24—S22	2.571(1)
—S28	2.542(2)	—S30	2.605(1)	—S10	2.593(1)
—S17	2.710(1)	—S31	2.6317(8)	—S27	2.689(2)
—S19	2.802(1)	—S25	2.715(2)	—S19	2.867(1)
<Ag19—S>	2.616	<Ag23—S>	2.619	<Ag24—S>	2.680
Ag25—S16	2.436(1)	Ag27—S17	2.476(1)	Ag30—S19	2.465(1)
—S30	2.534(1)	—S23	2.535(1)	—S19	2.465(1)
—S18	2.644(1)	—S20	2.714(1)	—S24	2.810(1)
—S20	2.670(1)	—S18	2.764(1)	—S24	2.810(1)
<Ag25—S>	2.571	<Ag27—S>	2.622	<Ag30—S>	2.638
Ag31—S20	2.282(1)				
—S31	2.469(1)				
—S16	2.878(1)				
—S27	2.929(1)				
<Ag31—S>	2.640				

R110042
 $[\text{Ag}_6\text{As}_2\text{S}_7]^{2-}$ A layer

As1—S10	2.179(6)	As2—S9	2.231(6)		
—S5	2.218(6)	—S8	2.228(6)		
—S2	2.286(6)	—S1	2.305(6)		
<As1—S>	2.228	<As2—S>	2.255		
As3—S4	2.260(6)	As4—S6	2.095(6)		
—S7	2.271(6)	—S11	2.196(6)		
—S3	2.312(6)	—S13	2.213(6)		
<As1—S>	2.281	<As1—S>	2.168		
Ag1—S11	2.453(7)	Ag2—S10	2.436(6)	Ag3—S4	2.417(5)
—S12	2.485(5)	—S14	2.533(3)	—S14	2.511(5)
—S10	2.586(6)	—S9	2.531(6)	—S1	2.475(6)
<Ag1—S>	2.508	<Ag2—S>	2.500	<Ag3—S>	2.468
Ag4—S5	2.477(6)	Ag5—S6	2.498(6)	Ag6—S8	2.439(6)
—S14	2.533(6)	—S1	2.520(5)	—S15	2.486(3)
—S7	2.525(6)	—S15	2.589(5)	—S2	2.508(6)
<Ag4—S>	2.512	<Ag5—S>	2.536	<Ag6—S>	2.478
Ag7—S13	2.407(6)	Ag8—S7	2.449(5)	Ag9—S12	2.407(5)
—S15	2.478(5)	—S13	2.583(6)	—S2	2.459(6)
—S5	2.493(7)	—S12	2.574(6)	—S3	2.453(6)
<Ag7—S>	2.459	<Ag8—S>	2.535	<Ag9—S>	2.440
Ag10—S3	2.497(6)	Ag11—S12	2.453(6)	Ag12—S9	2.438(6)
—S12	2.520(5)	—S6	2.555(5)	—S12	2.471(5)
—S8	2.586(6)	—S4	2.567(6)	—S11	2.669(7)
<Ag10—S>	2.534	<Ag11—S>	2.525	<Ag12—S>	2.526

TABLE 4 (*contd.*)

[Ag₁₀(Hg,Cu)As₂S₈]²⁺ B layer					
As5—S16	2.306(5)	As6—S22	2.159(8)		
—S21	2.261(5)	—S24	2.188(5)		
—S26	2.295(7)	—S25	2.256(5)		
<As5—S>	2.287	<As6—S>	2.201		
As7—S17	2.253(8)	As8—S28	2.242(6)		
—S23	2.229(5)	—S27	2.319(5)		
—S29	2.249(5)	—S30	2.348(8)		
<As7—S>	2.244	<As8—S>	2.303		
Hg1/Cu1—S19	2.323(6)	Hg2/Cu2—S18	2.348(6)		
—S20	2.386(6)	—S31	2.321(5)		
<Hg1/Cu1—S>	2.355	<Hg2/Cu2—S>	2.335		
Ag20—S18	2.355(6)	Ag29—S28	2.510(6)	Ag32—S29	2.321(7)
—S18	2.355(6)	—S21	2.539(6)	—S29	2.321(7)
<Ag20—S>	2.355	<Ag29—S>	2.525	<Ag32—S>	2.321
Ag34—S25	2.433(6)	Ag33—S22	2.473(6)	Ag13—S23	2.429(7)
—S25	2.433(6)	—S31	2.626(7)	—S6	2.528(5)
<Ag34—S>	2.433	—S24	2.625(5)	—S30	2.591(5)
		<Ag33—S>	2.575	<Ag13—S>	2.516
Ag14—S9	2.434(6)	Ag15—S1	2.452(6)	Ag21—S13	2.529(6)
—S21	2.593(7)	—S25	2.630(5)	—S26	2.763(5)
—S22	2.667(5)	—S23	2.694(5)	—S29	2.795(7)
<Ag14—S>	2.565	—S18	2.862(7)	—S20	2.787(5)
		<Ag15—S>	2.660	<Ag21—S>	2.719
Ag22—S26	2.397(6)	Ag26—S11	2.516(7)	Ag28—S17	2.561(5)
—S27	2.508(5)	—S21	2.521(5)	—S8	2.550(6)
—S19	2.916(7)	—S27	2.588(5)	—S16	2.723(8)
<Ag22—S>	2.607	—S20	2.898(8)	—S18	2.956(5)
		<Ag26—S>	2.631	<Ag28—S>	2.698
Ag16—S5	2.448(7)	Ag17—S7	2.425(6)	Ag18—S3	2.505(7)
—S24	2.588(5)	—S26	2.498(5)	—S28	2.525(5)
—S29	2.622(5)	—S24	2.600(7)	—S16	2.563(5)
—S19	2.852(7)	—S31	2.919(5)	—S31	2.899(8)
<Ag16—S>	2.628	<Ag17—S>	2.611	<Ag18—S>	2.623
Ag19—S2	2.426(6)	Ag23—S4	2.526(6)	Ag24—S22	2.589(5)
—S28	2.543(7)	—S30	2.582(5)	—S10	2.584(6)
—S17	2.706(5)	—S31	2.601(5)	—S27	2.692(7)
—S19	2.750 (5)	—S25	2.764(7)	—S19	2.767(5)
<Ag19—S>	2.606	<Ag23—S>	2.618	<Ag24—S>	2.658
Ag25—S16	2.442(5)	Ag27—S17	2.484(6)	Ag30—S19	2.497(6)
—S30	2.528(6)	—S23	2.514(5)	—S19	2.497(6)
—S18	2.671(7)	—S20	2.778(7)	—S24	2.740(6)
—S20	2.764(5)	—S18	2.762(5)	—S24	2.740(6)
<Ag25—S>	2.601	<Ag27—S>	2.635	<Ag30—S>	2.619
Ag31—S20	2.353(6)				
—S31	2.532(6)				
—S16	2.790(7)				
—S27	2.875(6)				
<Ag31—S>	2.638				

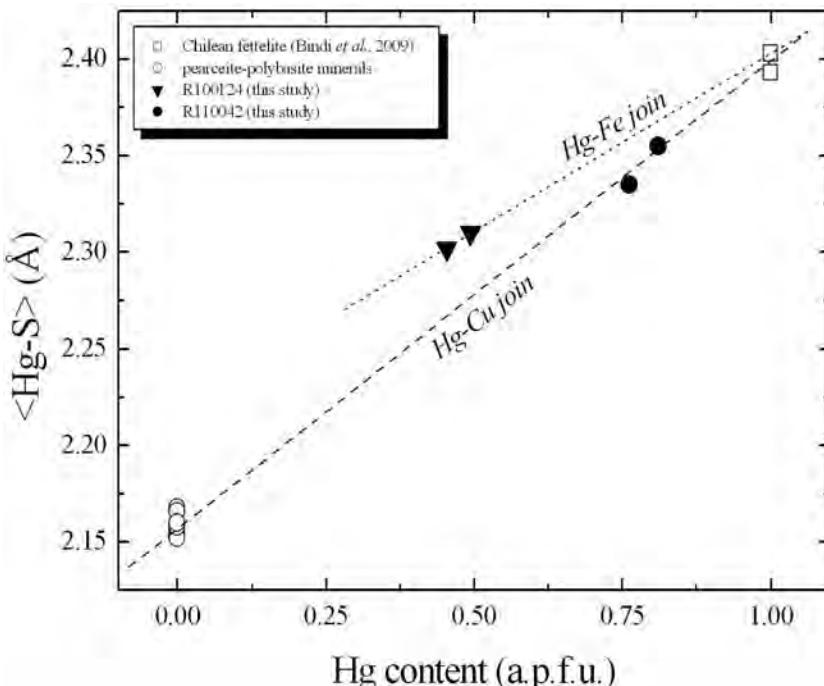


FIG. 4. The relationship between the Hg content (a.p.f.u.) and the $\langle \text{Hg}-\text{S} \rangle$ distance (\AA) for fettelite samples and for different members of the pearceite–polybasite group (see text). The dashed and dotted lines indicate the possible Hg–Cu and Hg–Fe joins for fettelite.

only requirement of a new fettelite-like mineral. As Cu is usually monovalent in these minerals [as confirmed by the excellent regression line shown in Fig. 4 ($R = 0.996$) which uses the Cu–S distances in pearceite–polybasite, where Cu is in a monovalent state], the $\text{Cu}^+ \leftrightarrow \text{Hg}^{2+}$ substitution would produce an excess negative charge. To maintain charge balance in a Cu-dominant mineral, another coupled substitution must occur, such as the replacement of Ag by a divalent cation (e.g. Zn, Pb). This type of replacement could occur either by random substitutions for Ag in the 34 available structural positions (i.e. in a disordered fashion) or in a more ordered manner at certain selected positions. For R110042, despite the high-quality structural data, we were not able to locate (in the refinements of the occupancy factors of the 34 Ag positions) a divalent lighter and/or heavier cation substituting for Ag. This might indicate that the divalent cation balancing the entry of copper substituting for mercury was distributed randomly among the available Ag positions.

Metal–metal bonding

Metal–metal bonding is a mechanism that may have an effect on the chemical variability at the Hg sites without the need to invoke charge-balance considerations. For instance, in pyrite, charge balance constraints are removed by S–S bond interactions, and a similar role is played by Ni–Ni bonds in heazlewoodite (Gibbs *et al.*, 2005, 2008). As a number of the Ag–Ag distances in fettelite are similar to those observed in face-centred cubic silver [$r_{(\text{Ag}-\text{Ag})} = 2.89 \text{ \AA}$; Suh *et al.*, 1988] or hexagonal close-packed silver [$r_{(\text{Ag}-\text{Ag})} = 2.93 \text{ \AA}$; Petruk *et al.*, 1970], an investigation of the possibility of metal–metal bonding in fettelite following the Bader model (Bader, 1990) seemed worthwhile. In this model, a pair of atoms is considered to exhibit a bond interaction if the electron density distribution indicates that a minimum energy bond path joins them, and if the pair of atoms shares a zero-flux interatomic surface. Therefore, using SPEEDEEN software (Downs *et al.*, 2002), the procrystal electron density distribution for sample R100124 was calculated and bond paths were determined.

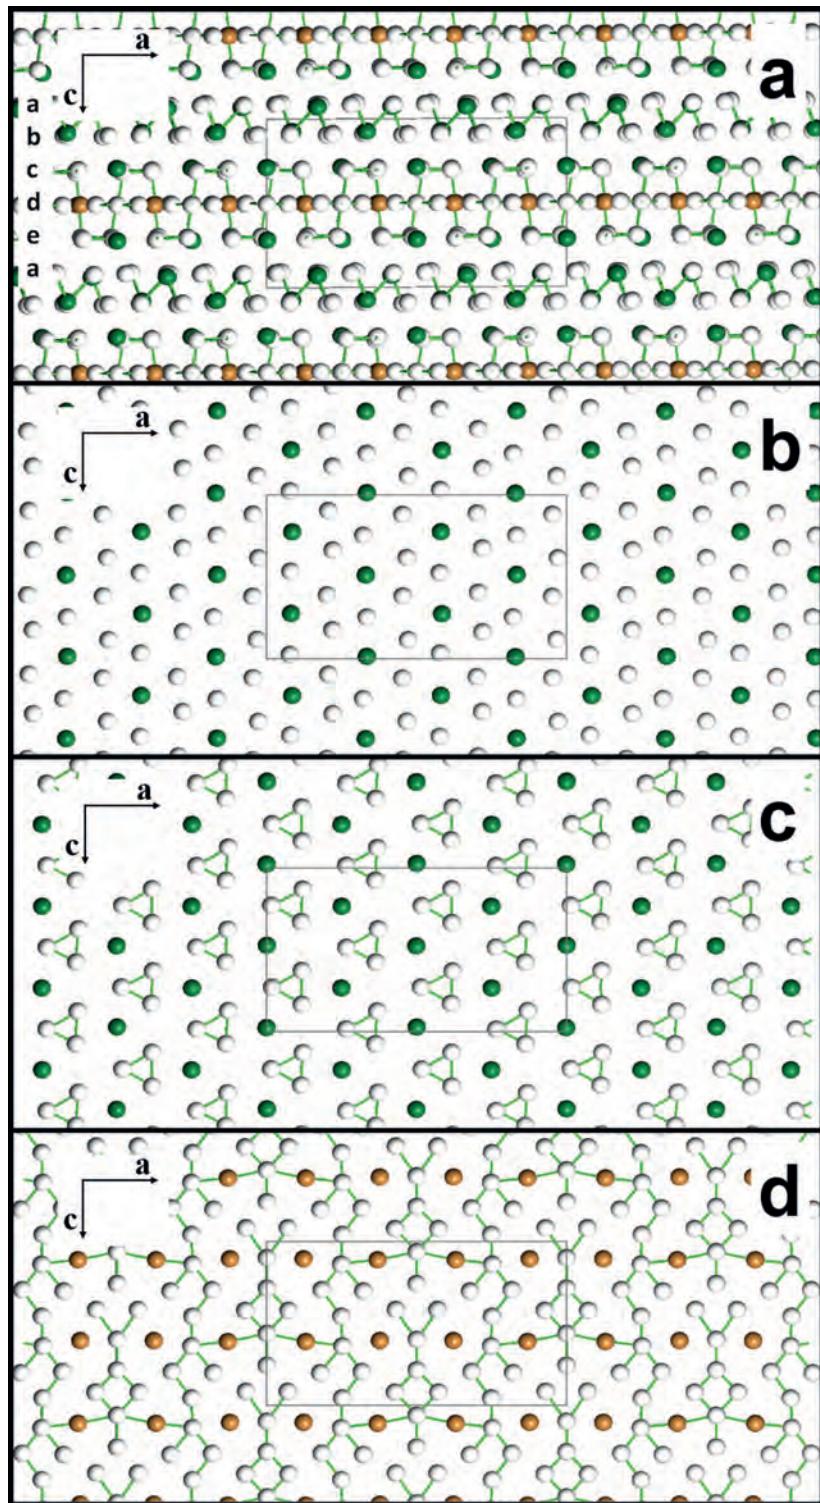


Figure 5*a* shows the fettelite metal atoms, without S, looking along the *b* axis, in a similar orientation to that shown in Fig. 3. Five distinct layers are observed, with *a*–*b* corresponding to module layer *A* in Fig. 3, and *c*–*d*–*e* corresponding to module layer *B*. The green lines joining pairs of metal atoms indicate bonds. Layer *d* has a composition $(\text{Fe},\text{Hg})\text{Ag}_4$, whereas the other layers are all AsAg_3 , with layers *a* = *b* and *c* = *e*. There are As–Ag bonds between layers *a* and *b*, with $\langle r_{(\text{As}-\text{Ag})} \rangle = 3.30 \text{ \AA}$, and a range from 3.17 to 3.49 Å, but no bond interactions within the layer, as shown in Fig. 5*b*. The layers *a* and *b* represent well-ordered close-packed monolayers with relatively little distortion. In contrast, layers *c* and *e* have the same composition as layers *a* and *b*, but are much more distorted due to the presence of bonded clusters containing three Ag atoms, as indicated in Fig. 5*c*. The mean $\langle r_{(\text{Ag}-\text{Ag})} \rangle$ is 3.04 Å, with a range from 2.88 to 3.24 Å. Layer *d* is composed only of Ag and (Fe,Hg) atoms. The Ag–Ag average $\langle r_{(\text{Ag}-\text{Ag})} \rangle = 2.92 \text{ \AA}$, with a range from 2.74 to 3.29 Å. The short Ag–Ag distances indicate that this layer has the strongest Ag–Ag bond interactions. The (Fe,Hg) is only bonded to Ag atoms within this layer, with $r_{(\text{Ag}-(\text{Fe},\text{Hg}))}$ values ranging from 3.19 to 3.47 Å, as shown in Fig. 5*d*. The metal atoms in layers *c*–*d*–*e* have (Fe,Hg) –Ag bond distances of 2.98 and 3.10 Å, and three Ag–Ag bonds ranging from 3.05 to 3.12 Å in length.

Metal–metal interactions can affect both charge balance and the conductivity of the crystal (Gibbs *et al.*, 2005). In this context, there is a continuous two-dimensional network of bond interactions in module layer *B*, as demonstrated in Fig. 5, which is not present in module layer *A*, or along the *c* axis. As such, fettelite crystals might be expected to have significantly anisotropic

electrical conductivities, with a greater conductivity in the *a*–*b* plane. As the continuous bond network in layer *d* is broken up by larger gaps around the (Fe,Hg) site, chemical variability in this site could produce a variable conductivity in the *a*–*b* plane. This feature is in perfect agreement with that observed by Bindi and Menchetti (2011) for HT-fettelite. In this HT-structure, the disorder responsible for the ionic conductivity is located in the *B* layer where the Ag–Hg cations are found in various sites corresponding to the most pronounced probability density function locations of diffusion-like paths.

Concluding remarks

On the basis of structural information gained from the characterization of fettelite from the type locality (including the holotype specimen), we can confirm that the crystal-chemical formula originally reported by Wang and Paniagua (1996) should be revised to $[\text{Ag}_6\text{As}_2\text{S}_7][\text{Ag}_{10}\text{HgAs}_2\text{S}_8]$ ($Z = 8$). The refined compositions of the crystals in this study, $[\text{Ag}_6\text{As}_2\text{S}_7][\text{Ag}_{10}(\text{Fe}_{0.53}\text{Hg}_{0.47})\text{As}_2\text{S}_8]$ (R100124) and $[\text{Ag}_6\text{As}_2\text{S}_7][\text{Ag}_{10}(\text{Hg}_{0.79}\text{Cu}_{0.21})\text{As}_2\text{S}_8]$ (R110042), clearly indicate that new minerals related to fettelite exist. Indeed, it seems likely that a new fettelite-like mineral, which has Fe dominant over Hg in two structural positions, occurs at the type locality. A new fettelite-like mineral with Cu substituting for Hg and, for charge balance requirements, a divalent cation randomly substituting for Ag (in a disordered fashion) may also occur. It is not surprising to see such differences in chemistry for crystals coming from the same occurrence (Odenwald, Germany). Minerals belonging to the pearceite–polybasite group, for example, which are strongly related to fettelite, exhibit similar chemical variability.

FIG. 5 (facing page). The structure of R100124 fettelite with metal atoms displayed as spheres, and S atoms not shown. White, green and brown spheres correspond to Ag, As, and (Fe,Hg) , respectively. The green lines indicate metal–metal bond interactions as determined by a procrystal electron density analysis. The figure is in the same orientation as Fig. 3, viewed along the *b* axis. (a) The module layer *A* is composed of 2 metal layers, *a*–*b*, and module layer *B* is composed of metal layers *c*–*d*–*e*. (b) A representation of the metal atoms in layers *a* (or equivalently *b*). Although the Ag and As atoms form a relatively undistorted close-packed monolayer, there is no metal–metal bonding in the layer, only between layers *a*–*b*. (c) A representation of the metal atoms in layers *c* (or equivalently *e*), showing a more distorted monolayer than layer *a* or *b*, with bonded clusters containing three Ag atoms. (d) A representation of the metal atoms in layer *d* showing a continuous network of Ag–Ag and Ag– (Fe,Hg) bonds, suggesting a strongly metallic character that probably produces a significantly greater electrical conductivity in the plane of the layer than that in the *c* direction. The distortion around the (Fe,Hg) sites suggests that chemical substitutions could produce tuneable electrical properties.

Acknowledgements

This work was funded by the CNR (Istituto di Geoscienze e Georisorse, sezione di Firenze) and by the M.I.U.R., P.R.I.N. 2009 project “Modularity, microstructures and non-stoichiometry in minerals” issued to Paola Bonazzi, and by Newmont Mining Co for RTD to study copper and silver sulfide minerals. The holotype material from the University of Heidelberg was kindly provided by Rainer Altherr. The manuscript was improved by comments of Frantisek Laufek and one anonymous reviewer.

References

- Bader, R.F.W. (1990) *Atoms in Molecules*. Oxford Science Publications, Oxford, UK.
- Bindi, L. and Menchetti, S. (2011) Fast ion conduction character and ionic phase-transition in silver sulfosalts: the case of fettelite $[Ag_6As_2S_7][Ag_{10}HgAs_2S_8]$. *American Mineralogist*, **96**, 792–796.
- Bindi, L., Evain, M. and Menchetti, S. (2006) Temperature dependence of the silver distribution in the crystal structure of natural pearceite, $(Ag,Cu)_{16}(As,Sb)_2S_{11}$. *Acta Crystallographica, B62*, 212–219.
- Bindi, L., Evain, M., Spry, P.G. and Menchetti, S. (2007a) The pearceite–polybasite group of minerals: crystal chemistry and new nomenclature rules. *American Mineralogist*, **92**, 918–925.
- Bindi, L., Evain, M. and Menchetti, S. (2007b) Complex twinning, polytypism and disorder phenomena in the crystal structures of antimонpearceite and arsenopolybasite. *The Canadian Mineralogist*, **45**, 321–333.
- Bindi, L., Evain, M., Spry, P.G., Tait, K.T. and Menchetti, S. (2007c) Structural role of copper in the minerals of the pearceite–polybasite group: the case of the new minerals cupropearceite and cupropolybasite. *Mineralogical Magazine*, **71**, 641–650.
- Bindi, L., Keutsch, F.N., Francis, C.A. and Menchetti, S. (2009) Fettelite, $[Ag_6As_2S_7][Ag_{10}HgAs_2S_8]$ from Chañarcillo, Chile: crystal structure, pseudosymmetry, twinning, and revised chemical formula. *American Mineralogist*, **94**, 609–615.
- Downs, R.T., Gibbs, G.V., Boisen, M.B. Jr and Rosso, K.M. (2002) A comparison of procrystal and *ab initio* representations of the electron-density distributions of minerals. *Physics and Chemistry of Minerals*, **29**, 369–385.
- Evain, M., Bindi, L. and Menchetti, S. (2006) Structural complexity in minerals: twinning, polytypism and disorder in the crystal structure of polybasite, $(Ag,Cu)_{16}(Sb,As)_2S_{11}$. *Acta Crystallographica, B62*, 447–456.
- Gibbs, G.V., Downs, R.T., Prewitt, C.T., Rosso, K.M., Ross, N.L. and Cox, D.F. (2005) Electron density distributions calculated for the nickel sulfides millerite, vaesite and heazlewoodite and nickel metal: a case for the importance of Ni–Ni bond paths for electron transport. *Journal of Physical Chemistry B*, **109**, 21788–21795.
- Gibbs, G.V., Downs, R.T., Cox, D.F., Ross, N.L., Prewitt, C.T., Rosso, K.M., Lippmann, T. and Kirfel, A. (2008) Bonded interactions and the crystal chemistry of minerals: a review. *Zeitschrift für Kristallographie*, **223**, 1–40.
- Nespoli, M. (2004) Twin point groups and the polychromatic symmetry of twins. *Zeitschrift für Kristallographie*, **219**, 57–71.
- Oxford Diffraction (2006) *CrysAlis RED* (Version 1.171.31.2) and *ABSPACK* in *CrysAlis RED*. Oxford Diffraction Ltd, Abingdon, Oxfordshire, England.
- Petříček, V., Dušek, M. and Palatinus, L. (2006) *JANA2000, a crystallographic computing system*. Institute of Physics, Academy of Sciences of the Czech Republic, Prague, Czech Republic.
- Petruk, W., Cabri, L.J., Harris, D.C., Stewart, J.M. and Clark, L.A. (1970) Allargentum, redefined. *The Canadian Mineralogist*, **10**, 163–172.
- Suh, I.-K., Ohta, H. and Waseda, Y. (1988) High-temperature thermal expansion of six metallic elements measured by dilatation method and X-ray diffraction. *Journal of Materials Science*, **23**, 757–760.
- Wang, N. and Paniagua, A. (1996) Fettelite, a new Hg-sulfosalt mineral from Odenwald. *Neues Jahrbuch für Mineralogie Monatshefte*, **1996**, 313–320.

```

data_R100124

_audit_creation_method           JANA2006
_chemical_name_systematic
;
?
;
_chemical_name_common            ?
_chemical_melting_point          ?
_chemical_formula_moiety         ?
_chemical_formula_sum
'Ag16 As4 Fe0 Hg S15'
_chemical_formula_weight          2707.09

loop_
_atom_type_symbol
_atom_type_description
_atom_type_scat_dispersion_real
_atom_type_scat_dispersion_imag
_atom_type_scat_source
'Ag'   'Ag'   -0.8971   1.1015
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'S'    'S'    0.1246   0.1234
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'As'   'As'   0.0499   2.0058
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Hg'   'Hg'   -2.3894   9.2266
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Fe'   'Fe'   0.3463   0.8444
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

_symmetry_cell_setting          ?
_symmetry_space_group_name_H-M   ?

loop_
_symmetry_equiv_pos_as_xyz
'x, y, z'
'-x, y, -z'
'x+1/2, y+1/2, z'
'-x+1/2, y+1/2, -z'

_cell_length_a                  26.011(2)
_cell_length_b                  15.0480(10)
_cell_length_c                  15.5130(10)
_cell_angle_alpha                90.00
_cell_angle_beta                 90.400(10)
_cell_angle_gamma                90.00
_cell_volume                     6071.9(7)
_cell_formula_units_Z            8
_cell_measurement_temperature    293(2)
_cell_measurement_reflns_used    ?
_cell_measurement_theta_min      ?
_cell_measurement_theta_max      ?

_exptl_crystal_description      ?
_exptl_crystal_colour           ?
_exptl_crystal_size_max          ?
_exptl_crystal_size_mid          ?
_exptl_crystal_size_min          ?

```

```

_exptl_crystal_density_meas      ?
_exptl_crystal_density_diffrn   5.923
_exptl_crystal_density_method    'not measured'
_exptl_crystal_F_000             9632
_exptl_absorpt_coefficient_mu   20.451
_exptl_absorpt_correction_type   ?
_exptl_absorpt_correction_T_min  ?
_exptl_absorpt_correction_T_max  ?
_exptl_absorpt_process_details   ?

_exptl_special_details
;
?
;

_diffrn_ambient_temperature      293(2)
_diffrn_radiation_wavelength     0.71069
_diffrn_radiation_type           MoK\alpha
_diffrn_radiation_source         'fine-focus sealed tube'
_diffrn_radiation_monochromator   graphite
_diffrn_measurement_device_type   ?
_diffrn_measurement_method        ?
_diffrn_detector_area_resol_mean  ?
_diffrn_standards_number          ?
_diffrn_standards_interval_count  ?
_diffrn_standards_interval_time   ?
_diffrn_standards_decay_%         ?
_diffrn_reflns_number             16981
_diffrn_reflns_av_R_equivalents   0.0000
_diffrn_reflns_av_sigmaI/netI     0.6978
_diffrn_reflns_limit_h_min        -40
_diffrn_reflns_limit_h_max        41
_diffrn_reflns_limit_k_min        -23
_diffrn_reflns_limit_k_max        23
_diffrn_reflns_limit_l_min        0
_diffrn_reflns_limit_l_max        24
_diffrn_reflns_theta_min          3.77
_diffrn_reflns_theta_max          34.84
_reflns_number_total              16981
_reflns_number_gt                 8136
_reflns_threshold_expression      >2sigma(I)

_computing_data_collection        ?
_computing_cell_refinement        ?
_computing_data_reduction         ?
_computing_structure_solution     ?
_computing_structure_refinement   'SHELXL-97 (Sheldrick, 1997)'
_computing_molecular_graphics     ?
_computing_publication_material   ?

_refine_special_details
;
Refinement of F^2^ against ALL reflections. The weighted R-factor wR and
goodness of fit S are based on F^2^, conventional R-factors R are based
on F, with F set to zero for negative F^2^. The threshold expression of
F^2^ > 2sigma(F^2^) is used only for calculating R-factors(gt) etc. and is
not relevant to the choice of reflections for refinement. R-factors based
on F^2^ are statistically about twice as large as those based on F, and R-
factors based on ALL data will be even larger.
;
```

```

_refine_ls_structure_factor_coef  Fsqd
_refine_ls_matrix_type          full
_refine_ls_weighting_scheme     calc
_refine_ls_weighting_details
  'calc w=1/[s^2^(Fo^2^)+(0.0654P)^2^+0.0000P] where P=(Fo^2^+2Fc^2^)/3'
_atom_sites_solution_primary    direct
_atom_sites_solution_secondary  difmap
_atom_sites_solution_hydrogens  geom
_refine_ls_hydrogen_treatment   mixed
_refine_ls_extinction_method   none
_refine_ls_extinction_coef     ?
_refine_ls_abs_structure_details
  'Flack H D (1983), Acta Cryst. A39, 876-881'
_refine_ls_abs_structure_Flack -0.061(2)
_refine_ls_number_reflns       16981
_refine_ls_number_parameters   659
_refine_ls_number_restraints   1
_refine_ls_R_factor_all        0.0341
_refine_ls_R_factor_gt         0.0314
_refine_ls_wR_factor_ref       0.0696
_refine_ls_wR_factor_gt         0.0682
_refine_ls_goodness_of_fit_ref 0.262
_refine_ls_restrained_S_all   0.262
_refine_ls_shift/su_max        0.003
_refine_ls_shift/su_mean       0.000

```

loop_

```

_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group

```

Fe1	Fe	0.122901(15)	0.10428(2)	0.501426(18)	0.01752(11)	Uani	0.546(2)	1	d	P	.	.
Hg1	Hg	0.122901(15)	0.10428(2)	0.501426(18)	0.01752(11)	Uani	0.454(2)	1	d	P	.	.
Fe2	Fe	0.130299(14)	0.61018(2)	0.500109(16)	0.01729(10)	Uani	0.506(2)	1	d	P	.	.
Hg2	Hg	0.130299(14)	0.61018(2)	0.500109(16)	0.01729(10)	Uani	0.494(2)	1	d	P	.	.
Ag1	Ag	0.28021(2)	0.83512(3)	0.91440(3)	0.02593(10)	Uani	1	1	d	.	.	.
Ag2	Ag	0.07835(2)	0.46559(3)	0.08702(3)	0.02467(10)	Uani	1	1	d	.	.	.
Ag3	Ag	0.047727(18)	0.61816(3)	-0.09586(2)	0.02018(9)	Uani	1	1	d	.	.	.
Ag4	Ag	-0.028565(18)	0.38326(2)	0.08976(2)	0.01871(8)	Uani	1	1	d	.	.	.
Ag5	Ag	-0.033039(17)	-0.11835(3)	0.08981(2)	0.01957(8)	Uani	1	1	d	.	.	.
Ag6	Ag	0.076749(19)	-0.02592(3)	0.08682(3)	0.02065(9)	Uani	1	1	d	.	.	.
Ag7	Ag	0.046889(17)	0.11624(3)	0.90526(2)	0.01833(8)	Uani	1	1	d	.	.	.
Ag8	Ag	0.167034(17)	0.24525(2)	0.91108(2)	0.01903(8)	Uani	1	1	d	.	.	.
Ag9	Ag	0.20499(2)	0.09411(3)	0.09844(3)	0.02543(10)	Uani	1	1	d	.	.	.
Ag10	Ag	0.281372(19)	0.32277(3)	0.91184(3)	0.02240(9)	Uani	1	1	d	.	.	.
Ag11	Ag	0.178361(17)	0.74447(2)	0.91295(2)	0.01897(8)	Uani	1	1	d	.	.	.
Ag12	Ag	0.200617(19)	0.60923(3)	0.09394(2)	0.02076(8)	Uani	1	1	d	.	.	.
Ag13	Ag	0.12902(2)	-0.12902(3)	0.71083(3)	0.02133(8)	Uani	1	1	d	.	.	.
Ag14	Ag	0.11669(2)	0.62581(3)	0.30174(3)	0.02276(9)	Uani	1	1	d	.	.	.
Ag15	Ag	0.017308(16)	0.72843(2)	0.30764(2)	0.01605(8)	Uani	1	1	d	.	.	.
Ag16	Ag	0.014475(17)	0.22697(2)	0.29593(2)	0.01684(7)	Uani	1	1	d	.	.	.
Ag17	Ag	0.131611(19)	0.37402(3)	0.70735(2)	0.02002(8)	Uani	1	1	d	.	.	.

Ag18 Ag 0.235210(18) 0.48299(3) 0.69742(2) 0.01990(9) Uani 1 1 d . . .
 Ag19 Ag 0.11995(2) 0.12830(3) 0.30838(3) 0.02386(9) Uani 1 1 d . . .
 Ag20 Ag 0.0000 0.75526(4) 0.5000 0.01891(10) Uani 1 2 d S . .
 Ag21 Ag 0.136562(17) 0.07341(2) 0.69020(2) 0.01554(7) Uani 1 1 d . . .
 Ag22 Ag 0.183003(16) 0.29319(2) 0.50033(2) 0.01686(8) Uani 1 1 d . . .
 Ag23 Ag 0.137532(19) 0.57402(3) 0.69499(2) 0.01912(8) Uani 1 1 d . . .
 Ag24 Ag 0.11434(2) 0.32675(3) 0.29817(3) 0.02107(8) Uani 1 1 d . . .
 Ag25 Ag 0.178294(18) 0.80086(3) 0.49719(2) 0.02178(9) Uani 1 1 d . . .
 Ag26 Ag 0.234617(16) -0.01597(2) 0.69520(2) 0.01659(8) Uani 1 1 d . . .
 Ag27 Ag 0.069523(18) -0.08556(3) 0.50162(2) 0.01937(8) Uani 1 1 d . . .
 Ag28 Ag 0.116633(19) 0.83269(3) 0.29454(3) 0.02098(9) Uani 1 1 d . . .
 Ag29 Ag 0.248024(13) 0.13711(3) 0.501372(13) 0.01682(9) Uani 1 1 d . . .
 Ag30 Ag 0.0000 0.28369(4) 0.5000 0.01911(10) Uani 1 2 d S . .
 Ag31 Ag 0.248555(12) 0.45515(3) 0.502075(14) 0.01653(9) Uani 1 1 d . . .
 Ag32 Ag 0.0000 0.09672(4) 0.5000 0.02402(12) Uani 1 2 d S . .
 Ag33 Ag 0.072298(17) 0.41941(3) 0.50040(2) 0.02052(8) Uani 1 1 d . . .
 Ag34 Ag 0.0000 0.56031(4) 0.5000 0.01567(9) Uani 1 2 d S . .
 As1 As 0.08444(3) 0.22513(4) 0.07232(4) 0.02198(13) Uani 1 1 d . . .
 As2 As 0.08084(3) 0.72355(4) 0.07285(3) 0.02030(12) Uani 1 1 d . . .
 As3 As 0.16626(3) 0.48536(4) 0.92769(3) 0.01835(12) Uani 1 1 d . . .
 As4 As 0.16989(3) -0.01196(4) 0.92668(4) 0.02160(13) Uani 1 1 d . . .
 As5 As 0.24901(2) 0.73297(3) 0.28512(3) 0.01703(11) Uani 1 1 d . . .
 As6 As 0.00013(2) 0.47190(4) 0.28488(3) 0.01797(12) Uani 1 1 d . . .
 As7 As 0.00114(2) -0.02438(3) 0.71439(3) 0.01416(10) Uani 1 1 d . . .
 As8 As 0.25028(2) 0.23298(3) 0.28479(3) 0.01498(10) Uani 1 1 d . . .
 S1 S 0.00661(6) 0.74554(9) 0.15107(8) 0.0223(2) Uani 1 1 d . . .
 S2 S 0.11788(6) 0.11159(10) 0.15381(8) 0.0248(3) Uani 1 1 d . . .
 S3 S 0.24226(6) 0.46568(8) 0.85759(7) 0.0178(2) Uani 1 1 d . . .
 S4 S 0.13515(5) 0.60325(7) 0.85525(7) 0.0140(2) Uani 1 1 d . . .
 S5 S 0.01035(5) 0.24233(7) 0.13887(7) 0.0168(2) Uani 1 1 d . . .
 S6 S 0.12487(6) -0.11805(8) 0.87426(8) 0.0202(2) Uani 1 1 d . . .
 S7 S 0.12064(6) 0.37808(8) 0.86105(8) 0.0198(3) Uani 1 1 d . . .
 S8 S 0.12282(5) 0.83964(7) 0.12975(7) 0.0142(2) Uani 1 1 d . . .
 S9 S 0.11306(6) 0.61056(9) 0.14685(7) 0.0191(2) Uani 1 1 d . . .
 S10 S 0.12580(6) 0.33539(10) 0.13245(8) 0.0220(3) Uani 1 1 d . . .
 S11 S 0.24145(6) -0.02660(8) 0.85481(7) 0.0167(2) Uani 1 1 d . . .
 S12 S 0.25443(5) 0.69873(9) -0.00351(5) 0.0190(3) Uani 1 1 d . . .
 S13 S 0.13136(5) 0.09774(7) 0.85122(6) 0.0129(2) Uani 1 1 d . . .
 S14 S 0.0000 0.51168(9) 0.0000 0.0130(3) Uani 1 2 d S . .
 S15 S 0.0000 0.01297(11) 0.0000 0.0200(3) Uani 1 2 d S . .
 S16 S 0.21319(6) 0.84667(8) 0.35884(7) 0.0160(2) Uani 1 1 d . . .
 S17 S 0.07400(5) -0.02650(7) 0.35289(7) 0.0157(2) Uani 1 1 d . . .
 S18 S 0.08550(5) 0.73689(7) 0.46472(6) 0.0156(2) Uani 1 1 d . . .
 S19 S 0.08326(5) 0.22844(7) 0.44726(7) 0.0172(2) Uani 1 1 d . . .
 S20 S 0.16669(4) -0.02623(6) 0.53039(6) 0.01305(19) Uani 1 1 d . . .
 S21 S 0.21299(6) 0.61444(7) 0.35125(7) 0.0147(2) Uani 1 1 d . . .
 S22 S 0.07369(5) 0.47227(7) 0.35161(6) 0.01157(19) Uani 1 1 d . . .
 S23 S 0.04260(6) -0.13486(8) 0.65087(8) 0.0180(2) Uani 1 1 d . . .
 S24 S -0.03842(6) 0.36196(8) 0.34823(7) 0.0147(2) Uani 1 1 d . . .
 S25 S -0.03742(6) 0.58788(7) 0.35383(7) 0.0155(2) Uani 1 1 d . . .
 S26 S 0.17414(5) 0.23817(7) 0.64448(7) 0.0145(2) Uani 1 1 d . . .
 S27 S 0.21099(5) 0.34744(6) 0.35752(6) 0.01060(19) Uani 1 1 d . . .
 S28 S 0.28549(6) 0.61957(8) 0.65009(7) 0.0159(2) Uani 1 1 d . . .
 S29 S -0.03374(5) 0.08965(6) 0.36107(6) 0.01099(19) Uani 1 1 d . . .
 S30 S 0.16878(6) 0.72989(8) 0.64438(7) 0.0178(2) Uani 1 1 d . . .
 S31 S 0.16113(4) 0.47849(5) 0.55879(5) 0.01042(16) Uani 1 1 d . . .

loop_

 _atom_site_aniso_label

 _atom_site_aniso_U_11

 _atom_site_aniso_U_22

_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12

Fe1 0.01671(18) 0.01724(14) 0.01860(14) 0.00003(7) 0.00049(12) -0.00001(9)
Hg1 0.01671(18) 0.01724(14) 0.01860(14) 0.00003(7) 0.00049(12) -0.00001(9)
Fe2 0.01660(18) 0.01696(14) 0.01832(13) 0.00011(7) 0.00047(11) 0.00011(9)
Hg2 0.01660(18) 0.01696(14) 0.01832(13) 0.00011(7) 0.00047(11) 0.00011(9)
Ag1 0.0259(2) 0.02531(18) 0.02657(15) -0.00018(11) 0.00063(18) -0.00011(14)
Ag2 0.0244(2) 0.02430(18) 0.02536(15) 0.00019(12) 0.00050(17) -0.00016(14)
Ag3 0.0197(2) 0.02005(15) 0.02085(14) 0.00014(11) 0.00059(17) -0.00003(13)
Ag4 0.01876(19) 0.01833(14) 0.01906(13) -0.00007(10) 0.00040(15) 0.00033(11)
Ag5 0.0190(2) 0.01934(15) 0.02040(13) 0.00009(10) 0.00022(15) 0.00016(11)
Ag6 0.0205(2) 0.02072(16) 0.02075(13) 0.00024(10) 0.00049(16) 0.00006(11)
Ag7 0.0180(2) 0.01807(14) 0.01889(13) -0.00023(10) 0.00044(16) -0.00015(12)
Ag8 0.0186(2) 0.01870(13) 0.01974(12) 0.00010(9) -0.00008(14) 0.00020(12)
Ag9 0.0255(3) 0.02514(18) 0.02567(15) -0.00013(11) 0.00122(17) -0.00007(14)
Ag10 0.0219(2) 0.02224(16) 0.02312(13) -0.00011(10) 0.00045(16) -0.00032(12)
Ag11 0.01873(19) 0.01894(13) 0.01924(11) 0.00001(9) 0.00068(14) -0.00022(12)
Ag12 0.0209(2) 0.01995(15) 0.02147(12) -0.00002(9) 0.00067(15) -0.00027(11)
Ag13 0.0211(2) 0.02094(16) 0.02199(14) -0.00005(11) 0.00037(16) 0.00002(13)
Ag14 0.0227(2) 0.02187(16) 0.02368(14) -0.00005(11) 0.00119(17) 0.00003(14)
Ag15 0.01589(18) 0.01513(11) 0.01715(12) 0.00003(9) 0.00058(13) -0.00023(10)
Ag16 0.01618(18) 0.01658(12) 0.01777(11) -0.00010(10) -0.00004(13) -0.00042(11)
Ag17 0.0196(2) 0.01958(15) 0.02086(13) -0.00025(10) 0.00011(15) 0.00000(13)
Ag18 0.0199(2) 0.01948(15) 0.02034(14) 0.00023(10) 0.00029(16) 0.00065(12)
Ag19 0.0238(2) 0.02298(16) 0.02485(14) -0.00042(11) 0.00114(18) -0.00021(13)
Ag20 0.0190(3) 0.0189(2) 0.01887(15) 0.000 0.00061(18) 0.000
Ag21 0.01533(17) 0.01476(12) 0.01653(12) 0.00018(9) 0.00076(13) -0.00037(11)
Ag22 0.01644(18) 0.01664(13) 0.01750(11) -0.00004(9) 0.00017(13) 0.00001(10)
Ag23 0.01898(19) 0.01825(14) 0.02014(14) 0.00010(10) 0.00083(15) -0.00035(12)
Ag24 0.0210(2) 0.02051(15) 0.02173(14) 0.00022(10) 0.00073(15) -0.00032(13)
Ag25 0.0219(2) 0.02086(15) 0.02257(13) -0.00007(10) 0.00074(16) 0.00013(12)
Ag26 0.0161(2) 0.01638(13) 0.01730(13) 0.00017(9) 0.00022(15) 0.00020(11)
Ag27 0.0196(2) 0.01848(15) 0.01998(13) 0.00005(9) 0.00064(15) 0.00020(11)
Ag28 0.0213(2) 0.01983(15) 0.02183(14) 0.00033(10) 0.00088(15) -0.00040(12)
Ag29 0.0167(2) 0.01637(16) 0.01743(14) -0.00009(5) 0.00051(17) -0.00002(7)
Ag30 0.0191(3) 0.01835(18) 0.01994(14) 0.000 0.00069(18) 0.000
Ag31 0.0157(2) 0.01611(16) 0.01774(14) 0.00006(6) 0.00013(17) 0.00004(8)
Ag32 0.0240(3) 0.0232(2) 0.02487(17) 0.000 0.0009(2) 0.000
Ag33 0.0204(2) 0.01981(14) 0.02136(13) 0.00002(10) 0.00056(15) 0.00029(12)
Ag34 0.0161(2) 0.01497(16) 0.01591(13) 0.000 0.00065(15) 0.000
As1 0.0216(4) 0.0215(2) 0.0228(2) -0.00041(16) -0.0001(3) -0.00080(18)
As2 0.0197(3) 0.0200(2) 0.0212(2) 0.00004(16) 0.0003(2) 0.00003(17)
As3 0.0173(3) 0.0187(2) 0.01899(19) -0.00044(14) 0.0004(2) 0.00018(17)
As4 0.0219(4) 0.0209(2) 0.0220(2) -0.00054(16) 0.0003(2) -0.00067(19)
As5 0.0171(3) 0.0165(2) 0.01753(18) 0.00029(14) 0.0009(2) 0.00033(16)
As6 0.0176(3) 0.0177(2) 0.01864(19) 0.00043(14) 0.0008(2) 0.00003(16)
As7 0.0145(3) 0.01340(18) 0.01462(17) -0.00006(12) 0.00078(19) -0.00014(14)
As8 0.0153(3) 0.01436(19) 0.01531(17) 0.00042(13) 0.00080(19) 0.00029(15)
S1 0.0209(6) 0.0227(4) 0.0231(4) -0.0022(3) 0.0018(5) 0.0016(4)
S2 0.0240(8) 0.0247(5) 0.0258(5) 0.0010(4) 0.0003(6) -0.0005(5)
S3 0.0172(6) 0.0176(4) 0.0187(4) -0.0001(3) 0.0005(4) 0.0009(4)
S4 0.0150(6) 0.0123(3) 0.0146(3) 0.0005(2) 0.0013(4) 0.0009(3)
S5 0.0154(6) 0.0167(4) 0.0183(3) 0.0007(3) 0.0006(4) -0.0003(3)
S6 0.0210(6) 0.0185(4) 0.0213(4) -0.0004(3) 0.0016(5) 0.0020(4)
S7 0.0193(6) 0.0190(4) 0.0212(4) 0.0003(3) 0.0024(5) 0.0003(3)
S8 0.0137(5) 0.0139(4) 0.0151(4) 0.0004(3) 0.0005(4) -0.0001(3)
S9 0.0187(6) 0.0193(4) 0.0192(4) 0.0001(3) 0.0006(5) -0.0009(4)
S10 0.0206(7) 0.0220(5) 0.0233(5) 0.0007(4) 0.0009(5) 0.0002(4)
S11 0.0180(6) 0.0152(4) 0.0171(4) 0.0006(3) 0.0003(4) -0.0010(3)

```

S12 0.0184(6) 0.0188(4) 0.0199(5) 0.0007(2) 0.0003(5) -0.0003(3)
S13 0.0123(5) 0.0124(4) 0.0141(3) 0.0003(2) 0.0004(4) 0.0007(3)
S14 0.0143(7) 0.0102(5) 0.0145(5) 0.000 -0.0003(6) 0.000
S15 0.0188(9) 0.0199(6) 0.0213(6) 0.000 -0.0002(7) 0.000
S16 0.0156(6) 0.0166(4) 0.0158(4) 0.0004(3) 0.0002(5) -0.0005(4)
S17 0.0153(6) 0.0156(4) 0.0163(4) 0.0006(3) -0.0003(5) -0.0012(3)
S18 0.0134(5) 0.0151(4) 0.0181(4) -0.0016(3) -0.0011(4) 0.0001(3)
S19 0.0150(6) 0.0172(4) 0.0193(3) -0.0009(3) -0.0018(4) -0.0006(3)
S20 0.0112(5) 0.0134(3) 0.0146(3) 0.0001(2) 0.0005(4) 0.0007(2)
S21 0.0163(6) 0.0132(4) 0.0145(3) -0.0005(3) -0.0001(5) 0.0004(3)
S22 0.0115(5) 0.0119(3) 0.0113(3) 0.0001(3) -0.0002(4) -0.0015(3)
S23 0.0165(7) 0.0198(4) 0.0176(4) 0.0006(3) -0.0018(5) -0.0010(4)
S24 0.0144(6) 0.0156(4) 0.0142(4) 0.0003(3) -0.0003(4) 0.0001(3)
S25 0.0146(6) 0.0164(4) 0.0154(4) -0.0008(3) 0.0001(4) -0.0007(3)
S26 0.0131(5) 0.0153(4) 0.0152(3) 0.0003(3) -0.0001(4) 0.0002(3)
S27 0.0099(5) 0.0105(3) 0.0115(3) 0.0001(2) 0.0000(4) -0.0002(3)
S28 0.0157(6) 0.0153(4) 0.0168(4) 0.0002(3) -0.0003(5) 0.0015(3)
S29 0.0107(5) 0.0116(3) 0.0106(3) -0.0005(2) 0.0009(4) -0.0010(3)
S30 0.0184(6) 0.0171(4) 0.0181(4) -0.0004(3) 0.0010(4) 0.0006(3)
S31 0.0088(5) 0.0106(3) 0.0118(3) -0.0004(2) -0.0011(3) -0.0001(2)

```

_geom_special_details

;

All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

;

loop_

_geom_bond_atom_site_label_1
_geom_bond_atom_site_label_2
_geom_bond_distance
_geom_bond_site_symmetry_2
_geom_bond_publ_flag

Fe1 S19 2.2908(13) . ?

Fe1 S20 2.3127(10) . ?

Fe1 Ag21 2.9839(5) . ?

Fe1 Ag19 3.0168(5) . ?

Fe1 Ag27 3.1762(5) . ?

Fe2 S18 2.2991(12) . ?

Fe2 S31 2.3213(9) . ?

Fe2 Ag23 3.0763(5) . ?

Fe2 Ag14 3.1040(5) . ?

Fe2 Ag25 3.1297(6) . ?

Ag1 S11 2.4875(14) 1_565 ?

Ag1 S12 2.5091(13) 1_556 ?

Ag1 S10 2.5554(15) 4_556 ?

Ag1 Ag11 2.9797(7) . ?

Ag1 Ag10 3.1506(7) 4_557 ?

Ag1 Ag8 3.3151(7) 4_557 ?

Ag2 S10 2.4180(16) . ?

Ag2 S14 2.5334(7) . ?

Ag2 S9 2.5346(15) . ?

Ag2 Ag4 3.0450(7) . ?

Ag2 Ag4 3.2685(7) 2 ?

Ag3 S4 2.4125(12) 1_554 ?

Ag3 S14 2.5191(9) . ?

Ag3 S1 2.5276(15) 2 ?

Ag4 S5 2.4682(13) . ?
Ag4 S14 2.4979(11) . ?
Ag4 S7 2.5198(14) 2_556 ?
Ag4 Ag4 3.1657(7) 2 ?
Ag4 Ag2 3.2685(7) 2 ?
Ag5 S6 2.4566(15) 2_556 ?
Ag5 S1 2.4796(15) 1_545 ?
Ag5 S15 2.5692(14) . ?
Ag5 Ag6 3.1770(7) . ?
Ag5 Ag6 3.2698(7) 2 ?
Ag5 Ag5 3.2840(7) 2 ?
Ag6 S8 2.4416(13) 1_545 ?
Ag6 S15 2.4707(7) . ?
Ag6 S2 2.5477(17) . ?
Ag6 Ag5 3.2698(7) 2 ?
Ag7 S13 2.3736(12) . ?
Ag7 S15 2.4673(11) 1_556 ?
Ag7 S5 2.5041(13) 2_556 ?
Ag8 S7 2.4579(14) . ?
Ag8 S13 2.5766(12) . ?
Ag8 S12 2.5841(13) 4_546 ?
Ag8 Ag10 3.1945(7) . ?
Ag8 Ag1 3.3151(7) 4_547 ?
Ag9 S12 2.4048(12) 4_545 ?
Ag9 S2 2.4430(15) . ?
Ag9 S3 2.4638(14) 4_546 ?
Ag10 S3 2.5211(14) . ?
Ag10 S12 2.5282(13) 4_546 ?
Ag10 S8 2.5910(13) 4_546 ?
Ag10 Ag11 3.1357(6) 4_547 ?
Ag10 Ag1 3.1506(7) 4_547 ?
Ag10 Ag12 3.2486(7) 4_546 ?
Ag11 S12 2.4562(13) 1_556 ?
Ag11 S6 2.5620(14) 1_565 ?
Ag11 S4 2.5626(13) . ?
Ag11 Ag10 3.1357(6) 4_557 ?
Ag12 S9 2.4262(13) . ?
Ag12 S12 2.4674(12) . ?
Ag12 S11 2.6579(14) 4_556 ?
Ag12 Ag10 3.2486(7) 4_556 ?
Ag13 S23 2.4282(18) . ?
Ag13 S6 2.5438(12) . ?
Ag13 S30 2.5796(11) 1_545 ?
Ag13 Ag21 3.0693(6) . ?
Ag13 Ag26 3.2414(6) . ?
Ag14 S9 2.4150(12) . ?
Ag14 S21 2.6202(17) . ?
Ag14 S22 2.6833(10) . ?
Ag14 Ag15 3.0131(7) . ?
Ag14 Ag28 3.1151(6) . ?
Ag15 S1 2.4562(13) . ?
Ag15 S25 2.6510(12) . ?
Ag15 S23 2.6625(14) 2_566 ?
Ag15 Ag28 3.0306(6) . ?
Ag15 Ag20 3.0479(4) . ?
Ag16 S5 2.4491(12) . ?
Ag16 S24 2.5872(12) . ?
Ag16 S29 2.6232(10) . ?
Ag16 S19 2.9418(15) . ?
Ag16 Ag24 3.0003(7) . ?
Ag16 Ag19 3.1243(7) . ?

Ag16 Ag30 3.3029(4) . ?
Ag17 S7 2.4041(12) . ?
Ag17 S26 2.5237(10) . ?
Ag17 S24 2.5734(17) 2_556 ?
Ag17 S31 2.8978(9) . ?
Ag17 Ag23 3.0196(6) . ?
Ag17 Ag18 3.1591(7) . ?
Ag18 S3 2.5039(12) . ?
Ag18 S28 2.5470(13) . ?
Ag18 S16 2.6053(12) 4_546 ?
Ag18 S31 2.8782(12) . ?
Ag18 Ag23 2.8864(7) . ?
Ag18 Ag31 3.0812(5) . ?
Ag19 S2 2.4112(14) . ?
Ag19 S28 2.5417(17) 4_546 ?
Ag19 S17 2.7097(12) . ?
Ag19 S19 2.8021(11) . ?
Ag19 Ag24 2.9940(6) . ?
Ag20 S18 2.3106(12) . ?
Ag20 S18 2.3106(12) 2_556 ?
Ag20 Ag34 2.9337(7) . ?
Ag20 Ag27 3.0013(7) 1_565 ?
Ag20 Ag27 3.0013(7) 2_566 ?
Ag20 Ag15 3.0479(4) 2_556 ?
Ag21 S13 2.5291(10) . ?
Ag21 S26 2.7596(11) . ?
Ag21 S29 2.7956(15) 2_556 ?
Ag21 Ag26 2.8839(6) . ?
Ag22 S26 2.3971(11) . ?
Ag22 S27 2.4753(9) . ?
Ag22 S19 2.8859(15) . ?
Ag22 Ag29 2.8943(6) . ?
Ag22 Ag31 2.9744(6) . ?
Ag23 S4 2.5259(11) . ?
Ag23 S30 2.6054(12) . ?
Ag23 S31 2.6317(8) . ?
Ag23 S25 2.7148(17) 2_556 ?
Ag24 S22 2.5714(10) . ?
Ag24 S10 2.5934(13) . ?
Ag24 S27 2.6893(15) . ?
Ag24 S19 2.8666(11) . ?
Ag25 S16 2.4356(10) . ?
Ag25 S30 2.5344(12) . ?
Ag25 S18 2.6436(14) . ?
Ag25 S20 2.6700(10) 1_565 ?
Ag25 Ag31 3.0017(7) 4_556 ?
Ag25 Ag29 3.1217(6) 4_556 ?
Ag25 Ag27 3.3065(6) 1_565 ?
Ag26 S11 2.4863(12) . ?
Ag26 S21 2.4983(12) 4_546 ?
Ag26 S27 2.6290(10) 4_546 ?
Ag26 Ag31 3.1248(4) 4_546 ?
Ag27 S17 2.4760(11) . ?
Ag27 S23 2.5345(12) . ?
Ag27 S20 2.7144(12) . ?
Ag27 S18 2.7644(11) 1_545 ?
Ag27 Ag20 3.0013(7) 1_545 ?
Ag27 Ag32 3.2855(7) . ?
Ag27 Ag25 3.3065(6) 1_545 ?
Ag28 S17 2.5599(11) 1_565 ?
Ag28 S8 2.5648(11) . ?

Ag28 S16 2.7041(17) . ?
Ag29 S28 2.5143(14) 4_546 ?
Ag29 S21 2.5178(14) 4_546 ?
Ag29 Ag31 2.7401(7) 4_546 ?
Ag29 Ag25 3.1217(6) 4_546 ?
Ag29 Hg2 3.1910(5) 4_546 ?
Ag30 S19 2.4649(12) . ?
Ag30 S19 2.4649(12) 2_556 ?
Ag30 Ag33 2.7762(6) . ?
Ag30 Ag33 2.7762(6) 2_556 ?
Ag30 S24 2.8101(13) 2_556 ?
Ag30 S24 2.8101(13) . ?
Ag30 Ag32 2.8135(7) . ?
Ag30 Ag16 3.3029(4) 2_556 ?
Ag31 S20 2.2822(11) 4_556 ?
Ag31 S31 2.4690(10) . ?
Ag31 Ag29 2.7401(7) 4_556 ?
Ag31 S16 2.8775(13) 4_546 ?
Ag31 S27 2.9292(11) . ?
Ag31 Ag25 3.0017(7) 4_546 ?
Ag31 Ag26 3.1248(4) 4_556 ?
Ag32 S29 2.3239(12) . ?
Ag32 S29 2.3239(12) 2_556 ?
Ag32 Hg1 3.1987(5) 2_556 ?
Ag32 Ag27 3.2855(7) 2_556 ?
Ag33 S22 2.4419(10) . ?
Ag33 S31 2.6308(12) . ?
Ag33 S24 2.6584(11) 2_556 ?
Ag33 Ag34 2.8340(6) . ?
Ag34 S25 2.4962(13) 2_556 ?
Ag34 Ag33 2.8340(6) 2_556 ?
As1 S10 2.1832(18) . ?
As1 S5 2.2077(13) . ?
As1 S2 2.2931(18) . ?
As2 S9 2.2130(16) . ?
As2 S8 2.2383(15) . ?
As2 S1 2.3114(13) . ?
As3 S4 2.2476(14) . ?
As3 S7 2.2507(15) . ?
As3 S3 2.2821(13) . ?
As4 S6 2.1374(16) . ?
As4 S11 2.1875(13) . ?
As4 S13 2.2546(14) . ?
As5 S16 2.2624(12) . ?
As5 S21 2.2639(11) . ?
As5 S26 2.2725(16) 4_556 ?
As6 S22 2.1691(14) . ?
As6 S24 2.1730(12) . ?
As6 S25 2.2713(12) . ?
As7 S17 2.2096(16) 2_556 ?
As7 S23 2.2163(13) . ?
As7 S29 2.2466(10) 2_556 ?
As8 S28 2.1935(12) 4_546 ?
As8 S27 2.3021(10) . ?
As8 S30 2.3685(17) 4_546 ?
S1 Ag5 2.4796(15) 1_565 ?
S1 Ag3 2.5276(15) 2 ?
S3 Ag9 2.4638(14) 4_556 ?
S4 Ag3 2.4125(12) 1_556 ?
S5 Ag7 2.5041(13) 2_556 ?

S6 Ag5 2.4566(15) 2_556 ?
S6 Ag11 2.5620(14) 1_545 ?
S7 Ag4 2.5198(14) 2_556 ?
S8 Ag6 2.4416(13) 1_565 ?
S8 Ag10 2.5910(13) 4_556 ?
S10 Ag1 2.5554(15) 4_546 ?
S11 Ag1 2.4875(14) 1_545 ?
S11 Ag12 2.6579(14) 4_546 ?
S12 Ag9 2.4048(12) 4 ?
S12 Ag11 2.4562(13) 1_554 ?
S12 Ag1 2.5091(13) 1_554 ?
S12 Ag10 2.5282(13) 4_556 ?
S12 Ag8 2.5841(13) 4_556 ?
S14 Ag4 2.4979(11) 2 ?
S14 Ag3 2.5191(9) 2 ?
S14 Ag2 2.5334(7) 2 ?
S15 Ag7 2.4673(11) 1_554 ?
S15 Ag7 2.4673(11) 2_556 ?
S15 Ag6 2.4707(7) 2 ?
S15 Ag5 2.5692(14) 2 ?
S16 Ag18 2.6053(12) 4_556 ?
S16 Ag31 2.8775(13) 4_556 ?
S17 As7 2.2096(16) 2_556 ?
S17 Ag28 2.5599(11) 1_545 ?
S18 Ag27 2.7644(11) 1_565 ?
S20 Ag31 2.2822(11) 4_546 ?
S20 Ag25 2.6700(10) 1_545 ?
S21 Ag26 2.4983(12) 4_556 ?
S21 Ag29 2.5178(14) 4_556 ?
S23 Ag15 2.6625(14) 2_546 ?
S24 Ag17 2.5734(17) 2_556 ?
S24 Ag33 2.6584(11) 2_556 ?
S25 Ag23 2.7148(17) 2_556 ?
S26 As5 2.2725(16) 4_546 ?
S27 Ag26 2.6290(10) 4_556 ?
S28 As8 2.1935(12) 4_556 ?
S28 Ag29 2.5143(14) 4_556 ?
S28 Ag19 2.5417(17) 4_556 ?
S29 As7 2.2466(10) 2_556 ?
S29 Ag21 2.7956(15) 2_556 ?
S30 As8 2.3685(17) 4_556 ?
S30 Ag13 2.5796(11) 1_565 ?

loop_
_geom_angle_atom_site_label_1
_geom_angle_atom_site_label_2
_geom_angle_atom_site_label_3
_geom_angle
_geom_angle_site_symmetry_1
_geom_angle_site_symmetry_3
_geom_angle_publ_flag
S19 Fe1 S20 169.61(3) . . ?
S19 Fe1 Ag21 122.49(3) . . ?
S20 Fe1 Ag21 67.79(2) . . ?
S19 Fe1 Ag19 61.96(3) . . ?
S20 Fe1 Ag19 107.68(2) . . ?
Ag21 Fe1 Ag19 174.212(18) . . ?
S19 Fe1 Ag27 122.57(4) . . ?
S20 Fe1 Ag27 56.69(3) . . ?
Ag21 Fe1 Ag27 84.727(13) . . ?
Ag19 Fe1 Ag27 95.774(15) . . ?

S18 Fe2 S31 167.10(3) . . ?
S18 Fe2 Ag23 114.13(3) . . ?
S31 Fe2 Ag23 56.29(2) . . ?
S18 Fe2 Ag14 69.29(3) . . ?
S31 Fe2 Ag14 119.35(2) . . ?
Ag23 Fe2 Ag14 173.441(18) . . ?
S18 Fe2 Ag25 55.79(3) . . ?
S31 Fe2 Ag25 130.66(3) . . ?
Ag23 Fe2 Ag25 98.901(15) . . ?
Ag14 Fe2 Ag25 87.646(14) . . ?
S11 Ag1 S12 139.80(4) 1_565 1_556 ?
S11 Ag1 S10 106.20(5) 1_565 4_556 ?
S12 Ag1 S10 113.91(5) 1_556 4_556 ?
S11 Ag1 Ag11 91.27(4) 1_565 . ?
S12 Ag1 Ag11 52.31(3) 1_556 . ?
S10 Ag1 Ag11 148.31(4) 4_556 . ?
S11 Ag1 Ag10 99.21(3) 1_565 4_557 ?
S12 Ag1 Ag10 51.56(3) 1_556 4_557 ?
S10 Ag1 Ag10 137.44(4) 4_556 4_557 ?
Ag11 Ag1 Ag10 61.454(16) . 4_557 ?
S11 Ag1 Ag8 144.01(3) 1_565 4_557 ?
S12 Ag1 Ag8 50.38(3) 1_556 4_557 ?
S10 Ag1 Ag8 80.88(4) 4_556 4_557 ?
Ag11 Ag1 Ag8 100.506(19) . 4_557 ?
Ag10 Ag1 Ag8 59.153(15) 4_557 4_557 ?
S10 Ag2 S14 141.64(5) . . ?
S10 Ag2 S9 114.26(6) . . ?
S14 Ag2 S9 104.05(5) . . ?
S10 Ag2 Ag4 97.50(4) . . ?
S14 Ag2 Ag4 52.23(3) . . ?
S9 Ag2 Ag4 131.92(4) . . ?
S10 Ag2 Ag4 97.81(4) . 2 ?
S14 Ag2 Ag4 49.02(3) . 2 ?
S9 Ag2 Ag4 140.49(3) . 2 ?
Ag4 Ag2 Ag4 60.064(16) . 2 ?
S4 Ag3 S14 126.58(4) 1_554 . ?
S4 Ag3 S1 119.34(4) 1_554 2 ?
S14 Ag3 S1 113.94(4) . 2 ?
S5 Ag4 S14 135.55(3) . . ?
S5 Ag4 S7 105.58(4) . 2_556 ?
S14 Ag4 S7 118.67(4) . 2_556 ?
S5 Ag4 Ag2 88.93(4) . . ?
S14 Ag4 Ag2 53.289(14) . . ?
S7 Ag4 Ag2 152.48(3) 2_556 . ?
S5 Ag4 Ag4 94.44(2) . 2 ?
S14 Ag4 Ag4 50.68(2) . 2 ?
S7 Ag4 Ag4 136.00(4) 2_556 2 ?
Ag2 Ag4 Ag4 63.472(17) . 2 ?
S5 Ag4 Ag2 138.06(3) . 2 ?
S14 Ag4 Ag2 49.960(13) . 2 ?
S7 Ag4 Ag2 83.91(4) 2_556 2 ?
Ag2 Ag4 Ag2 100.99(2) . 2 ?
Ag4 Ag4 Ag2 56.464(15) 2 2 ?
S6 Ag5 S1 108.48(5) 2_556 1_545 ?
S6 Ag5 S15 116.81(4) 2_556 . ?
S1 Ag5 S15 134.70(4) 1_545 . ?
S6 Ag5 Ag6 151.41(3) 2_556 . ?
S1 Ag5 Ag6 89.76(4) 1_545 . ?
S15 Ag5 Ag6 49.555(12) . . ?
S6 Ag5 Ag6 81.74(4) 2_556 2 ?
S1 Ag5 Ag6 144.47(3) 1_545 2 ?

S15 Ag5 Ag6 48.248(12) . 2 ?
Ag6 Ag5 Ag6 96.250(19) . 2 ?
S6 Ag5 Ag5 135.07(4) 2_556 2 ?
S1 Ag5 Ag5 96.11(3) 1_545 2 ?
S15 Ag5 Ag5 50.27(3) . 2 ?
Ag6 Ag5 Ag5 60.778(15) . 2 ?
Ag6 Ag5 Ag5 57.993(14) 2 2 ?
S8 Ag6 S15 137.57(5) 1_545 . ?
S8 Ag6 S2 110.97(5) 1_545 . ?
S15 Ag6 S2 111.43(6) . . ?
S8 Ag6 Ag5 94.17(3) 1_545 . ?
S15 Ag6 Ag5 52.32(3) . . ?
S2 Ag6 Ag5 136.43(4) . . ?
S8 Ag6 Ag5 92.48(3) 1_545 2 ?
S15 Ag6 Ag5 50.88(3) . 2 ?
S2 Ag6 Ag5 146.09(3) . 2 ?
Ag5 Ag6 Ag5 61.229(16) . 2 ?
S13 Ag7 S15 126.81(4) . 1_556 ?
S13 Ag7 S5 122.85(4) . 2_556 ?
S15 Ag7 S5 110.16(4) 1_556 2_556 ?
S7 Ag8 S13 114.33(5) . . ?
S7 Ag8 S12 141.26(5) . 4_546 ?
S13 Ag8 S12 104.35(4) . 4_546 ?
S7 Ag8 Ag10 99.16(3) . . ?
S13 Ag8 Ag10 130.45(3) . . ?
S12 Ag8 Ag10 50.55(3) 4_546 . ?
S7 Ag8 Ag1 97.22(4) . 4_547 ?
S13 Ag8 Ag1 142.35(3) . 4_547 ?
S12 Ag8 Ag1 48.41(3) 4_546 4_547 ?
Ag10 Ag8 Ag1 57.858(15) . 4_547 ?
S12 Ag9 S2 123.84(5) 4_545 . ?
S12 Ag9 S3 115.92(5) 4_545 4_546 ?
S2 Ag9 S3 120.21(5) . 4_546 ?
S3 Ag10 S12 131.92(4) . 4_546 ?
S3 Ag10 S8 102.70(4) . 4_546 ?
S12 Ag10 S8 124.83(5) 4_546 4_546 ?
S3 Ag10 Ag11 137.85(3) . 4_547 ?
S12 Ag10 Ag11 50.00(3) 4_546 4_547 ?
S8 Ag10 Ag11 86.37(3) 4_546 4_547 ?
S3 Ag10 Ag1 91.65(3) . 4_547 ?
S12 Ag10 Ag1 51.01(3) 4_546 4_547 ?
S8 Ag10 Ag1 134.66(4) 4_546 4_547 ?
Ag11 Ag10 Ag1 56.587(15) 4_547 4_547 ?
S3 Ag10 Ag8 86.37(4) . . ?
S12 Ag10 Ag8 52.11(3) 4_546 . ?
S8 Ag10 Ag8 158.73(3) 4_546 . ?
Ag11 Ag10 Ag8 99.865(17) 4_547 . ?
Ag1 Ag10 Ag8 62.989(16) 4_547 . ?
S3 Ag10 Ag12 153.18(4) . 4_546 ?
S12 Ag10 Ag12 48.63(3) 4_546 4_546 ?
S8 Ag10 Ag12 87.19(3) 4_546 4_546 ?
Ag11 Ag10 Ag12 66.729(14) 4_547 4_546 ?
Ag1 Ag10 Ag12 98.990(13) 4_547 4_546 ?
Ag8 Ag10 Ag12 76.889(15) . 4_546 ?
S12 Ag11 S6 141.63(5) 1_556 1_565 ?
S12 Ag11 S4 107.56(5) 1_556 . ?
S6 Ag11 S4 110.59(5) 1_565 . ?
S12 Ag11 Ag1 53.94(3) 1_556 . ?
S6 Ag11 Ag1 96.52(4) 1_565 . ?
S4 Ag11 Ag1 140.36(3) . . ?
S12 Ag11 Ag10 52.05(3) 1_556 4_557 ?

S6 Ag11 Ag10 94.43(3) 1_565 4_557 ?
S4 Ag11 Ag10 139.24(3) . 4_557 ?
Ag1 Ag11 Ag10 61.959(16) . 4_557 ?
S9 Ag12 S12 137.79(5) . . ?
S9 Ag12 S11 115.89(4) . 4_556 ?
S12 Ag12 S11 106.27(4) . 4_556 ?
S9 Ag12 Ag10 97.88(4) . 4_556 ?
S12 Ag12 Ag10 50.26(3) . 4_556 ?
S11 Ag12 Ag10 133.42(4) 4_556 4_556 ?
S23 Ag13 S6 109.79(5) . . ?
S23 Ag13 S30 100.94(5) . 1_545 ?
S6 Ag13 S30 118.14(5) . 1_545 ?
S23 Ag13 Ag21 93.19(4) . . ?
S6 Ag13 Ag21 92.45(3) . . ?
S30 Ag13 Ag21 138.51(3) 1_545 . ?
S23 Ag13 Ag26 140.62(3) . . ?
S6 Ag13 Ag26 94.72(4) . . ?
S30 Ag13 Ag26 93.42(3) 1_545 . ?
Ag21 Ag13 Ag26 54.302(13) . . ?
S9 Ag14 S21 108.43(4) . . ?
S9 Ag14 S22 101.04(4) . . ?
S21 Ag14 S22 105.00(4) . . ?
S9 Ag14 Ag15 92.94(4) . . ?
S21 Ag14 Ag15 147.47(3) . . ?
S22 Ag14 Ag15 94.19(3) . . ?
S9 Ag14 Fe2 169.30(4) . . ?
S21 Ag14 Fe2 66.57(3) . . ?
S22 Ag14 Fe2 72.17(3) . . ?
Ag15 Ag14 Fe2 95.778(16) . . ?
S9 Ag14 Ag28 93.40(4) . . ?
S21 Ag14 Ag28 94.36(3) . . ?
S22 Ag14 Ag28 150.55(3) . . ?
Ag15 Ag14 Ag28 59.250(15) . . ?
Fe2 Ag14 Ag28 96.391(17) . . ?
S1 Ag15 S25 107.07(5) . . ?
S1 Ag15 S23 95.49(4) . 2_566 ?
S25 Ag15 S23 103.58(4) . 2_566 ?
S1 Ag15 Ag14 96.61(4) . . ?
S25 Ag15 Ag14 93.54(3) . . ?
S23 Ag15 Ag14 155.10(4) 2_566 . ?
S1 Ag15 Ag28 88.29(4) . . ?
S25 Ag15 Ag28 152.97(4) . . ?
S23 Ag15 Ag28 96.71(3) 2_566 . ?
Ag14 Ag15 Ag28 62.051(15) . . ?
S1 Ag15 Ag20 159.68(4) . . ?
S25 Ag15 Ag20 75.98(3) . . ?
S23 Ag15 Ag20 64.55(3) 2_566 . ?
Ag14 Ag15 Ag20 103.310(18) . . ?
Ag28 Ag15 Ag20 97.404(17) . . ?
S5 Ag16 S24 102.60(4) . . ?
S5 Ag16 S29 116.09(4) . . ?
S24 Ag16 S29 103.94(3) . . ?
S5 Ag16 S19 144.63(4) . . ?
S24 Ag16 S19 93.77(4) . . ?
S29 Ag16 S19 89.33(4) . . ?
S5 Ag16 Ag24 89.78(3) . . ?
S24 Ag16 Ag24 93.77(3) . . ?
S29 Ag16 Ag24 143.70(4) . . ?
S19 Ag16 Ag24 57.68(2) . . ?
S5 Ag16 Ag19 97.97(3) . . ?
S24 Ag16 Ag19 145.33(4) . . ?

S29 Ag16 Ag19 91.36(3) . . ?
S19 Ag16 Ag19 54.92(2) . . ?
Ag24 Ag16 Ag19 58.488(15) . . ?
S5 Ag16 Ag30 157.62(3) . . ?
S24 Ag16 Ag30 55.40(3) . . ?
S29 Ag16 Ag30 77.08(2) . . ?
S19 Ag16 Ag30 46.05(2) . . ?
Ag24 Ag16 Ag30 87.938(16) . . ?
Ag19 Ag16 Ag30 99.757(17) . . ?
S7 Ag17 S26 117.34(5) . . ?
S7 Ag17 S24 102.47(5) . 2_556 ?
S26 Ag17 S24 103.17(4) . 2_556 ?
S7 Ag17 S31 143.99(4) . . ?
S26 Ag17 S31 90.73(3) . . ?
S24 Ag17 S31 91.49(4) 2_556 . ?
S7 Ag17 Ag23 92.53(3) . . ?
S26 Ag17 Ag23 139.47(3) . . ?
S24 Ag17 Ag23 95.59(3) 2_556 . ?
S31 Ag17 Ag23 52.764(18) . . ?
S7 Ag17 Ag18 98.19(4) . . ?
S26 Ag17 Ag18 91.45(3) . . ?
S24 Ag17 Ag18 145.29(3) 2_556 . ?
S31 Ag17 Ag18 56.55(2) . . ?
Ag23 Ag17 Ag18 55.645(14) . . ?
S3 Ag18 S28 109.63(5) . . ?
S3 Ag18 S16 102.49(4) . 4_546 ?
S28 Ag18 S16 105.79(4) . 4_546 ?
S3 Ag18 S31 141.54(4) . . ?
S28 Ag18 S31 98.39(4) . . ?
S16 Ag18 S31 94.30(4) 4_546 . ?
S3 Ag18 Ag23 96.93(3) . . ?
S28 Ag18 Ag23 93.84(3) . . ?
S16 Ag18 Ag23 145.56(4) 4_546 . ?
S31 Ag18 Ag23 54.32(2) . . ?
S3 Ag18 Ag31 162.53(3) . . ?
S28 Ag18 Ag31 76.39(3) . . ?
S16 Ag18 Ag31 60.11(3) 4_546 . ?
S31 Ag18 Ag31 48.805(19) . . ?
Ag23 Ag18 Ag31 99.027(19) . . ?
S3 Ag18 Ag17 87.37(3) . . ?
S28 Ag18 Ag17 150.79(4) . . ?
S16 Ag18 Ag17 92.82(3) 4_546 . ?
S31 Ag18 Ag17 57.14(2) . . ?
Ag23 Ag18 Ag17 59.728(15) . . ?
Ag31 Ag18 Ag17 94.553(18) . . ?
S2 Ag19 S28 105.16(5) . 4_546 ?
S2 Ag19 S17 99.03(5) . . ?
S28 Ag19 S17 108.59(4) 4_546 . ?
S2 Ag19 S19 144.62(5) . . ?
S28 Ag19 S19 99.62(4) 4_546 . ?
S17 Ag19 S19 96.50(3) . . ?
S2 Ag19 Ag24 92.90(4) . . ?
S28 Ag19 Ag24 96.41(3) 4_546 . ?
S17 Ag19 Ag24 148.16(3) . . ?
S19 Ag19 Ag24 59.17(3) . . ?
S2 Ag19 Fe1 167.13(4) . . ?
S28 Ag19 Fe1 74.00(3) 4_546 . ?
S17 Ag19 Fe1 69.65(3) . . ?
S19 Ag19 Fe1 46.18(3) . . ?
Ag24 Ag19 Fe1 99.957(17) . . ?
S2 Ag19 Ag16 88.54(4) . . ?

S28 Ag19 Ag16 152.63(3) 4_546 . ?
S17 Ag19 Ag16 92.04(3) . . ?
S19 Ag19 Ag16 59.23(3) . . ?
Ag24 Ag19 Ag16 58.686(16) . . ?
Fe1 Ag19 Ag16 97.734(17) . . ?
S18 Ag20 S18 166.26(6) . 2_556 ?
S18 Ag20 Ag34 83.13(3) . . ?
S18 Ag20 Ag34 83.13(3) 2_556 . ?
S18 Ag20 Ag27 61.09(3) . 1_565 ?
S18 Ag20 Ag27 132.41(3) 2_556 1_565 ?
Ag34 Ag20 Ag27 142.949(12) . 1_565 ?
S18 Ag20 Ag27 132.41(3) . 2_566 ?
S18 Ag20 Ag27 61.09(3) 2_556 2_566 ?
Ag34 Ag20 Ag27 142.949(12) . 2_566 ?
Ag27 Ag20 Ag27 74.10(2) 1_565 2_566 ?
S18 Ag20 Ag15 66.63(3) . . ?
S18 Ag20 Ag15 111.41(3) 2_556 . ?
Ag34 Ag20 Ag15 82.387(14) . . ?
Ag27 Ag20 Ag15 91.193(14) 1_565 . ?
Ag27 Ag20 Ag15 100.990(15) 2_566 . ?
S18 Ag20 Ag15 111.41(3) . 2_556 ?
S18 Ag20 Ag15 66.63(3) 2_556 2_556 ?
Ag34 Ag20 Ag15 82.387(14) . 2_556 ?
Ag27 Ag20 Ag15 100.990(15) 1_565 2_556 ?
Ag27 Ag20 Ag15 91.193(14) 2_566 2_556 ?
Ag15 Ag20 Ag15 164.77(3) . 2_556 ?
S13 Ag21 S26 98.35(3) . . ?
S13 Ag21 S29 102.16(4) . 2_556 ?
S26 Ag21 S29 100.85(4) . 2_556 ?
S13 Ag21 Ag26 95.42(3) . . ?
S26 Ag21 Ag26 96.38(3) . . ?
S29 Ag21 Ag26 153.20(3) 2_556 . ?
S13 Ag21 Fe1 160.04(3) . . ?
S26 Ag21 Fe1 69.38(3) . . ?
S29 Ag21 Fe1 66.42(2) 2_556 . ?
Ag26 Ag21 Fe1 101.433(15) . . ?
S13 Ag21 Ag13 92.11(3) . . ?
S26 Ag21 Ag13 160.30(3) . . ?
S29 Ag21 Ag13 93.14(2) 2_556 . ?
Ag26 Ag21 Ag13 65.893(15) . . ?
Fe1 Ag21 Ag13 104.452(15) . . ?
S26 Ag22 S27 168.42(5) . . ?
S26 Ag22 S19 93.29(4) . . ?
S27 Ag22 S19 97.20(4) . . ?
S26 Ag22 Ag29 76.97(3) . . ?
S27 Ag22 Ag29 95.57(3) . . ?
S19 Ag22 Ag29 104.58(3) . . ?
S26 Ag22 Ag31 109.48(3) . . ?
S27 Ag22 Ag31 64.26(3) . . ?
S19 Ag22 Ag31 142.50(3) . . ?
Ag29 Ag22 Ag31 109.267(18) . . ?
S4 Ag23 S30 98.61(4) . . ?
S4 Ag23 S31 153.23(4) . . ?
S30 Ag23 S31 100.07(3) . . ?
S4 Ag23 S25 103.36(4) . 2_556 ?
S30 Ag23 S25 98.48(4) . 2_556 ?
S31 Ag23 S25 92.68(4) . 2_556 ?
S4 Ag23 Ag18 95.59(4) . . ?
S30 Ag23 Ag18 98.90(3) . . ?
S31 Ag23 Ag18 62.68(3) . . ?
S25 Ag23 Ag18 151.96(3) 2_556 . ?

S4 Ag23 Ag17 96.29(3) . . ?
S30 Ag23 Ag17 158.84(3) . . ?
S31 Ag23 Ag17 61.24(2) . . ?
S25 Ag23 Ag17 92.58(3) 2_556 . ?
Ag18 Ag23 Ag17 64.627(16) . . ?
S4 Ag23 Fe2 159.18(3) . . ?
S30 Ag23 Fe2 64.00(3) . . ?
S31 Ag23 Fe2 47.20(2) . . ?
S25 Ag23 Fe2 70.14(3) 2_556 . ?
Ag18 Ag23 Fe2 98.311(16) . . ?
Ag17 Ag23 Fe2 103.645(16) . . ?
S22 Ag24 S10 109.10(4) . . ?
S22 Ag24 S27 100.17(4) . . ?
S10 Ag24 S27 102.70(4) . . ?
S22 Ag24 S19 93.47(3) . . ?
S10 Ag24 S19 149.39(4) . . ?
S27 Ag24 S19 92.97(4) . . ?
S22 Ag24 Ag19 148.46(3) . . ?
S10 Ag24 Ag19 95.54(3) . . ?
S27 Ag24 Ag19 92.99(3) . . ?
S19 Ag24 Ag19 57.08(2) . . ?
S22 Ag24 Ag16 94.13(3) . . ?
S10 Ag24 Ag16 96.84(4) . . ?
S27 Ag24 Ag16 150.35(3) . . ?
S19 Ag24 Ag16 60.14(3) . . ?
Ag19 Ag24 Ag16 62.826(17) . . ?
S16 Ag25 S30 162.26(5) . . ?
S16 Ag25 S18 106.29(5) . . ?
S30 Ag25 S18 85.61(4) . . ?
S16 Ag25 S20 86.42(3) . 1_565 ?
S30 Ag25 S20 103.00(3) . 1_565 ?
S18 Ag25 S20 106.70(3) . 1_565 ?
S16 Ag25 Ag31 62.89(3) . 4_556 ?
S30 Ag25 Ag31 112.85(4) . 4_556 ?
S18 Ag25 Ag31 149.34(3) . 4_556 ?
S20 Ag25 Ag31 47.00(3) 1_565 4_556 ?
S16 Ag25 Ag29 89.84(3) . 4_556 ?
S30 Ag25 Ag29 74.02(3) . 4_556 ?
S18 Ag25 Ag29 105.88(3) . 4_556 ?
S20 Ag25 Ag29 146.94(3) 1_565 4_556 ?
Ag31 Ag25 Ag29 102.791(18) 4_556 4_556 ?
S16 Ag25 Fe2 115.05(3) . . ?
S30 Ag25 Fe2 63.84(3) . . ?
S18 Ag25 Fe2 45.99(3) . . ?
S20 Ag25 Fe2 147.68(3) 1_565 . ?
Ag31 Ag25 Fe2 164.15(2) 4_556 . ?
Ag29 Ag25 Fe2 61.387(13) 4_556 . ?
S16 Ag25 Ag27 101.31(4) . 1_565 ?
S30 Ag25 Ag27 96.33(3) . 1_565 ?
S18 Ag25 Ag27 53.98(3) . 1_565 ?
S20 Ag25 Ag27 52.72(3) 1_565 1_565 ?
Ag31 Ag25 Ag27 98.197(16) 4_556 1_565 ?
Ag29 Ag25 Ag27 158.944(18) 4_556 1_565 ?
Fe2 Ag25 Ag27 97.594(16) . 1_565 ?
S11 Ag26 S21 107.60(4) . 4_546 ?
S11 Ag26 S27 102.98(4) . 4_546 ?
S21 Ag26 S27 103.21(3) 4_546 4_546 ?
S11 Ag26 Ag21 96.54(3) . . ?
S21 Ag26 Ag21 96.32(4) 4_546 . ?
S27 Ag26 Ag21 146.51(3) 4_546 . ?
S11 Ag26 Ag31 163.10(3) . 4_546 ?

S21 Ag26 Ag31 75.31(3) 4_546 4_546 ?
S27 Ag26 Ag31 60.48(2) 4_546 4_546 ?
Ag21 Ag26 Ag31 99.698(17) . 4_546 ?
S11 Ag26 Ag13 86.93(3) . . ?
S21 Ag26 Ag13 153.91(4) 4_546 . ?
S27 Ag26 Ag13 94.07(3) 4_546 . ?
Ag21 Ag26 Ag13 59.805(14) . . ?
Ag31 Ag26 Ag13 97.170(17) 4_546 . ?
S17 Ag27 S23 166.26(5) . . ?
S17 Ag27 S20 89.16(4) . . ?
S23 Ag27 S20 102.06(5) . . ?
S17 Ag27 S18 98.39(3) . 1_545 ?
S23 Ag27 S18 87.08(4) . 1_545 ?
S20 Ag27 S18 102.17(4) . 1_545 ?
S17 Ag27 Ag20 108.11(3) . 1_545 ?
S23 Ag27 Ag20 66.66(4) . 1_545 ?
S20 Ag27 Ag20 145.50(3) . 1_545 ?
S18 Ag27 Ag20 47.03(3) 1_545 1_545 ?
S17 Ag27 Fe1 69.69(3) . . ?
S23 Ag27 Fe1 112.81(3) . . ?
S20 Ag27 Fe1 45.40(2) . . ?
S18 Ag27 Fe1 143.39(3) 1_545 . ?
Ag20 Ag27 Fe1 168.86(2) 1_545 . ?
S17 Ag27 Ag32 73.90(3) . . ?
S23 Ag27 Ag32 95.50(3) . . ?
S20 Ag27 Ag32 103.79(2) . . ?
S18 Ag27 Ag32 152.73(3) 1_545 . ?
Ag20 Ag27 Ag32 109.553(17) 1_545 . ?
Fe1 Ag27 Ag32 59.315(12) . . ?
S17 Ag27 Ag25 96.91(3) . 1_545 ?
S23 Ag27 Ag25 96.29(4) . 1_545 ?
S20 Ag27 Ag25 51.51(2) . 1_545 ?
S18 Ag27 Ag25 50.67(3) 1_545 1_545 ?
Ag20 Ag27 Ag25 95.905(16) 1_545 1_545 ?
Fe1 Ag27 Ag25 95.208(16) . 1_545 ?
Ag32 Ag27 Ag25 154.474(16) . 1_545 ?
S17 Ag28 S8 110.43(4) 1_565 . ?
S17 Ag28 S16 102.04(5) 1_565 . ?
S8 Ag28 S16 107.45(4) . . ?
S17 Ag28 Ag15 91.90(3) 1_565 . ?
S8 Ag28 Ag15 98.48(4) . . ?
S16 Ag28 Ag15 143.67(3) . . ?
S17 Ag28 Ag14 144.55(3) 1_565 . ?
S8 Ag28 Ag14 94.39(3) . . ?
S16 Ag28 Ag14 93.69(3) . . ?
Ag15 Ag28 Ag14 58.700(16) . . ?
S28 Ag29 S21 165.73(5) 4_546 4_546 ?
S28 Ag29 Ag31 83.57(3) 4_546 4_546 ?
S21 Ag29 Ag31 82.50(3) 4_546 4_546 ?
S28 Ag29 Ag22 83.18(3) 4_546 . ?
S21 Ag29 Ag22 110.28(3) 4_546 . ?
Ag31 Ag29 Ag22 146.086(17) 4_546 . ?
S28 Ag29 Ag25 107.36(3) 4_546 4_546 ?
S21 Ag29 Ag25 81.78(3) 4_546 4_546 ?
Ag31 Ag29 Ag25 140.256(17) 4_546 4_546 ?
Ag22 Ag29 Ag25 73.630(19) . 4_546 ?
S28 Ag29 Hg2 108.50(3) 4_546 4_546 ?
S21 Ag29 Hg2 66.18(3) 4_546 4_546 ?
Ag31 Ag29 Hg2 80.829(13) 4_546 4_546 ?
Ag22 Ag29 Hg2 133.045(18) . 4_546 ?
Ag25 Ag29 Hg2 59.428(12) 4_546 4_546 ?

S19 Ag30 S19 140.57(6) . 2_556 ?
S19 Ag30 Ag33 69.65(3) . . ?
S19 Ag30 Ag33 147.58(3) 2_556 . ?
S19 Ag30 Ag33 147.58(3) . 2_556 ?
S19 Ag30 Ag33 69.65(3) 2_556 2_556 ?
Ag33 Ag30 Ag33 85.28(3) . 2_556 ?
S19 Ag30 S24 96.39(4) . 2_556 ?
S19 Ag30 S24 99.87(4) 2_556 2_556 ?
Ag33 Ag30 S24 56.83(2) . 2_556 ?
Ag33 Ag30 S24 86.01(3) 2_556 2_556 ?
S19 Ag30 S24 99.87(4) . . ?
S19 Ag30 S24 96.39(4) 2_556 . ?
Ag33 Ag30 S24 86.01(3) . . ?
Ag33 Ag30 S24 56.83(2) 2_556 . ?
S24 Ag30 S24 130.44(5) 2_556 . ?
S19 Ag30 Ag32 70.29(3) . . ?
S19 Ag30 Ag32 70.29(3) 2_556 . ?
Ag33 Ag30 Ag32 137.362(13) . . ?
Ag33 Ag30 Ag32 137.362(13) 2_556 . ?
S24 Ag30 Ag32 114.78(3) 2_556 . ?
S24 Ag30 Ag32 114.78(3) . . ?
S19 Ag30 Ag16 59.23(3) . . ?
S19 Ag30 Ag16 109.71(3) 2_556 . ?
Ag33 Ag30 Ag16 96.344(13) . . ?
Ag33 Ag30 Ag16 105.648(14) 2_556 . ?
S24 Ag30 Ag16 150.36(3) 2_556 . ?
S24 Ag30 Ag16 49.27(2) . . ?
Ag32 Ag30 Ag16 75.023(12) . . ?
S19 Ag30 Ag16 109.71(3) . 2_556 ?
S19 Ag30 Ag16 59.23(3) 2_556 2_556 ?
Ag33 Ag30 Ag16 105.648(14) . 2_556 ?
Ag33 Ag30 Ag16 96.344(13) 2_556 2_556 ?
S24 Ag30 Ag16 49.27(2) 2_556 2_556 ?
S24 Ag30 Ag16 150.36(3) . 2_556 ?
Ag32 Ag30 Ag16 75.023(12) . 2_556 ?
Ag16 Ag30 Ag16 150.05(2) . 2_556 ?
S20 Ag31 S31 162.69(4) 4_556 . ?
S20 Ag31 Ag29 80.88(3) 4_556 4_556 ?
S31 Ag31 Ag29 83.97(2) . 4_556 ?
S20 Ag31 S16 84.58(4) 4_556 4_546 ?
S31 Ag31 S16 97.36(3) . 4_546 ?
Ag29 Ag31 S16 124.78(3) 4_556 4_546 ?
S20 Ag31 S27 102.51(3) 4_556 . ?
S31 Ag31 S27 92.78(3) . . ?
Ag29 Ag31 S27 123.28(2) 4_556 . ?
S16 Ag31 S27 111.83(4) 4_546 . ?
S20 Ag31 Ag22 130.79(3) 4_556 . ?
S31 Ag31 Ag22 65.83(2) . . ?
Ag29 Ag31 Ag22 146.855(18) 4_556 . ?
S16 Ag31 Ag22 74.76(3) 4_546 . ?
S27 Ag31 Ag22 49.57(2) . . ?
S20 Ag31 Ag25 58.84(3) 4_556 4_546 ?
S31 Ag31 Ag25 133.95(3) . 4_546 ?
Ag29 Ag31 Ag25 138.789(17) 4_556 4_546 ?
S16 Ag31 Ag25 48.89(2) 4_546 4_546 ?
S27 Ag31 Ag25 77.47(3) . 4_546 ?
Ag22 Ag31 Ag25 74.31(2) . 4_546 ?
S20 Ag31 Ag18 108.42(3) 4_556 . ?
S31 Ag31 Ag18 61.30(3) . . ?
Ag29 Ag31 Ag18 83.524(14) 4_556 . ?
S16 Ag31 Ag18 51.72(2) 4_546 . ?

S27 Ag31 Ag18 142.08(2) . . ?
Ag22 Ag31 Ag18 92.971(14) . . ?
Ag25 Ag31 Ag18 100.207(16) 4_546 . ?
S20 Ag31 Ag26 67.95(3) 4_556 4_556 ?
S31 Ag31 Ag26 117.70(3) . 4_556 ?
Ag29 Ag31 Ag26 80.625(13) 4_556 4_556 ?
S16 Ag31 Ag26 139.74(3) 4_546 4_556 ?
S27 Ag31 Ag26 51.353(19) . 4_556 ?
Ag22 Ag31 Ag26 100.912(15) . 4_556 ?
Ag25 Ag31 Ag26 91.042(14) 4_546 4_556 ?
Ag18 Ag31 Ag26 164.11(2) . 4_556 ?
S29 Ag32 S29 174.75(6) . 2_556 ?
S29 Ag32 Ag30 92.63(3) . . ?
S29 Ag32 Ag30 92.63(3) 2_556 . ?
S29 Ag32 Hg1 67.93(3) . 2_556 ?
S29 Ag32 Hg1 112.27(3) 2_556 2_556 ?
Ag30 Ag32 Hg1 87.964(13) . 2_556 ?
S29 Ag32 Ag27 99.97(3) . . ?
S29 Ag32 Ag27 75.54(3) 2_556 . ?
Ag30 Ag32 Ag27 146.605(10) . . ?
Hg1 Ag32 Ag27 125.43(2) 2_556 . ?
S29 Ag32 Ag27 75.54(3) . 2_556 ?
S29 Ag32 Ag27 99.97(3) 2_556 2_556 ?
Ag30 Ag32 Ag27 146.605(10) . 2_556 ?
Hg1 Ag32 Ag27 58.642(12) 2_556 2_556 ?
Ag27 Ag32 Ag27 66.79(2) . 2_556 ?
S22 Ag33 S31 101.34(4) . . ?
S22 Ag33 S24 161.46(5) . 2_556 ?
S31 Ag33 S24 95.82(4) . 2_556 ?
S22 Ag33 Ag30 104.60(3) . . ?
S31 Ag33 Ag30 147.42(3) . . ?
S24 Ag33 Ag30 62.23(3) 2_556 . ?
S22 Ag33 Ag34 76.61(3) . . ?
S31 Ag33 Ag34 109.22(3) . . ?
S24 Ag33 Ag34 91.21(3) 2_556 . ?
Ag30 Ag33 Ag34 95.791(17) . . ?
S25 Ag34 S25 160.87(6) . 2_556 ?
S25 Ag34 Ag33 112.39(3) . . ?
S25 Ag34 Ag33 82.40(3) 2_556 . ?
S25 Ag34 Ag33 82.40(3) . 2_556 ?
S25 Ag34 Ag33 112.39(3) 2_556 2_556 ?
Ag33 Ag34 Ag33 83.14(2) . 2_556 ?
S25 Ag34 Ag20 80.43(3) . . ?
S25 Ag34 Ag20 80.43(3) 2_556 . ?
Ag33 Ag34 Ag20 138.429(12) . . ?
Ag33 Ag34 Ag20 138.429(12) 2_556 . ?
S10 As1 S5 98.06(5) . . ?
S10 As1 S2 98.44(7) . . ?
S5 As1 S2 99.12(5) . . ?
S9 As2 S8 102.30(6) . . ?
S9 As2 S1 98.77(5) . . ?
S8 As2 S1 95.06(5) . . ?
S4 As3 S7 98.61(6) . . ?
S4 As3 S3 100.04(5) . . ?
S7 As3 S3 98.26(5) . . ?
S6 As4 S11 101.34(5) . . ?
S6 As4 S13 96.26(6) . . ?
S11 As4 S13 100.71(5) . . ?
S16 As5 S21 101.16(4) . . ?
S16 As5 S26 95.45(5) . 4_556 ?
S21 As5 S26 100.07(5) . 4_556 ?

S22 As6 S24 101.21(5) . . ?
S22 As6 S25 98.87(5) . . ?
S24 As6 S25 99.83(4) . . ?
S17 As7 S23 102.17(6) 2_556 . ?
S17 As7 S29 95.78(5) 2_556 2_556 ?
S23 As7 S29 98.90(4) . 2_556 ?
S28 As8 S27 99.51(4) 4_546 . ?
S28 As8 S30 98.60(5) 4_546 4_546 ?
S27 As8 S30 100.57(5) . 4_546 ?
As2 S1 Ag15 114.51(7) . . ?
As2 S1 Ag5 105.29(5) . 1_565 ?
Ag15 S1 Ag5 120.63(5) . 1_565 ?
As2 S1 Ag3 100.41(4) . 2 ?
Ag15 S1 Ag3 108.35(5) . 2 ?
Ag5 S1 Ag3 105.45(6) 1_565 2 ?
As1 S2 Ag19 118.44(6) . . ?
As1 S2 Ag9 103.63(5) . . ?
Ag19 S2 Ag9 110.28(7) . . ?
As1 S2 Ag6 102.92(7) . . ?
Ag19 S2 Ag6 119.78(6) . . ?
Ag9 S2 Ag6 99.03(5) . . ?
As3 S3 Ag9 104.41(5) . 4_556 ?
As3 S3 Ag18 113.68(7) . . ?
Ag9 S3 Ag18 103.29(4) 4_556 . ?
As3 S3 Ag10 107.49(4) . . ?
Ag9 S3 Ag10 110.74(6) 4_556 . ?
Ag18 S3 Ag10 116.53(4) . . ?
As3 S4 Ag3 104.66(4) . 1_556 ?
As3 S4 Ag23 110.08(4) . . ?
Ag3 S4 Ag23 110.81(6) 1_556 . ?
As3 S4 Ag11 108.93(6) . . ?
Ag3 S4 Ag11 103.01(4) 1_556 . ?
Ag23 S4 Ag11 118.33(4) . . ?
As1 S5 Ag16 114.95(7) . . ?
As1 S5 Ag4 108.29(4) . . ?
Ag16 S5 Ag4 113.78(4) . . ?
As1 S5 Ag7 107.61(4) . 2_556 ?
Ag16 S5 Ag7 102.84(4) . 2_556 ?
Ag4 S5 Ag7 108.96(6) . 2_556 ?
As4 S6 Ag5 116.49(5) . 2_556 ?
As4 S6 Ag13 113.62(5) . . ?
Ag5 S6 Ag13 105.91(6) 2_556 . ?
As4 S6 Ag11 102.64(7) . 1_545 ?
Ag5 S6 Ag11 118.21(5) 2_556 1_545 ?
Ag13 S6 Ag11 98.88(4) . 1_545 ?
As3 S7 Ag17 114.07(5) . . ?
As3 S7 Ag8 100.49(6) . . ?
Ag17 S7 Ag8 103.36(4) . . ?
As3 S7 Ag4 109.75(5) . 2_556 ?
Ag17 S7 Ag4 114.89(7) . 2_556 ?
Ag8 S7 Ag4 113.27(4) . 2_556 ?
As2 S8 Ag6 107.58(6) . 1_565 ?
As2 S8 Ag28 109.11(4) . . ?
Ag6 S8 Ag28 105.76(4) 1_565 . ?
As2 S8 Ag10 107.03(4) . 4_556 ?
Ag6 S8 Ag10 118.97(4) 1_565 4_556 ?
Ag28 S8 Ag10 108.14(5) . 4_556 ?
As2 S9 Ag14 117.08(6) . . ?
As2 S9 Ag12 100.60(5) . . ?
Ag14 S9 Ag12 107.89(6) . . ?
As2 S9 Ag2 109.79(6) . . ?

Ag14 S9 Ag2 117.22(5) . . ?
Ag12 S9 Ag2 101.65(5) . . ?
As1 S10 Ag2 104.02(7) . . ?
As1 S10 Ag1 110.29(5) . 4_546 ?
Ag2 S10 Ag1 113.94(5) . 4_546 ?
As1 S10 Ag24 109.01(5) . . ?
Ag2 S10 Ag24 105.52(5) . . ?
Ag1 S10 Ag24 113.49(7) 4_546 . ?
As4 S11 Ag26 116.48(7) . . ?
As4 S11 Ag1 103.83(4) . 1_545 ?
Ag26 S11 Ag1 116.74(4) . 1_545 ?
As4 S11 Ag12 104.64(4) . 4_546 ?
Ag26 S11 Ag12 106.55(4) . 4_546 ?
Ag1 S11 Ag12 107.74(6) 1_545 4_546 ?
Ag9 S12 Ag11 102.46(4) 4 1_554 ?
Ag9 S12 Ag12 105.73(6) 4 . ?
Ag11 S12 Ag12 91.02(4) 1_554 . ?
Ag9 S12 Ag1 96.01(3) 4 1_554 ?
Ag11 S12 Ag1 73.75(4) 1_554 1_554 ?
Ag12 S12 Ag1 155.81(6) . 1_554 ?
Ag9 S12 Ag10 173.10(6) 4 4_556 ?
Ag11 S12 Ag10 77.95(4) 1_554 4_556 ?
Ag12 S12 Ag10 81.12(3) . 4_556 ?
Ag1 S12 Ag10 77.43(4) 1_554 4_556 ?
Ag9 S12 Ag8 99.71(5) 4 4_556 ?
Ag11 S12 Ag8 147.96(6) 1_554 4_556 ?
Ag12 S12 Ag8 104.93(4) . 4_556 ?
Ag1 S12 Ag8 81.20(4) 1_554 4_556 ?
Ag10 S12 Ag8 77.34(4) 4_556 4_556 ?
As4 S13 Ag7 108.16(4) . . ?
As4 S13 Ag21 112.34(4) . . ?
Ag7 S13 Ag21 114.95(6) . . ?
As4 S13 Ag8 106.62(6) . . ?
Ag7 S13 Ag8 95.95(4) . . ?
Ag21 S13 Ag8 117.33(4) . . ?
Ag4 S14 Ag4 78.64(4) 2 . ?
Ag4 S14 Ag3 90.761(14) 2 . ?
Ag4 S14 Ag3 166.14(4) . . ?
Ag4 S14 Ag3 166.14(4) 2 2 ?
Ag4 S14 Ag3 90.761(14) . 2 ?
Ag3 S14 Ag3 101.00(5) . 2 ?
Ag4 S14 Ag2 81.02(3) 2 . ?
Ag4 S14 Ag2 74.48(3) . . ?
Ag3 S14 Ag2 95.21(2) . . ?
Ag3 S14 Ag2 104.92(2) 2 . ?
Ag4 S14 Ag2 74.48(3) 2 2 ?
Ag4 S14 Ag2 81.02(3) . 2 ?
Ag3 S14 Ag2 104.92(2) . 2 ?
Ag3 S14 Ag2 95.21(2) 2 2 ?
Ag2 S14 Ag2 148.23(6) . 2 ?
Ag7 S15 Ag7 101.92(6) 1_554 2_556 ?
Ag7 S15 Ag6 103.02(2) 1_554 2 ?
Ag7 S15 Ag6 94.19(2) 2_556 2 ?
Ag7 S15 Ag6 94.19(2) 1_554 . ?
Ag7 S15 Ag6 103.02(2) 2_556 . ?
Ag6 S15 Ag6 152.60(8) 2 . ?
Ag7 S15 Ag5 89.588(14) 1_554 2 ?
Ag7 S15 Ag5 167.43(5) 2_556 2 ?
Ag6 S15 Ag5 78.13(4) 2 2 ?
Ag6 S15 Ag5 80.87(4) . 2 ?
Ag7 S15 Ag5 167.43(5) 1_554 . ?

Ag7 S15 Ag5 89.588(14) 2_556 . ?
Ag6 S15 Ag5 80.87(4) 2 . ?
Ag6 S15 Ag5 78.13(4) . . ?
Ag5 S15 Ag5 79.45(5) 2 . ?
As5 S16 Ag25 112.88(5) . . ?
As5 S16 Ag18 102.19(4) . 4_556 ?
Ag25 S16 Ag18 135.56(5) . 4_556 ?
As5 S16 Ag28 98.01(5) . . ?
Ag25 S16 Ag28 87.26(4) . . ?
Ag18 S16 Ag28 114.65(5) 4_556 . ?
As5 S16 Ag31 131.80(7) . 4_556 ?
Ag25 S16 Ag31 68.22(3) . 4_556 ?
Ag18 S16 Ag31 68.18(3) 4_556 4_556 ?
Ag28 S16 Ag31 129.51(5) . 4_556 ?
As7 S17 Ag27 113.46(5) 2_556 . ?
As7 S17 Ag28 103.23(5) 2_556 1_545 ?
Ag27 S17 Ag28 93.19(4) . 1_545 ?
As7 S17 Ag19 104.93(5) 2_556 . ?
Ag27 S17 Ag19 124.73(5) . . ?
Ag28 S17 Ag19 115.38(4) 1_545 . ?
Fe2 S18 Ag20 121.99(4) . . ?
Fe2 S18 Ag25 78.23(4) . . ?
Ag20 S18 Ag25 142.21(4) . . ?
Fe2 S18 Ag27 145.98(6) . 1_565 ?
Ag20 S18 Ag27 71.88(3) . 1_565 ?
Ag25 S18 Ag27 75.35(3) . 1_565 ?
Fe1 S19 Ag30 123.20(4) . . ?
Fe1 S19 Ag19 71.86(3) . . ?
Ag30 S19 Ag19 137.84(6) . . ?
Fe1 S19 Ag24 126.02(5) . . ?
Ag30 S19 Ag24 110.31(5) . . ?
Ag19 S19 Ag24 63.75(2) . . ?
Fe1 S19 Ag22 76.66(4) . . ?
Ag30 S19 Ag22 125.57(4) . . ?
Ag19 S19 Ag22 95.20(4) . . ?
Ag24 S19 Ag22 78.34(3) . . ?
Fe1 S19 Ag16 123.80(5) . . ?
Ag30 S19 Ag16 74.72(4) . . ?
Ag19 S19 Ag16 65.85(3) . . ?
Ag24 S19 Ag16 62.19(3) . . ?
Ag22 S19 Ag16 140.42(4) . . ?
Ag31 S20 Fe1 122.45(4) 4_546 . ?
Ag31 S20 Ag25 74.16(3) 4_546 1_545 ?
Fe1 S20 Ag25 147.80(5) . 1_545 ?
Ag31 S20 Ag27 145.40(4) 4_546 . ?
Fe1 S20 Ag27 77.92(4) . . ?
Ag25 S20 Ag27 75.77(3) 1_545 . ?
As5 S21 Ag26 105.06(5) . 4_556 ?
As5 S21 Ag29 98.01(5) . 4_556 ?
Ag26 S21 Ag29 98.70(5) 4_556 4_556 ?
As5 S21 Ag14 102.33(5) . . ?
Ag26 S21 Ag14 119.28(5) 4_556 . ?
Ag29 S21 Ag14 129.45(4) 4_556 . ?
As6 S22 Ag33 115.56(4) . . ?
As6 S22 Ag24 101.96(4) . . ?
Ag33 S22 Ag24 92.08(4) . . ?
As6 S22 Ag14 103.46(4) . . ?
Ag33 S22 Ag14 124.19(5) . . ?
Ag24 S22 Ag14 117.85(4) . . ?
As7 S23 Ag13 104.74(6) . . ?
As7 S23 Ag27 108.96(5) . . ?

Ag13 S23 Ag27 94.50(5) . . ?
As7 S23 Ag15 100.64(5) . 2_546 ?
Ag13 S23 Ag15 118.50(6) . 2_546 ?
Ag27 S23 Ag15 127.80(6) . 2_546 ?
As6 S24 Ag17 103.38(6) . 2_556 ?
As6 S24 Ag16 102.00(4) . . ?
Ag17 S24 Ag16 116.88(5) 2_556 . ?
As6 S24 Ag33 107.99(5) . 2_556 ?
Ag17 S24 Ag33 87.47(4) 2_556 2_556 ?
Ag16 S24 Ag33 135.45(5) . 2_556 ?
As6 S24 Ag30 122.38(7) . . ?
Ag17 S24 Ag30 129.71(4) 2_556 . ?
Ag16 S24 Ag30 75.33(4) . . ?
Ag33 S24 Ag30 60.94(3) 2_556 . ?
As6 S25 Ag34 97.69(5) . . ?
As6 S25 Ag15 104.61(4) . . ?
Ag34 S25 Ag15 99.87(5) . . ?
As6 S25 Ag23 102.97(5) . 2_556 ?
Ag34 S25 Ag23 127.43(4) . 2_556 ?
Ag15 S25 Ag23 120.12(5) . 2_556 ?
As5 S26 Ag22 111.73(5) 4_546 . ?
As5 S26 Ag17 103.21(5) 4_546 . ?
Ag22 S26 Ag17 97.24(4) . . ?
As5 S26 Ag21 99.06(4) 4_546 . ?
Ag22 S26 Ag21 125.92(5) . . ?
Ag17 S26 Ag21 118.13(4) . . ?
As8 S27 Ag22 109.04(4) . . ?
As8 S27 Ag26 101.00(4) . 4_556 ?
Ag22 S27 Ag26 134.31(5) . 4_556 ?
As8 S27 Ag24 99.36(4) . . ?
Ag22 S27 Ag24 89.32(4) . . ?
Ag26 S27 Ag24 119.20(4) 4_556 . ?
As8 S27 Ag31 129.97(6) . . ?
Ag22 S27 Ag31 66.16(3) . . ?
Ag26 S27 Ag31 68.17(3) 4_556 . ?
Ag24 S27 Ag31 129.21(4) . . ?
As8 S28 Ag29 101.73(6) 4_556 4_556 ?
As8 S28 Ag19 104.82(6) 4_556 4_556 ?
Ag29 S28 Ag19 124.06(4) 4_556 4_556 ?
As8 S28 Ag18 105.95(5) 4_556 . ?
Ag29 S28 Ag18 100.29(5) 4_556 . ?
Ag19 S28 Ag18 117.81(5) 4_556 . ?
As7 S29 Ag32 112.13(5) 2_556 . ?
As7 S29 Ag16 102.58(4) 2_556 . ?
Ag32 S29 Ag16 98.20(5) . . ?
As7 S29 Ag21 98.56(4) 2_556 2_556 ?
Ag32 S29 Ag21 128.48(4) . 2_556 ?
Ag16 S29 Ag21 114.73(4) . 2_556 ?
As8 S30 Ag25 108.52(5) 4_556 . ?
As8 S30 Ag13 98.98(5) 4_556 1_565 ?
Ag25 S30 Ag13 93.16(4) . 1_565 ?
As8 S30 Ag23 98.98(5) 4_556 . ?
Ag25 S30 Ag23 133.12(5) . . ?
Ag13 S30 Ag23 119.59(4) 1_565 . ?
Fe2 S31 Ag31 107.35(3) . . ?
Fe2 S31 Ag33 81.56(4) . . ?
Ag31 S31 Ag33 129.65(3) . . ?
Fe2 S31 Ag23 76.51(3) . . ?
Ag31 S31 Ag23 125.76(4) . . ?
Ag33 S31 Ag23 104.58(3) . . ?
Fe2 S31 Ag18 120.04(4) . . ?

Ag31 S31 Ag18 69.89(3) . . ?
Ag33 S31 Ag18 147.89(3) . . ?
Ag23 S31 Ag18 63.00(2) . . ?
Fe2 S31 Ag17 133.02(4) . . ?
Ag31 S31 Ag17 117.13(4) . . ?
Ag33 S31 Ag17 81.58(3) . . ?
Ag23 S31 Ag17 65.99(2) . . ?
Ag18 S31 Ag17 66.31(2) . . ?

_diffrn_measured_fraction_theta_max 0.650
_diffrn_reflns_theta_full 34.84
_diffrn_measured_fraction_theta_full 0.650
_refine_diff_density_max 1.130
_refine_diff_density_min -1.396
_refine_diff_density_rms 0.168

```

data_R110042

_audit_creation_method           JANA2006
_chemical_name_systematic
;
?
;
_chemical_name_common            ?
_chemical_melting_point          ?
_chemical_formula_moiety         ?
_chemical_formula_sum
'Ag16 As4 Cu0 Hg S15'
_chemical_formula_weight          2707.09

loop_
_atom_type_symbol
_atom_type_description
_atom_type_scat_dispersion_real
_atom_type_scat_dispersion_imag
_atom_type_scat_source
'Ag'   'Ag'   -0.8971   1.1015
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'S'    'S'    0.1246   0.1234
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'As'   'As'   0.0499   2.0058
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Hg'   'Hg'   -2.3894   9.2266
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Cu'   'Cu'   0.3201   1.2651
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

_symmetry_cell_setting          ?
_symmetry_space_group_name_H-M   ?

loop_
_symmetry_equiv_pos_as_xyz
'x, y, z'
'-x, y, -z'
'x+1/2, y+1/2, z'
'-x+1/2, y+1/2, -z'

_cell_length_a                  26.030(2)
_cell_length_b                  15.0590(10)
_cell_length_c                  15.5240(10)
_cell_angle_alpha                90.00
_cell_angle_beta                 90.450(10)
_cell_angle_gamma                90.00
_cell_volume                     6085.0(7)
_cell_formula_units_Z            8
_cell_measurement_temperature    293(2)
_cell_measurement_reflns_used    ?
_cell_measurement_theta_min      ?
_cell_measurement_theta_max      ?

_exptl_crystal_description      ?
_exptl_crystal_colour           ?
_exptl_crystal_size_max          ?
_exptl_crystal_size_mid          ?
_exptl_crystal_size_min          ?

```

```

_exptl_crystal_density_meas      ?
_exptl_crystal_density_diffrn   5.910
_exptl_crystal_density_method    'not measured'
_exptl_crystal_F_000             9632
_exptl_absorpt_coefficient_mu   20.407
_exptl_absorpt_correction_type   ?
_exptl_absorpt_correction_T_min  ?
_exptl_absorpt_correction_T_max  ?
_exptl_absorpt_process_details   ?

_exptl_special_details
;
?
;

_diffrn_ambient_temperature      293(2)
_diffrn_radiation_wavelength     0.71069
_diffrn_radiation_type           MoK\alpha
_diffrn_radiation_source         'fine-focus sealed tube'
_diffrn_radiation_monochromator   graphite
_diffrn_measurement_device_type   ?
_diffrn_measurement_method        ?
_diffrn_detector_area_resol_mean  ?
_diffrn_standards_number          ?
_diffrn_standards_interval_count  ?
_diffrn_standards_interval_time   ?
_diffrn_standards_decay_%         ?
_diffrn_reflns_number             17368
_diffrn_reflns_av_R_equivalents  0.0000
_diffrn_reflns_av_sigmaI/netI    0.2111
_diffrn_reflns_limit_h_min        -40
_diffrn_reflns_limit_h_max        41
_diffrn_reflns_limit_k_min        -23
_diffrn_reflns_limit_k_max        23
_diffrn_reflns_limit_l_min        0
_diffrn_reflns_limit_l_max        24
_diffrn_reflns_theta_min          3.77
_diffrn_reflns_theta_max          34.79
_reflns_number_total              17368
_reflns_number_gt                7445
_reflns_threshold_expression      >2sigma(I)

_computing_data_collection        ?
_computing_cell_refinement        ?
_computing_data_reduction         ?
_computing_structure_solution     ?
_computing_structure_refinement   'SHELXL-97 (Sheldrick, 1997)'
_computing_molecular_graphics     ?
_computing_publication_material   ?

_refine_special_details
;
Refinement of F^2^ against ALL reflections. The weighted R-factor wR and
goodness of fit S are based on F^2^, conventional R-factors R are based
on F, with F set to zero for negative F^2^. The threshold expression of
F^2^ > 2sigma(F^2^) is used only for calculating R-factors(gt) etc. and is
not relevant to the choice of reflections for refinement. R-factors based
on F^2^ are statistically about twice as large as those based on F, and R-
factors based on ALL data will be even larger.
;
```

```

_refine_ls_structure_factor_coef  Fsqd
_refine_ls_matrix_type          full
_refine_ls_weighting_scheme     calc
_refine_ls_weighting_details
  'calc w=1/[s^2^(Fo^2^)+(0.0224P)^2^+0.0000P] where P=(Fo^2^+2Fc^2^)/3'
_atom_sites_solution_primary    direct
_atom_sites_solution_secondary  difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment   mixed
_refine_ls_extinction_method   none
_refine_ls_extinction_coef     ?
_refine_ls_abs_structure_details
  'Flack H D (1983), Acta Cryst. A39, 876-881'
_refine_ls_abs_structure_Flack  0.0(4)
_refine_ls_number_reflns        17368
_refine_ls_number_parameters   659
_refine_ls_number_restraints   1
_refine_ls_R_factor_all        0.0489
_refine_ls_R_factor_gt         0.0430
_refine_ls_wR_factor_ref       0.0854
_refine_ls_wR_factor_gt        0.0846
_refine_ls_goodness_of_fit_ref 0.566
_refine_ls_restrained_S_all   0.566
_refine_ls_shift/su_max        0.031
_refine_ls_shift/su_mean       0.002

```

loop_

```

_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group

```

Hg1	Hg	0.12317(5)	0.10741(6)	0.50142(7)	0.0259(3)	Uani	0.811(4)	1	d	P	.	.	.
Cu1	Cu	0.12317(5)	0.10741(6)	0.50142(7)	0.0259(3)	Uani	0.189(4)	1	d	P	.	.	.
Hg2	Hg	0.13044(4)	0.61371(6)	0.50032(7)	0.0245(3)	Uani	0.762(4)	1	d	P	.	.	.
Cu2	Cu	0.13044(4)	0.61371(6)	0.50032(7)	0.0245(3)	Uani	0.238(4)	1	d	P	.	.	.
Ag1	Ag	0.27942(7)	0.83547(9)	0.91487(11)	0.0303(4)	Uani	1	1	d
Ag2	Ag	0.07787(7)	0.46518(8)	0.08665(10)	0.0231(4)	Uani	1	1	d
Ag3	Ag	0.04799(6)	0.61918(9)	-0.09576(9)	0.0207(3)	Uani	1	1	d
Ag4	Ag	-0.02886(7)	0.38295(9)	0.08959(11)	0.0276(4)	Uani	1	1	d
Ag5	Ag	-0.03282(7)	-0.11871(9)	0.09015(10)	0.0269(4)	Uani	1	1	d
Ag6	Ag	0.07739(7)	-0.02527(8)	0.08672(11)	0.0240(4)	Uani	1	1	d
Ag7	Ag	0.04706(7)	0.11772(10)	0.90500(11)	0.0304(4)	Uani	1	1	d
Ag8	Ag	0.16718(7)	0.24399(8)	0.91076(10)	0.0240(4)	Uani	1	1	d
Ag9	Ag	0.20512(7)	0.09588(9)	0.09778(11)	0.0301(4)	Uani	1	1	d
Ag10	Ag	0.28159(6)	0.32376(8)	0.91149(10)	0.0234(4)	Uani	1	1	d
Ag11	Ag	0.17838(7)	0.74481(9)	0.91217(11)	0.0287(4)	Uani	1	1	d
Ag12	Ag	0.20066(7)	0.60997(10)	0.09356(11)	0.0330(4)	Uani	1	1	d
Ag13	Ag	0.12931(6)	-0.12908(8)	0.71132(10)	0.0227(3)	Uani	1	1	d
Ag14	Ag	0.11725(6)	0.62574(9)	0.30257(10)	0.0288(4)	Uani	1	1	d
Ag15	Ag	0.01748(7)	0.72701(9)	0.30817(10)	0.0262(4)	Uani	1	1	d
Ag16	Ag	0.01481(7)	0.22641(10)	0.29645(10)	0.0304(4)	Uani	1	1	d
Ag17	Ag	0.13132(6)	0.37339(8)	0.70689(9)	0.0196(3)	Uani	1	1	d

Ag18 Ag 0.23574(7) 0.48206(8) 0.69797(11) 0.0248(4) Uani 1 1 d . . .
 Ag19 Ag 0.12004(6) 0.12922(9) 0.30833(10) 0.0264(4) Uani 1 1 d . . .
 Ag20 Ag 0.0000 0.73161(13) 0.5000 0.0302(5) Uani 1 2 d S . .
 Ag21 Ag 0.13640(6) 0.07349(9) 0.68981(10) 0.0239(3) Uani 1 1 d . . .
 Ag22 Ag 0.18294(6) 0.29352(9) 0.50066(10) 0.0268(4) Uani 1 1 d . . .
 Ag23 Ag 0.13781(7) 0.57552(9) 0.69449(11) 0.0282(4) Uani 1 1 d . . .
 Ag24 Ag 0.11447(6) 0.32572(8) 0.29886(9) 0.0221(3) Uani 1 1 d . . .
 Ag25 Ag 0.17866(6) 0.80057(9) 0.49758(10) 0.0258(4) Uani 1 1 d . . .
 Ag26 Ag 0.23458(7) -0.01717(8) 0.69532(11) 0.0269(4) Uani 1 1 d . . .
 Ag27 Ag 0.06951(6) -0.08579(8) 0.50236(9) 0.0211(3) Uani 1 1 d . . .
 Ag28 Ag 0.11660(7) 0.83255(9) 0.29365(11) 0.0283(4) Uani 1 1 d . . .
 Ag29 Ag 0.24810(6) 0.13996(7) 0.50085(9) 0.0220(3) Uani 1 1 d . . .
 Ag30 Ag 0.0000 0.28735(13) 0.5000 0.0230(5) Uani 1 2 d S . .
 Ag31 Ag 0.24918(7) 0.44863(8) 0.50166(11) 0.0234(3) Uani 1 1 d . . .
 Ag32 Ag 0.0000 0.09451(11) 0.5000 0.0262(5) Uani 1 2 d S . .
 Ag33 Ag 0.07276(6) 0.41872(9) 0.50135(9) 0.0222(4) Uani 1 1 d . . .
 Ag34 Ag 0.0000 0.57624(12) 0.5000 0.0217(5) Uani 1 2 d S . .
 As1 As 0.08490(9) 0.22497(12) 0.07298(13) 0.0233(5) Uani 1 1 d . . .
 As2 As 0.08056(10) 0.72482(12) 0.07406(14) 0.0257(6) Uani 1 1 d . . .
 As3 As 0.16697(9) 0.48559(10) 0.92885(14) 0.0211(6) Uani 1 1 d . . .
 As4 As 0.16915(9) -0.01251(10) 0.92661(14) 0.0194(5) Uani 1 1 d . . .
 As5 As 0.24888(9) 0.73253(11) 0.28503(13) 0.0207(5) Uani 1 1 d . . .
 As6 As 0.00058(9) 0.47155(11) 0.28595(14) 0.0208(5) Uani 1 1 d . . .
 As7 As 0.00114(9) -0.02443(11) 0.71493(14) 0.0209(5) Uani 1 1 d . . .
 As8 As 0.25080(9) 0.23280(11) 0.28486(13) 0.0200(5) Uani 1 1 d . . .
 S1 S 0.0061(2) 0.7417(3) 0.1519(4) 0.0329(14) Uani 1 1 d . . .
 S2 S 0.1173(3) 0.1103(3) 0.1532(4) 0.0393(16) Uani 1 1 d . . .
 S3 S 0.2440(3) 0.4662(3) 0.8581(4) 0.0391(17) Uani 1 1 d . . .
 S4 S 0.1353(2) 0.6030(3) 0.8549(4) 0.0297(13) Uani 1 1 d . . .
 S5 S 0.0105(3) 0.2421(4) 0.1396(4) 0.0418(17) Uani 1 1 d . . .
 S6 S 0.1261(2) -0.1170(3) 0.8736(3) 0.0306(14) Uani 1 1 d . . .
 S7 S 0.1212(2) 0.3769(3) 0.8620(4) 0.0294(13) Uani 1 1 d . . .
 S8 S 0.1228(2) 0.8401(3) 0.1300(4) 0.0351(15) Uani 1 1 d . . .
 S9 S 0.1128(2) 0.6095(3) 0.1467(4) 0.0341(14) Uani 1 1 d . . .
 S10 S 0.1258(3) 0.3348(3) 0.1339(4) 0.0365(15) Uani 1 1 d . . .
 S11 S 0.2417(3) -0.0276(3) 0.8567(4) 0.0416(18) Uani 1 1 d . . .
 S12 S 0.2542(2) 0.7008(3) -0.0032(3) 0.0339(13) Uani 1 1 d . . .
 S13 S 0.1325(3) 0.0953(3) 0.8512(4) 0.0373(15) Uani 1 1 d . . .
 S14 S 0.0000 0.5141(5) 0.0000 0.040(2) Uani 1 2 d S . .
 S15 S 0.0000 0.0140(4) 0.0000 0.0320(18) Uani 1 2 d S . .
 S16 S 0.2133(3) 0.8494(3) 0.3597(4) 0.0384(16) Uani 1 1 d . . .
 S17 S 0.0755(3) -0.0261(3) 0.3536(4) 0.0369(16) Uani 1 1 d . . .
 S18 S 0.0857(2) 0.7403(3) 0.4531(4) 0.0316(14) Uani 1 1 d . . .
 S19 S 0.0828(3) 0.2305(3) 0.4414(4) 0.0376(15) Uani 1 1 d . . .
 S20 S 0.1668(3) -0.0242(3) 0.5465(4) 0.0335(16) Uani 1 1 d . . .
 S21 S 0.2126(2) 0.6145(3) 0.3510(4) 0.0355(14) Uani 1 1 d . . .
 S22 S 0.0742(3) 0.4732(3) 0.3511(4) 0.0372(16) Uani 1 1 d . . .
 S23 S 0.0431(3) -0.1346(3) 0.6504(4) 0.0340(14) Uani 1 1 d . . .
 S24 S -0.0376(3) 0.3610(3) 0.3509(4) 0.0337(15) Uani 1 1 d . . .
 S25 S -0.0358(2) 0.5870(3) 0.3551(4) 0.0305(13) Uani 1 1 d . . .
 S26 S 0.1733(2) 0.2390(3) 0.6447(4) 0.0329(15) Uani 1 1 d . . .
 S27 S 0.2113(3) 0.3491(3) 0.3564(4) 0.0331(15) Uani 1 1 d . . .
 S28 S 0.2857(2) 0.6165(4) 0.6493(4) 0.0364(14) Uani 1 1 d . . .
 S29 S -0.0336(2) 0.0893(3) 0.3612(4) 0.0331(13) Uani 1 1 d . . .
 S30 S 0.1692(3) 0.7296(3) 0.6442(4) 0.0376(15) Uani 1 1 d . . .
 S31 S 0.1605(3) 0.4818(3) 0.5593(4) 0.0326(15) Uani 1 1 d . . .

loop_

 _atom_site_aniso_label

 _atom_site_aniso_U_11

 _atom_site_aniso_U_22

`_atom_site_aniso_U_33`
`_atom_site_aniso_U_23`
`_atom_site_aniso_U_13`
`_atom_site_aniso_U_12`
Hg1 0.0255(5) 0.0257(4) 0.0264(4) 0.0003(3) -0.0002(4) -0.0002(3)
Cu1 0.0255(5) 0.0257(4) 0.0264(4) 0.0003(3) -0.0002(4) -0.0002(3)
Hg2 0.0246(6) 0.0243(4) 0.0247(5) 0.0003(3) 0.0012(4) -0.0005(4)
Cu2 0.0246(6) 0.0243(4) 0.0247(5) 0.0003(3) 0.0012(4) -0.0005(4)
Ag1 0.0296(11) 0.0316(8) 0.0297(9) -0.0004(6) 0.0004(8) 0.0003(7)
Ag2 0.0238(10) 0.0217(6) 0.0240(9) -0.0008(5) 0.0006(7) -0.0020(6)
Ag3 0.0204(9) 0.0208(6) 0.0209(7) -0.0003(5) -0.0003(6) -0.0005(6)
Ag4 0.0268(11) 0.0281(7) 0.0278(9) 0.0004(5) -0.0004(8) -0.0001(7)
Ag5 0.0296(11) 0.0259(7) 0.0252(8) 0.0004(5) 0.0028(8) 0.0006(6)
Ag6 0.0260(11) 0.0221(6) 0.0239(9) -0.0012(5) 0.0014(8) -0.0012(6)
Ag7 0.0304(10) 0.0293(7) 0.0316(9) 0.0013(6) 0.0004(8) 0.0010(7)
Ag8 0.0236(11) 0.0249(7) 0.0235(8) 0.0008(5) -0.0013(7) 0.0022(6)
Ag9 0.0308(11) 0.0302(8) 0.0295(9) 0.0002(5) 0.0028(8) -0.0011(7)
Ag10 0.0239(10) 0.0225(7) 0.0237(8) -0.0008(5) 0.0011(7) -0.0010(6)
Ag11 0.0300(11) 0.0262(7) 0.0298(9) -0.0005(5) -0.0012(8) -0.0026(6)
Ag12 0.0306(10) 0.0355(7) 0.0328(8) 0.0007(6) -0.0004(8) -0.0006(7)
Ag13 0.0241(9) 0.0220(6) 0.0220(7) 0.0000(5) 0.0013(6) 0.0000(6)
Ag14 0.0295(10) 0.0279(7) 0.0289(8) 0.0000(5) -0.0009(7) -0.0008(6)
Ag15 0.0249(10) 0.0271(6) 0.0267(8) 0.0002(5) -0.0025(8) 0.0000(6)
Ag16 0.0287(11) 0.0324(7) 0.0301(9) -0.0007(6) -0.0004(8) -0.0013(7)
Ag17 0.0184(9) 0.0200(6) 0.0204(7) 0.0006(4) -0.0014(6) 0.0004(5)
Ag18 0.0236(11) 0.0252(7) 0.0257(9) -0.0002(5) 0.0013(8) -0.0006(6)
Ag19 0.0286(9) 0.0252(7) 0.0253(8) 0.0000(5) 0.0012(7) 0.0000(6)
Ag20 0.0323(14) 0.0286(10) 0.0296(10) 0.0000 0.0041(10) 0.000
Ag21 0.0224(9) 0.0259(6) 0.0234(8) 0.0007(5) -0.0029(7) 0.0011(6)
Ag22 0.0284(10) 0.0267(6) 0.0253(7) -0.0004(5) -0.0011(7) -0.0004(6)
Ag23 0.0271(10) 0.0296(7) 0.0277(8) 0.0013(5) -0.0018(7) 0.0001(6)
Ag24 0.0230(9) 0.0211(6) 0.0222(7) 0.0010(4) -0.0002(6) 0.0010(5)
Ag25 0.0259(10) 0.0257(7) 0.0258(8) -0.0009(5) 0.0005(7) -0.0004(6)
Ag26 0.0270(12) 0.0263(7) 0.0274(10) -0.0005(5) 0.0007(9) -0.0013(6)
Ag27 0.0232(10) 0.0193(6) 0.0206(7) -0.0006(4) 0.0022(7) -0.0003(6)
Ag28 0.0286(11) 0.0283(7) 0.0281(9) 0.0001(5) -0.0005(8) 0.0015(7)
Ag29 0.0214(9) 0.0210(6) 0.0235(7) -0.0005(5) 0.0014(6) -0.0006(6)
Ag30 0.0242(12) 0.0207(8) 0.0242(9) 0.0000 0.0036(8) 0.000
Ag31 0.0204(7) 0.0252(6) 0.0246(6) -0.0006(5) -0.0023(5) -0.0012(6)
Ag32 0.0255(13) 0.0275(10) 0.0257(10) 0.0000 -0.0003(10) 0.000
Ag33 0.0218(9) 0.0227(6) 0.0221(7) 0.0004(5) 0.0017(7) -0.0005(6)
Ag34 0.0233(14) 0.0200(9) 0.0219(11) 0.0000 0.0011(10) 0.000
As1 0.0220(15) 0.0255(9) 0.0222(10) -0.0004(7) -0.0016(10) 0.0007(9)
As2 0.0254(16) 0.0255(9) 0.0261(11) -0.0010(7) -0.0013(11) -0.0007(9)
As3 0.0219(15) 0.0206(9) 0.0210(12) -0.0004(6) -0.0002(11) -0.0003(8)
As4 0.0198(14) 0.0195(9) 0.0191(11) -0.0007(6) 0.0016(10) -0.0007(7)
As5 0.0209(13) 0.0209(8) 0.0201(10) -0.0016(7) -0.0012(9) -0.0001(8)
As6 0.0193(13) 0.0208(8) 0.0223(12) -0.0002(6) -0.0001(10) -0.0025(8)
As7 0.0203(14) 0.0215(8) 0.0209(12) -0.0014(6) -0.0005(10) 0.0012(8)
As8 0.0188(13) 0.0208(8) 0.0203(10) 0.0000(7) -0.0020(9) -0.0003(8)
S1 0.031(4) 0.035(3) 0.033(3) 0.0012(18) -0.002(3) 0.006(2)
S2 0.037(4) 0.037(3) 0.044(4) 0.001(2) 0.003(3) 0.004(3)
S3 0.040(4) 0.031(3) 0.047(4) -0.003(2) 0.004(3) 0.002(2)
S4 0.028(3) 0.033(2) 0.028(3) -0.0019(17) -0.001(3) -0.004(2)
S5 0.039(5) 0.048(3) 0.039(4) -0.001(2) 0.001(3) 0.005(3)
S6 0.042(4) 0.026(2) 0.024(3) 0.0024(16) 0.001(3) 0.000(2)
S7 0.029(4) 0.027(2) 0.032(3) 0.0018(18) -0.002(3) -0.002(2)
S8 0.035(4) 0.030(2) 0.040(3) -0.0007(19) -0.002(3) 0.003(2)
S9 0.036(4) 0.030(2) 0.037(3) 0.0012(19) 0.001(3) 0.002(2)
S10 0.037(4) 0.036(3) 0.036(3) 0.000(2) -0.003(3) -0.001(2)
S11 0.042(5) 0.042(3) 0.041(4) -0.004(2) 0.000(4) -0.003(3)

```

S12 0.029(4) 0.037(2) 0.036(3) 0.001(2) -0.010(3) 0.002(2)
S13 0.041(4) 0.035(3) 0.036(3) -0.0004(19) -0.002(3) -0.003(2)
S14 0.034(5) 0.029(3) 0.057(6) 0.000 -0.001(4) 0.000
S15 0.024(5) 0.027(3) 0.045(5) 0.000 0.002(4) 0.000
S16 0.049(5) 0.032(2) 0.034(3) 0.0034(19) 0.007(3) 0.004(2)
S17 0.028(4) 0.041(3) 0.042(4) 0.003(2) -0.001(3) 0.004(2)
S18 0.029(4) 0.032(2) 0.033(3) -0.0021(18) 0.005(3) 0.002(2)
S19 0.034(4) 0.046(3) 0.033(3) -0.003(2) 0.003(3) -0.004(2)
S20 0.037(4) 0.034(2) 0.030(3) 0.0056(18) 0.006(3) -0.002(2)
S21 0.047(4) 0.025(2) 0.034(3) -0.0003(19) 0.002(3) 0.002(2)
S22 0.027(4) 0.046(3) 0.039(4) 0.007(2) -0.003(3) 0.007(2)
S23 0.039(4) 0.029(2) 0.034(3) 0.0011(18) 0.001(3) 0.004(2)
S24 0.041(4) 0.035(2) 0.026(3) -0.0015(18) 0.002(3) 0.001(2)
S25 0.030(3) 0.024(2) 0.038(3) 0.0023(18) 0.001(3) 0.004(2)
S26 0.034(4) 0.030(2) 0.035(3) -0.0001(18) 0.004(3) -0.003(2)
S27 0.038(4) 0.026(2) 0.035(3) 0.0002(18) 0.004(3) -0.001(2)
S28 0.039(4) 0.038(2) 0.032(3) -0.003(2) -0.003(3) -0.006(3)
S29 0.023(3) 0.035(2) 0.041(3) 0.0031(19) -0.004(3) 0.005(2)
S30 0.042(4) 0.036(2) 0.034(3) 0.002(2) 0.001(3) -0.004(2)
S31 0.037(4) 0.031(2) 0.031(3) -0.0014(17) 0.008(3) -0.004(2)

```

_geom_special_details

;

All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

;

loop_

_geom_bond_atom_site_label_1
_geom_bond_atom_site_label_2
_geom_bond_distance
_geom_bond_site_symmetry_2
_geom_bond_publ_flag

Hg1 S19 2.323(6) . ?
Hg1 S20 2.386(6) . ?
Hg1 Ag21 2.986(2) . ?
Hg1 Ag19 3.016(2) . ?
Hg1 Ag22 3.2056(19) . ?
Hg1 Ag32 3.2118(13) . ?
Hg1 Ag27 3.2274(17) . ?
Hg1 Ag29 3.289(2) . ?
Hg2 S31 2.321(5) . ?
Hg2 S18 2.348(6) . ?
Hg2 S30 3.002(6) . ?
Hg2 Ag23 3.073(2) . ?
Hg2 Ag25 3.0816(17) . ?
Hg2 Ag14 3.092(2) . ?
Hg2 Ag29 3.1864(19) 4_556 ?
Hg2 Ag33 3.2981(17) . ?
Ag1 S11 2.453(7) 1_565 ?
Ag1 S12 2.485(5) 1_556 ?
Ag1 S10 2.586(6) 4_556 ?
Ag1 Ag11 2.963(2) . ?
Ag1 Ag10 3.1443(19) 4_557 ?
Ag1 Ag8 3.331(3) 4_557 ?
Ag2 S10 2.436(6) . ?
Ag2 S14 2.533(3) . ?

Ag2 S9 2.531(6) . ?
Ag2 Ag4 3.042(2) . ?
Ag2 Ag4 3.254(3) 2 ?
Ag3 S4 2.417(5) 1_554 ?
Ag3 S1 2.475(6) 2 ?
Ag3 S14 2.511(5) . ?
Ag4 S5 2.477(6) . ?
Ag4 S7 2.525(6) 2_556 ?
Ag4 S14 2.533(6) . ?
Ag4 Ag4 3.172(3) 2 ?
Ag4 Ag2 3.254(3) 2 ?
Ag5 S6 2.498(6) 2_556 ?
Ag5 S1 2.520(5) 1_545 ?
Ag5 S15 2.589(5) . ?
Ag5 Ag6 3.196(2) . ?
Ag5 Ag6 3.289(3) 2 ?
Ag5 Ag5 3.291(3) 2 ?
Ag6 S8 2.439(6) 1_545 ?
Ag6 S15 2.486(3) . ?
Ag6 S2 2.508(6) . ?
Ag6 Ag5 3.289(3) 2 ?
Ag7 S13 2.407(6) . ?
Ag7 S15 2.478(5) 1_556 ?
Ag7 S5 2.493(7) 2_556 ?
Ag8 S7 2.449(5) . ?
Ag8 S12 2.574(6) 4_546 ?
Ag8 S13 2.583(6) . ?
Ag8 Ag10 3.211(2) . ?
Ag8 Ag1 3.331(3) 4_547 ?
Ag9 S12 2.407(5) 4_545 ?
Ag9 S2 2.459(6) . ?
Ag9 S3 2.453(6) 4_546 ?
Ag10 S3 2.497(6) . ?
Ag10 S12 2.520(5) 4_546 ?
Ag10 S8 2.586(6) 4_546 ?
Ag10 Ag1 3.144(2) 4_547 ?
Ag10 Ag11 3.154(2) 4_547 ?
Ag10 Ag12 3.2535(19) 4_546 ?
Ag11 S12 2.453(6) 1_556 ?
Ag11 S6 2.555(5) 1_565 ?
Ag11 S4 2.567(6) . ?
Ag11 Ag10 3.154(2) 4_557 ?
Ag12 S9 2.438(6) . ?
Ag12 S12 2.471(5) . ?
Ag12 S11 2.669(7) 4_556 ?
Ag12 Ag10 3.2535(19) 4_556 ?
Ag13 S23 2.429(7) . ?
Ag13 S6 2.528(5) . ?
Ag13 S30 2.591(5) 1_545 ?
Ag13 Ag21 3.0744(19) . ?
Ag13 Ag26 3.228(2) . ?
Ag14 S9 2.434(6) . ?
Ag14 S21 2.593(7) . ?
Ag14 S22 2.667(5) . ?
Ag14 Ag15 3.014(2) . ?
Ag14 Ag28 3.117(2) . ?
Ag15 S1 2.452(6) . ?
Ag15 S25 2.630(5) . ?
Ag15 S23 2.694(5) 2_566 ?
Ag15 S18 2.862(7) . ?
Ag15 Ag20 3.0169(15) . ?

Ag15 Ag28 3.040(2) . ?
Ag16 S5 2.448(7) . ?
Ag16 S24 2.588(5) . ?
Ag16 S29 2.622(5) . ?
Ag16 S19 2.852(7) . ?
Ag16 Ag24 2.994(2) . ?
Ag16 Ag19 3.110(2) . ?
Ag16 Ag30 3.3159(17) . ?
Ag17 S7 2.425(6) . ?
Ag17 S26 2.498(5) . ?
Ag17 S24 2.600(7) 2_556 ?
Ag17 S31 2.919(5) . ?
Ag17 Ag23 3.0546(19) . ?
Ag17 Ag18 3.177(2) . ?
Ag18 S3 2.505(7) . ?
Ag18 S28 2.525(5) . ?
Ag18 S16 2.563(5) 4_546 ?
Ag18 S31 2.899(8) . ?
Ag18 Ag23 2.912(2) . ?
Ag18 Ag31 3.111(2) . ?
Ag19 S2 2.426(6) . ?
Ag19 S28 2.543(7) 4_546 ?
Ag19 S17 2.706(5) . ?
Ag19 S19 2.750(5) . ?
Ag19 Ag24 2.9662(18) . ?
Ag20 Ag34 2.340(2) . ?
Ag20 S18 2.355(6) 2_556 ?
Ag20 S18 2.355(6) . ?
Ag20 Ag15 3.0169(15) 2_556 ?
Ag20 Ag27 3.292(2) 2_566 ?
Ag20 Ag27 3.292(2) 1_565 ?
Ag21 S13 2.529(6) . ?
Ag21 S26 2.763(5) . ?
Ag21 S29 2.795(7) 2_556 ?
Ag21 S20 2.787(5) . ?
Ag21 Ag26 2.898(2) . ?
Ag22 S26 2.397(6) . ?
Ag22 S27 2.508(5) . ?
Ag22 Ag29 2.8677(19) . ?
Ag22 Ag31 2.903(2) . ?
Ag22 S19 2.916(7) . ?
Ag23 S4 2.526(6) . ?
Ag23 S30 2.582(5) . ?
Ag23 S31 2.601(5) . ?
Ag23 S25 2.764(7) 2_556 ?
Ag24 S22 2.589(5) . ?
Ag24 S10 2.584(6) . ?
Ag24 S27 2.692(7) . ?
Ag24 S19 2.767(5) . ?
Ag25 S16 2.442(5) . ?
Ag25 S30 2.528(6) . ?
Ag25 S18 2.671(7) . ?
Ag25 S20 2.764(5) 1_565 ?
Ag25 Ag31 2.915(2) 4_556 ?
Ag25 Ag29 3.0796(19) 4_556 ?
Ag25 Ag27 3.3181(17) 1_565 ?
Ag26 S21 2.521(5) 4_546 ?
Ag26 S11 2.516(7) . ?
Ag26 S27 2.588(5) 4_546 ?
Ag26 S20 2.898(8) . ?
Ag26 Ag31 3.133(2) 4_546 ?

Ag27 S17 2.484(6) . ?
Ag27 S23 2.514(5) . ?
Ag27 S18 2.762(5) 1_545 ?
Ag27 S20 2.778(7) . ?
Ag27 Ag32 3.2629(19) . ?
Ag27 Ag20 3.292(2) 1_545 ?
Ag27 Ag25 3.3181(17) 1_545 ?
Ag28 S8 2.550(6) . ?
Ag28 S17 2.561(5) 1_565 ?
Ag28 S16 2.723(8) . ?
Ag28 S18 2.956(5) . ?
Ag29 S28 2.510(6) 4_546 ?
Ag29 S21 2.539(6) 4_546 ?
Ag29 Ag31 2.8824(16) 4_546 ?
Ag29 Ag25 3.0796(19) 4_546 ?
Ag29 Hg2 3.1864(19) 4_546 ?
Ag29 Cu2 3.1864(19) 4_546 ?
Ag30 S19 2.497(6) 2_556 ?
Ag30 S19 2.497(6) . ?
Ag30 Ag33 2.739(2) 2_556 ?
Ag30 Ag33 2.739(2) . ?
Ag30 S24 2.740(6) 2_556 ?
Ag30 S24 2.740(6) . ?
Ag30 Ag32 2.904(3) . ?
Ag30 Ag16 3.3159(17) 2_556 ?
Ag31 S20 2.353(6) 4_556 ?
Ag31 S31 2.532(6) . ?
Ag31 S16 2.790(7) 4_546 ?
Ag31 S27 2.875(6) . ?
Ag31 Ag29 2.8824(16) 4_556 ?
Ag31 Ag25 2.915(2) 4_546 ?
Ag31 Ag26 3.133(2) 4_556 ?
Ag32 S29 2.321(7) 2_556 ?
Ag32 S29 2.321(7) . ?
Ag32 Cu1 3.2118(13) 2_556 ?
Ag32 Hg1 3.2118(13) 2_556 ?
Ag32 Ag27 3.2629(19) 2_556 ?
Ag33 S22 2.473(6) . ?
Ag33 S24 2.625(5) 2_556 ?
Ag33 S31 2.626(7) . ?
Ag33 Ag34 3.0354(19) . ?
Ag34 S25 2.433(6) 2_556 ?
Ag34 S25 2.433(6) . ?
Ag34 Ag33 3.035(2) 2_556 ?
As1 S10 2.179(6) . ?
As1 S5 2.218(6) . ?
As1 S2 2.286(6) . ?
As2 S8 2.228(6) . ?
As2 S9 2.231(6) . ?
As2 S1 2.305(6) . ?
As3 S4 2.260(6) . ?
As3 S7 2.271(6) . ?
As3 S3 2.312(6) . ?
As4 S6 2.095(6) . ?
As4 S11 2.196(6) . ?
As4 S13 2.213(6) . ?
As5 S21 2.261(5) . ?
As5 S26 2.295(7) 4_556 ?
As5 S16 2.306(5) . ?
As6 S22 2.159(8) . ?
As6 S24 2.188(5) . ?

As6 S25 2.256(5) . ?
As7 S23 2.229(5) . ?
As7 S29 2.249(5) 2_556 ?
As7 S17 2.253(8) 2_556 ?
As8 S28 2.242(6) 4_546 ?
As8 S27 2.319(5) . ?
As8 S30 2.348(8) 4_546 ?
S1 Ag3 2.475(6) 2 ?
S1 Ag5 2.520(5) 1_565 ?
S3 Ag9 2.453(6) 4_556 ?
S4 Ag3 2.417(5) 1_556 ?
S5 Ag7 2.493(7) 2_556 ?
S6 Ag5 2.498(6) 2_556 ?
S6 Ag11 2.555(5) 1_545 ?
S7 Ag4 2.525(6) 2_556 ?
S8 Ag6 2.439(6) 1_565 ?
S8 Ag10 2.586(6) 4_556 ?
S10 Ag1 2.586(6) 4_546 ?
S11 Ag1 2.453(7) 1_545 ?
S11 Ag12 2.669(7) 4_546 ?
S12 Ag9 2.407(5) 4 ?
S12 Ag11 2.453(6) 1_554 ?
S12 Ag1 2.485(5) 1_554 ?
S12 Ag10 2.520(5) 4_556 ?
S12 Ag8 2.574(6) 4_556 ?
S14 Ag3 2.511(5) 2 ?
S14 Ag2 2.533(3) 2 ?
S14 Ag4 2.533(6) 2 ?
S15 Ag7 2.478(4) 2_556 ?
S15 Ag7 2.478(4) 1_554 ?
S15 Ag6 2.486(3) 2 ?
S15 Ag5 2.589(5) 2 ?
S16 Ag18 2.563(5) 4_556 ?
S16 Ag31 2.790(7) 4_556 ?
S17 As7 2.253(8) 2_556 ?
S17 Ag28 2.561(5) 1_545 ?
S18 Ag27 2.762(5) 1_565 ?
S20 Ag31 2.353(6) 4_546 ?
S20 Ag25 2.764(5) 1_545 ?
S21 Ag26 2.521(5) 4_556 ?
S21 Ag29 2.539(6) 4_556 ?
S23 Ag15 2.694(5) 2_546 ?
S24 Ag17 2.600(7) 2_556 ?
S24 Ag33 2.625(5) 2_556 ?
S25 Ag23 2.764(7) 2_556 ?
S26 As5 2.295(7) 4_546 ?
S27 Ag26 2.588(5) 4_556 ?
S28 As8 2.242(6) 4_556 ?
S28 Ag29 2.510(6) 4_556 ?
S28 Ag19 2.543(7) 4_556 ?
S29 As7 2.249(5) 2_556 ?
S29 Ag21 2.795(7) 2_556 ?
S30 As8 2.348(8) 4_556 ?
S30 Ag13 2.591(5) 1_565 ?

loop_
_geom_angle_atom_site_label_1
_geom_angle_atom_site_label_2
_geom_angle_atom_site_label_3
_geom_angle
_geom_angle_site_symmetry_1

_geom_angle_site_symmetry_3
_geom_angle_publ_flag
S19 Hg1 S20 173.4(2) . . ?
S19 Hg1 Ag21 125.31(14) . . ?
S20 Hg1 Ag21 61.29(14) . . ?
S19 Hg1 Ag19 60.36(13) . . ?
S20 Hg1 Ag19 113.03(14) . . ?
Ag21 Hg1 Ag19 173.75(6) . . ?
S19 Hg1 Ag22 61.23(16) . . ?
S20 Hg1 Ag22 119.82(17) . . ?
Ag21 Hg1 Ag22 95.79(5) . . ?
Ag19 Hg1 Ag22 84.86(5) . . ?
S19 Hg1 Ag32 66.25(16) . . ?
S20 Hg1 Ag32 115.12(15) . . ?
Ag21 Hg1 Ag32 95.96(4) . . ?
Ag19 Hg1 Ag32 88.89(5) . . ?
Ag22 Hg1 Ag32 122.50(5) . . ?
S19 Hg1 Ag27 121.81(17) . . ?
S20 Hg1 Ag27 56.98(16) . . ?
Ag21 Hg1 Ag27 83.57(5) . . ?
Ag19 Hg1 Ag27 95.42(5) . . ?
Ag22 Hg1 Ag27 176.60(6) . . ?
Ag32 Hg1 Ag27 60.89(5) . . ?
S19 Hg1 Ag29 108.91(15) . . ?
S20 Hg1 Ag29 69.89(15) . . ?
Ag21 Hg1 Ag29 85.51(5) . . ?
Ag19 Hg1 Ag29 90.01(5) . . ?
Ag22 Hg1 Ag29 52.39(4) . . ?
Ag32 Hg1 Ag29 174.87(5) . . ?
Ag27 Hg1 Ag29 124.22(5) . . ?
S31 Hg2 S18 169.4(2) . . ?
S31 Hg2 S30 95.4(2) . . ?
S18 Hg2 S30 85.63(19) . . ?
S31 Hg2 Ag23 55.57(13) . . ?
S18 Hg2 Ag23 119.02(13) . . ?
S30 Hg2 Ag23 50.29(10) . . ?
S31 Hg2 Ag25 130.61(18) . . ?
S18 Hg2 Ag25 57.04(15) . . ?
S30 Hg2 Ag25 49.09(10) . . ?
Ag23 Hg2 Ag25 99.33(5) . . ?
S31 Hg2 Ag14 118.45(14) . . ?
S18 Hg2 Ag14 65.89(13) . . ?
S30 Hg2 Ag14 137.61(10) . . ?
Ag23 Hg2 Ag14 172.09(6) . . ?
Ag25 Hg2 Ag14 88.56(5) . . ?
S31 Hg2 Ag29 77.11(15) . 4_556 ?
S18 Hg2 Ag29 112.81(14) . 4_556 ?
S30 Hg2 Ag29 66.70(12) . 4_556 ?
Ag23 Hg2 Ag29 88.54(5) . 4_556 ?
Ag25 Hg2 Ag29 58.83(4) . 4_556 ?
Ag14 Hg2 Ag29 95.13(5) . 4_556 ?
S31 Hg2 Ag33 52.27(17) . . ?
S18 Hg2 Ag33 119.94(16) . . ?
S30 Hg2 Ag33 131.61(10) . . ?
Ag23 Hg2 Ag33 81.58(5) . . ?
Ag25 Hg2 Ag33 176.92(7) . . ?
Ag14 Hg2 Ag33 90.57(5) . . ?
Ag29 Hg2 Ag33 124.21(5) 4_556 . ?
S11 Ag1 S12 140.1(2) 1_565 1_556 ?
S11 Ag1 S10 106.0(2) 1_565 4_556 ?
S12 Ag1 S10 113.76(18) 1_556 4_556 ?

S11 Ag1 Ag11 91.67(18) 1_565 . ?
S12 Ag1 Ag11 52.64(14) 1_556 . ?
S10 Ag1 Ag11 147.42(14) 4_556 . ?
S11 Ag1 Ag10 99.14(15) 1_565 4_557 ?
S12 Ag1 Ag10 51.57(12) 1_556 4_557 ?
S10 Ag1 Ag10 137.73(16) 4_556 4_557 ?
Ag11 Ag1 Ag10 62.10(5) . 4_557 ?
S11 Ag1 Ag8 144.08(18) 1_565 4_557 ?
S12 Ag1 Ag8 49.98(14) 1_556 4_557 ?
S10 Ag1 Ag8 80.98(15) 4_556 4_557 ?
Ag11 Ag1 Ag8 100.70(6) . 4_557 ?
Ag10 Ag1 Ag8 59.37(5) 4_557 4_557 ?
S10 Ag2 S14 143.1(2) . . ?
S10 Ag2 S9 113.6(2) . . ?
S14 Ag2 S9 103.3(2) . . ?
S10 Ag2 Ag4 97.65(16) . . ?
S14 Ag2 Ag4 53.08(13) . . ?
S9 Ag2 Ag4 132.00(14) . . ?
S10 Ag2 Ag4 98.21(16) . 2 ?
S14 Ag2 Ag4 50.02(13) . 2 ?
S9 Ag2 Ag4 140.68(15) . 2 ?
Ag4 Ag2 Ag4 60.38(6) . 2 ?
S4 Ag3 S1 119.84(18) 1_554 2 ?
S4 Ag3 S14 126.71(17) 1_554 . ?
S1 Ag3 S14 113.18(16) 2 . ?
S5 Ag4 S7 105.56(19) . 2_556 ?
S5 Ag4 S14 135.70(17) . . ?
S7 Ag4 S14 118.60(14) 2_556 . ?
S5 Ag4 Ag2 88.71(17) . . ?
S7 Ag4 Ag2 152.93(13) 2_556 . ?
S14 Ag4 Ag2 53.10(5) . . ?
S5 Ag4 Ag4 94.42(14) . 2 ?
S7 Ag4 Ag4 136.02(17) 2_556 2 ?
S14 Ag4 Ag4 51.23(11) . 2 ?
Ag2 Ag4 Ag4 63.12(6) . 2 ?
S5 Ag4 Ag2 138.37(17) . 2 ?
S7 Ag4 Ag2 84.04(15) 2_556 2 ?
S14 Ag4 Ag2 50.04(5) . 2 ?
Ag2 Ag4 Ag2 100.64(7) . 2 ?
Ag4 Ag4 Ag2 56.50(6) 2 2 ?
S6 Ag5 S1 108.19(18) 2_556 1_545 ?
S6 Ag5 S15 116.06(14) 2_556 . ?
S1 Ag5 S15 135.74(16) 1_545 . ?
S6 Ag5 Ag6 150.89(12) 2_556 . ?
S1 Ag5 Ag6 90.87(15) 1_545 . ?
S15 Ag5 Ag6 49.54(4) . . ?
S6 Ag5 Ag6 81.16(14) 2_556 2 ?
S1 Ag5 Ag6 144.36(14) 1_545 2 ?
S15 Ag5 Ag6 48.25(4) . 2 ?
Ag6 Ag5 Ag6 96.23(6) . 2 ?
S6 Ag5 Ag5 134.75(16) 2_556 2 ?
S1 Ag5 Ag5 96.51(12) 1_545 2 ?
S15 Ag5 Ag5 50.54(10) . 2 ?
Ag6 Ag5 Ag5 60.90(6) . 2 ?
Ag6 Ag5 Ag5 58.13(6) 2 2 ?
S8 Ag6 S15 137.4(2) 1_545 . ?
S8 Ag6 S2 111.4(2) 1_545 . ?
S15 Ag6 S2 111.1(2) . . ?
S8 Ag6 Ag5 93.61(16) 1_545 . ?
S15 Ag6 Ag5 52.42(12) . . ?
S2 Ag6 Ag5 136.06(14) . . ?

S8 Ag6 Ag5 92.38(16) 1_545 2 ?
S15 Ag6 Ag5 50.99(12) . 2 ?
S2 Ag6 Ag5 146.49(15) . 2 ?
Ag5 Ag6 Ag5 60.97(5) . 2 ?
S13 Ag7 S15 125.51(17) . 1_556 ?
S13 Ag7 S5 124.36(19) . 2_556 ?
S15 Ag7 S5 109.86(17) 1_556 2_556 ?
S7 Ag8 S12 139.78(19) . 4_546 ?
S7 Ag8 S13 115.4(2) . . ?
S12 Ag8 S13 104.7(2) 4_546 . ?
S7 Ag8 Ag10 98.43(14) . . ?
S12 Ag8 Ag10 50.17(12) 4_546 . ?
S13 Ag8 Ag10 130.30(15) . . ?
S7 Ag8 Ag1 96.49(15) . 4_547 ?
S12 Ag8 Ag1 47.66(12) 4_546 4_547 ?
S13 Ag8 Ag1 142.35(15) . 4_547 ?
Ag10 Ag8 Ag1 57.41(5) . 4_547 ?
S12 Ag9 S2 124.75(19) 4_545 . ?
S12 Ag9 S3 117.0(2) 4_545 4_546 ?
S2 Ag9 S3 118.29(19) . 4_546 ?
S3 Ag10 S12 132.35(19) . 4_546 ?
S3 Ag10 S8 102.16(19) . 4_546 ?
S12 Ag10 S8 124.85(18) 4_546 4_546 ?
S3 Ag10 Ag1 92.12(14) . 4_547 ?
S12 Ag10 Ag1 50.58(12) 4_546 4_547 ?
S8 Ag10 Ag1 134.54(16) 4_546 4_547 ?
S3 Ag10 Ag11 137.54(16) . 4_547 ?
S12 Ag10 Ag11 49.71(14) 4_546 4_547 ?
S8 Ag10 Ag11 86.57(15) 4_546 4_547 ?
Ag1 Ag10 Ag11 56.13(5) 4_547 4_547 ?
S3 Ag10 Ag8 87.68(16) . . ?
S12 Ag10 Ag8 51.68(14) 4_546 . ?
S8 Ag10 Ag8 158.22(13) 4_546 . ?
Ag1 Ag10 Ag8 63.22(5) 4_547 . ?
Ag11 Ag10 Ag8 99.33(6) 4_547 . ?
S3 Ag10 Ag12 153.86(19) . 4_546 ?
S12 Ag10 Ag12 48.66(12) 4_546 4_546 ?
S8 Ag10 Ag12 87.20(12) 4_546 4_546 ?
Ag1 Ag10 Ag12 98.56(5) 4_547 4_546 ?
Ag11 Ag10 Ag12 66.54(5) 4_547 4_546 ?
Ag8 Ag10 Ag12 76.21(5) . 4_546 ?
S12 Ag11 S6 140.36(19) 1_556 1_565 ?
S12 Ag11 S4 107.9(2) 1_556 . ?
S6 Ag11 S4 111.5(2) 1_565 . ?
S12 Ag11 Ag1 53.61(13) 1_556 . ?
S6 Ag11 Ag1 95.66(14) 1_565 . ?
S4 Ag11 Ag1 140.63(13) . . ?
S12 Ag11 Ag10 51.57(13) 1_556 4_557 ?
S6 Ag11 Ag10 93.90(14) 1_565 4_557 ?
S4 Ag11 Ag10 138.98(14) . 4_557 ?
Ag1 Ag11 Ag10 61.76(5) . 4_557 ?
S9 Ag12 S12 137.97(19) . . ?
S9 Ag12 S11 115.29(19) . 4_556 ?
S12 Ag12 S11 106.66(19) . 4_556 ?
S9 Ag12 Ag10 98.33(12) . 4_556 ?
S12 Ag12 Ag10 49.96(12) . 4_556 ?
S11 Ag12 Ag10 134.06(18) 4_556 4_556 ?
S23 Ag13 S6 110.7(2) . . ?
S23 Ag13 S30 100.8(2) . 1_545 ?
S6 Ag13 S30 118.46(18) . 1_545 ?
S23 Ag13 Ag21 92.76(13) . . ?

S6 Ag13 Ag21 92.24(11) . . ?
S30 Ag13 Ag21 138.32(12) 1_545 . ?
S23 Ag13 Ag26 140.35(13) . . ?
S6 Ag13 Ag26 94.21(14) . . ?
S30 Ag13 Ag26 93.14(14) 1_545 . ?
Ag21 Ag13 Ag26 54.69(5) . . ?
S9 Ag14 S21 108.65(19) . . ?
S9 Ag14 S22 100.2(2) . . ?
S21 Ag14 S22 105.39(19) . . ?
S9 Ag14 Ag15 92.57(15) . . ?
S21 Ag14 Ag15 147.98(13) . . ?
S22 Ag14 Ag15 93.64(14) . . ?
S9 Ag14 Hg2 170.18(13) . . ?
S21 Ag14 Hg2 67.04(12) . . ?
S22 Ag14 Hg2 73.31(16) . . ?
Ag15 Ag14 Hg2 95.17(5) . . ?
S9 Ag14 Ag28 93.21(12) . . ?
S21 Ag14 Ag28 94.76(12) . . ?
S22 Ag14 Ag28 150.56(13) . . ?
Ag15 Ag14 Ag28 59.43(5) . . ?
Hg2 Ag14 Ag28 95.92(6) . . ?
S1 Ag15 S25 106.66(19) . . ?
S1 Ag15 S23 95.76(18) . 2_566 ?
S25 Ag15 S23 104.04(15) . 2_566 ?
S1 Ag15 S18 147.23(18) . . ?
S25 Ag15 S18 99.40(17) . . ?
S23 Ag15 S18 96.84(18) 2_566 . ?
S1 Ag15 Ag14 96.56(14) . . ?
S25 Ag15 Ag14 93.39(13) . . ?
S23 Ag15 Ag14 154.76(16) 2_566 . ?
S18 Ag15 Ag14 61.88(10) . . ?
S1 Ag15 Ag20 163.10(15) . . ?
S25 Ag15 Ag20 70.17(13) . . ?
S23 Ag15 Ag20 69.72(13) 2_566 . ?
S18 Ag15 Ag20 47.14(10) . . ?
Ag14 Ag15 Ag20 100.18(6) . . ?
S1 Ag15 Ag28 88.58(15) . . ?
S25 Ag15 Ag28 152.81(15) . . ?
S23 Ag15 Ag28 96.44(13) 2_566 . ?
S18 Ag15 Ag28 60.02(11) . . ?
Ag14 Ag15 Ag28 61.99(5) . . ?
Ag20 Ag15 Ag28 101.29(6) . . ?
S5 Ag16 S24 103.23(19) . . ?
S5 Ag16 S29 116.0(2) . . ?
S24 Ag16 S29 103.63(16) . . ?
S5 Ag16 S19 143.7(2) . . ?
S24 Ag16 S19 92.90(19) . . ?
S29 Ag16 S19 90.69(18) . . ?
S5 Ag16 Ag24 89.83(17) . . ?
S24 Ag16 Ag24 93.62(15) . . ?
S29 Ag16 Ag24 143.81(16) . . ?
S19 Ag16 Ag24 56.43(11) . . ?
S5 Ag16 Ag19 97.93(16) . . ?
S24 Ag16 Ag19 144.60(17) . . ?
S29 Ag16 Ag19 91.86(13) . . ?
S19 Ag16 Ag19 54.73(11) . . ?
Ag24 Ag16 Ag19 58.11(5) . . ?
S5 Ag16 Ag30 156.39(15) . . ?
S24 Ag16 Ag30 53.61(14) . . ?
S29 Ag16 Ag30 78.06(13) . . ?
S19 Ag16 Ag30 47.03(11) . . ?

Ag24 Ag16 Ag30 87.54(6) . . ?
Ag19 Ag16 Ag30 100.52(6) . . ?
S7 Ag17 S26 116.93(18) . . ?
S7 Ag17 S24 103.58(19) . 2_556 ?
S26 Ag17 S24 102.8(2) . 2_556 ?
S7 Ag17 S31 142.97(16) . . ?
S26 Ag17 S31 91.86(15) . . ?
S24 Ag17 S31 91.07(18) 2_556 . ?
S7 Ag17 Ag23 92.71(11) . . ?
S26 Ag17 Ag23 139.33(12) . . ?
S24 Ag17 Ag23 95.85(12) 2_556 . ?
S31 Ag17 Ag23 51.56(9) . . ?
S7 Ag17 Ag18 97.59(14) . . ?
S26 Ag17 Ag18 91.35(14) . . ?
S24 Ag17 Ag18 145.39(12) 2_556 . ?
S31 Ag17 Ag18 56.60(15) . . ?
Ag23 Ag17 Ag18 55.68(5) . . ?
S3 Ag18 S28 109.4(2) . . ?
S3 Ag18 S16 103.42(19) . 4_546 ?
S28 Ag18 S16 104.57(18) . 4_546 ?
S3 Ag18 S31 142.10(19) . . ?
S28 Ag18 S31 97.20(18) . . ?
S16 Ag18 S31 95.04(19) 4_546 . ?
S3 Ag18 Ag23 97.63(15) . . ?
S28 Ag18 Ag23 93.40(15) . . ?
S16 Ag18 Ag23 145.63(18) 4_546 . ?
S31 Ag18 Ag23 53.18(10) . . ?
S3 Ag18 Ag31 161.31(14) . . ?
S28 Ag18 Ag31 76.98(13) . . ?
S16 Ag18 Ag31 57.94(15) 4_546 . ?
S31 Ag18 Ag31 49.68(10) . . ?
Ag23 Ag18 Ag31 99.51(7) . . ?
S3 Ag18 Ag17 88.55(15) . . ?
S28 Ag18 Ag17 150.32(17) . . ?
S16 Ag18 Ag17 93.39(15) 4_546 . ?
S31 Ag18 Ag17 57.20(10) . . ?
Ag23 Ag18 Ag17 60.04(5) . . ?
Ag31 Ag18 Ag17 93.56(6) . . ?
S2 Ag19 S28 105.6(2) . 4_546 ?
S2 Ag19 S17 98.4(2) . . ?
S28 Ag19 S17 106.4(2) 4_546 . ?
S2 Ag19 S19 143.4(2) . . ?
S28 Ag19 S19 101.1(2) 4_546 . ?
S17 Ag19 S19 97.48(17) . . ?
S2 Ag19 Ag24 93.84(13) . . ?
S28 Ag19 Ag24 97.73(13) 4_546 . ?
S17 Ag19 Ag24 148.67(13) . . ?
S19 Ag19 Ag24 57.75(11) . . ?
S2 Ag19 Hg1 166.99(14) . . ?
S28 Ag19 Hg1 73.53(13) 4_546 . ?
S17 Ag19 Hg1 69.88(15) . . ?
S19 Ag19 Hg1 47.24(13) . . ?
Ag24 Ag19 Hg1 99.14(5) . . ?
S2 Ag19 Ag16 88.69(16) . . ?
S28 Ag19 Ag16 153.97(14) 4_546 . ?
S17 Ag19 Ag16 92.47(15) . . ?
S19 Ag19 Ag16 57.86(15) . . ?
Ag24 Ag19 Ag16 59.00(5) . . ?
Hg1 Ag19 Ag16 97.30(5) . . ?
Ag34 Ag20 S18 93.17(11) . 2_556 ?
Ag34 Ag20 S18 93.17(11) . . ?

S18 Ag20 S18 173.7(2) 2_556 . ?
Ag34 Ag20 Ag15 88.68(4) . 2_556 ?
S18 Ag20 Ag15 62.97(16) 2_556 2_556 ?
S18 Ag20 Ag15 117.20(16) . 2_556 ?
Ag34 Ag20 Ag15 88.68(4) . . ?
S18 Ag20 Ag15 117.20(16) 2_556 . ?
S18 Ag20 Ag15 62.97(16) . . ?
Ag15 Ag20 Ag15 177.37(9) 2_556 . ?
Ag34 Ag20 Ag27 146.65(3) . 2_566 ?
S18 Ag20 Ag27 55.63(11) 2_556 2_566 ?
S18 Ag20 Ag27 118.17(13) . 2_566 ?
Ag15 Ag20 Ag27 86.73(5) 2_556 2_566 ?
Ag15 Ag20 Ag27 95.47(5) . 2_566 ?
Ag34 Ag20 Ag27 146.65(3) . 1_565 ?
S18 Ag20 Ag27 118.17(13) 2_556 1_565 ?
S18 Ag20 Ag27 55.63(11) . 1_565 ?
Ag15 Ag20 Ag27 95.47(5) 2_556 1_565 ?
Ag15 Ag20 Ag27 86.73(5) . 1_565 ?
Ag27 Ag20 Ag27 66.69(6) 2_566 1_565 ?
S13 Ag21 S26 98.67(17) . . ?
S13 Ag21 S29 102.9(2) . 2_556 ?
S26 Ag21 S29 100.67(18) . 2_556 ?
S13 Ag21 S20 150.79(19) . . ?
S26 Ag21 S20 99.92(14) . . ?
S29 Ag21 S20 95.5(2) 2_556 . ?
S13 Ag21 Ag26 94.23(16) . . ?
S26 Ag21 Ag26 97.13(14) . . ?
S29 Ag21 Ag26 152.97(12) 2_556 . ?
S20 Ag21 Ag26 61.26(16) . . ?
S13 Ag21 Hg1 160.51(14) . . ?
S26 Ag21 Hg1 68.60(13) . . ?
S29 Ag21 Hg1 66.75(12) 2_556 . ?
S20 Ag21 Hg1 48.68(13) . . ?
Ag26 Ag21 Hg1 101.79(6) . . ?
S13 Ag21 Ag13 91.04(12) . . ?
S26 Ag21 Ag13 160.69(12) . . ?
S29 Ag21 Ag13 93.28(11) 2_556 . ?
S20 Ag21 Ag13 65.21(10) . . ?
Ag26 Ag21 Ag13 65.36(5) . . ?
Hg1 Ag21 Ag13 105.63(6) . . ?
S26 Ag22 S27 168.9(2) . . ?
S26 Ag22 Ag29 77.82(13) . . ?
S27 Ag22 Ag29 95.27(13) . . ?
S26 Ag22 Ag31 109.70(16) . . ?
S27 Ag22 Ag31 63.69(14) . . ?
Ag29 Ag22 Ag31 107.31(7) . . ?
S26 Ag22 S19 94.8(2) . . ?
S27 Ag22 S19 95.5(2) . . ?
Ag29 Ag22 S19 105.38(12) . . ?
Ag31 Ag22 S19 142.43(13) . . ?
S26 Ag22 Hg1 69.07(14) . . ?
S27 Ag22 Hg1 116.22(14) . . ?
Ag29 Ag22 Hg1 65.30(4) . . ?
Ag31 Ag22 Hg1 172.59(7) . . ?
S19 Ag22 Hg1 44.29(11) . . ?
S4 Ag23 S30 99.29(18) . . ?
S4 Ag23 S31 153.16(19) . . ?
S30 Ag23 S31 99.72(16) . . ?
S4 Ag23 S25 103.46(18) . 2_556 ?
S30 Ag23 S25 99.49(19) . 2_556 ?
S31 Ag23 S25 91.9(2) . 2_556 ?

S4 Ag23 Ag18 95.16(15) . . ?
S30 Ag23 Ag18 99.24(15) . . ?
S31 Ag23 Ag18 63.15(16) . . ?
S25 Ag23 Ag18 150.96(11) 2_556 . ?
S4 Ag23 Ag17 95.71(11) . . ?
S30 Ag23 Ag17 158.73(13) . . ?
S31 Ag23 Ag17 61.52(11) . . ?
S25 Ag23 Ag17 91.53(10) 2_556 . ?
Ag18 Ag23 Ag17 64.28(5) . . ?
S4 Ag23 Hg2 159.15(13) . . ?
S30 Ag23 Hg2 63.43(14) . . ?
S31 Ag23 Hg2 47.38(13) . . ?
S25 Ag23 Hg2 70.28(11) 2_556 . ?
Ag18 Ag23 Hg2 99.00(6) . . ?
Ag17 Ag23 Hg2 104.19(6) . . ?
S22 Ag24 S10 108.34(19) . . ?
S22 Ag24 S27 99.46(19) . . ?
S10 Ag24 S27 102.01(19) . . ?
S22 Ag24 S19 94.02(17) . . ?
S10 Ag24 S19 148.97(18) . . ?
S27 Ag24 S19 94.98(19) . . ?
S22 Ag24 Ag19 149.33(13) . . ?
S10 Ag24 Ag19 95.51(12) . . ?
S27 Ag24 Ag19 93.95(11) . . ?
S19 Ag24 Ag19 57.20(11) . . ?
S22 Ag24 Ag16 94.56(15) . . ?
S10 Ag24 Ag16 96.87(15) . . ?
S27 Ag24 Ag16 151.50(12) . . ?
S19 Ag24 Ag16 59.19(15) . . ?
Ag19 Ag24 Ag16 62.90(5) . . ?
S16 Ag25 S30 162.8(2) . . ?
S16 Ag25 S18 102.5(2) . . ?
S30 Ag25 S18 89.7(2) . . ?
S16 Ag25 S20 89.77(16) . 1_565 ?
S30 Ag25 S20 98.31(17) . 1_565 ?
S18 Ag25 S20 107.0(2) . 1_565 ?
S16 Ag25 Ag31 62.02(16) . 4_556 ?
S30 Ag25 Ag31 112.77(16) . 4_556 ?
S18 Ag25 Ag31 147.52(13) . 4_556 ?
S20 Ag25 Ag31 48.86(13) 1_565 4_556 ?
S16 Ag25 Ag29 90.61(14) . 4_556 ?
S30 Ag25 Ag29 74.06(14) . 4_556 ?
S18 Ag25 Ag29 107.14(11) . 4_556 ?
S20 Ag25 Ag29 144.90(17) 1_565 4_556 ?
Ag31 Ag25 Ag29 101.65(6) 4_556 4_556 ?
S16 Ag25 Hg2 116.13(15) . . ?
S30 Ag25 Hg2 63.82(14) . . ?
S18 Ag25 Hg2 47.53(11) . . ?
S20 Ag25 Hg2 145.24(12) 1_565 . ?
Ag31 Ag25 Hg2 163.90(7) 4_556 . ?
Ag29 Ag25 Hg2 62.28(4) 4_556 . ?
S16 Ag25 Ag27 100.74(16) . 1_565 ?
S30 Ag25 Ag27 96.23(15) . 1_565 ?
S18 Ag25 Ag27 53.61(10) . 1_565 ?
S20 Ag25 Ag27 53.41(15) 1_565 1_565 ?
Ag31 Ag25 Ag27 99.05(5) 4_556 1_565 ?
Ag29 Ag25 Ag27 159.23(5) 4_556 1_565 ?
Hg2 Ag25 Ag27 96.99(5) . 1_565 ?
S21 Ag26 S11 107.3(2) 4_546 . ?
S21 Ag26 S27 102.96(18) 4_546 4_546 ?
S11 Ag26 S27 103.0(2) . 4_546 ?

S21 Ag26 Ag21 95.96(14) 4_546 . ?
S11 Ag26 Ag21 96.68(17) . . ?
S27 Ag26 Ag21 147.03(17) 4_546 . ?
S21 Ag26 S20 97.55(18) 4_546 . ?
S11 Ag26 S20 146.20(19) . . ?
S27 Ag26 S20 93.07(19) 4_546 . ?
Ag21 Ag26 S20 57.47(11) . . ?
S21 Ag26 Ag31 76.88(13) 4_546 4_546 ?
S11 Ag26 Ag31 162.26(16) . 4_546 ?
S27 Ag26 Ag31 59.43(14) 4_546 4_546 ?
Ag21 Ag26 Ag31 100.04(7) . 4_546 ?
S20 Ag26 Ag31 45.73(11) . 4_546 ?
S21 Ag26 Ag13 153.87(16) 4_546 . ?
S11 Ag26 Ag13 86.92(16) . . ?
S27 Ag26 Ag13 94.70(14) 4_546 . ?
Ag21 Ag26 Ag13 59.95(5) . . ?
S20 Ag26 Ag13 61.99(11) . . ?
Ag31 Ag26 Ag13 96.34(6) 4_546 . ?
S17 Ag27 S23 167.2(2) . . ?
S17 Ag27 S18 94.31(17) . 1_545 ?
S23 Ag27 S18 91.08(16) . 1_545 ?
S17 Ag27 S20 92.6(2) . . ?
S23 Ag27 S20 97.3(2) . . ?
S18 Ag27 S20 104.17(19) 1_545 . ?
S17 Ag27 Hg1 68.85(15) . . ?
S23 Ag27 Hg1 112.91(14) . . ?
S18 Ag27 Hg1 141.90(12) 1_545 . ?
S20 Ag27 Hg1 46.07(11) . . ?
S17 Ag27 Ag32 74.16(13) . . ?
S23 Ag27 Ag32 95.64(13) . . ?
S18 Ag27 Ag32 150.66(16) 1_545 . ?
S20 Ag27 Ag32 103.24(11) . . ?
Hg1 Ag27 Ag32 59.32(3) . . ?
S17 Ag27 Ag20 109.30(16) . 1_545 ?
S23 Ag27 Ag20 67.14(14) . 1_545 ?
S18 Ag27 Ag20 44.73(12) 1_545 1_545 ?
S20 Ag27 Ag20 141.42(12) . 1_545 ?
Hg1 Ag27 Ag20 172.25(6) . 1_545 ?
Ag32 Ag27 Ag20 112.97(5) . 1_545 ?
S17 Ag27 Ag25 96.09(14) . 1_545 ?
S23 Ag27 Ag25 96.30(15) . 1_545 ?
S18 Ag27 Ag25 51.13(14) 1_545 1_545 ?
S20 Ag27 Ag25 53.04(10) . 1_545 ?
Hg1 Ag27 Ag25 95.40(5) . 1_545 ?
Ag32 Ag27 Ag25 154.66(5) . 1_545 ?
Ag20 Ag27 Ag25 92.27(4) 1_545 1_545 ?
S8 Ag28 S17 110.80(19) . 1_565 ?
S8 Ag28 S16 107.78(19) . . ?
S17 Ag28 S16 100.0(2) 1_565 . ?
S8 Ag28 S18 151.09(17) . . ?
S17 Ag28 S18 88.23(16) 1_565 . ?
S16 Ag28 S18 89.17(18) . . ?
S8 Ag28 Ag15 99.10(15) . . ?
S17 Ag28 Ag15 92.89(15) 1_565 . ?
S16 Ag28 Ag15 143.47(12) . . ?
S18 Ag28 Ag15 56.99(14) . . ?
S8 Ag28 Ag14 95.08(12) . . ?
S17 Ag28 Ag14 144.73(13) 1_565 . ?
S16 Ag28 Ag14 94.12(12) . . ?
S18 Ag28 Ag14 59.64(9) . . ?
Ag15 Ag28 Ag14 58.59(5) . . ?

S28 Ag29 S21 162.91(18) 4_546 4_546 ?
S28 Ag29 Ag22 84.81(14) 4_546 . ?
S21 Ag29 Ag22 110.90(13) 4_546 . ?
S28 Ag29 Ag31 81.69(13) 4_546 4_546 ?
S21 Ag29 Ag31 81.46(12) 4_546 4_546 ?
Ag22 Ag29 Ag31 145.15(7) . 4_546 ?
S28 Ag29 Ag25 109.27(14) 4_546 4_546 ?
S21 Ag29 Ag25 82.33(13) 4_546 4_546 ?
Ag22 Ag29 Ag25 74.50(5) . 4_546 ?
Ag31 Ag29 Ag25 140.34(7) 4_546 4_546 ?
S28 Ag29 Hg2 108.51(14) 4_546 4_546 ?
S21 Ag29 Hg2 66.03(13) 4_546 4_546 ?
Ag22 Ag29 Hg2 133.38(6) . 4_546 ?
Ag31 Ag29 Hg2 81.45(5) 4_546 4_546 ?
Ag25 Ag29 Hg2 58.89(4) 4_546 4_546 ?
S28 Ag29 Cu2 108.51(14) 4_546 4_546 ?
S21 Ag29 Cu2 66.03(13) 4_546 4_546 ?
Ag22 Ag29 Cu2 133.38(6) . 4_546 ?
Ag31 Ag29 Cu2 81.45(5) 4_546 4_546 ?
Ag25 Ag29 Cu2 58.89(4) 4_546 4_546 ?
Hg2 Ag29 Cu2 0.00(5) 4_546 4_546 ?
S28 Ag29 Hg1 69.05(14) 4_546 . ?
S21 Ag29 Hg1 111.49(13) 4_546 . ?
Ag22 Ag29 Hg1 62.31(5) . . ?
Ag31 Ag29 Hg1 82.85(5) 4_546 . ?
Ag25 Ag29 Hg1 136.81(5) 4_546 . ?
Hg2 Ag29 Hg1 164.30(5) 4_546 . ?
Cu2 Ag29 Hg1 164.30(5) 4_546 . ?
S19 Ag30 S19 139.9(3) 2_556 . ?
S19 Ag30 Ag33 69.60(13) 2_556 2_556 ?
S19 Ag30 Ag33 147.50(14) . 2_556 ?
S19 Ag30 Ag33 147.50(14) 2_556 . ?
S19 Ag30 Ag33 69.60(13) . . ?
Ag33 Ag30 Ag33 87.50(8) 2_556 . ?
S19 Ag30 S24 97.70(19) 2_556 2_556 ?
S19 Ag30 S24 98.2(2) . 2_556 ?
Ag33 Ag30 S24 87.49(14) 2_556 2_556 ?
Ag33 Ag30 S24 57.25(11) . 2_556 ?
S19 Ag30 S24 98.2(2) 2_556 . ?
S19 Ag30 S24 97.70(19) . . ?
Ag33 Ag30 S24 57.25(11) 2_556 . ?
Ag33 Ag30 S24 87.49(14) . . ?
S24 Ag30 S24 132.2(2) 2_556 . ?
S19 Ag30 Ag32 69.97(13) 2_556 . ?
S19 Ag30 Ag32 69.97(13) . . ?
Ag33 Ag30 Ag32 136.25(4) 2_556 . ?
Ag33 Ag30 Ag32 136.25(4) . . ?
S24 Ag30 Ag32 113.88(12) 2_556 . ?
S24 Ag30 Ag32 113.88(12) . . ?
S19 Ag30 Ag16 56.68(15) 2_556 2_556 ?
S19 Ag30 Ag16 111.08(15) . 2_556 ?
Ag33 Ag30 Ag16 96.99(4) 2_556 2_556 ?
Ag33 Ag30 Ag16 106.15(5) . 2_556 ?
S24 Ag30 Ag16 49.49(11) 2_556 2_556 ?
S24 Ag30 Ag16 150.89(12) . 2_556 ?
Ag32 Ag30 Ag16 73.93(4) . 2_556 ?
S19 Ag30 Ag16 111.08(15) 2_556 . ?
S19 Ag30 Ag16 56.68(15) . . ?
Ag33 Ag30 Ag16 106.15(5) 2_556 . ?
Ag33 Ag30 Ag16 96.99(4) . . ?
S24 Ag30 Ag16 150.89(12) 2_556 . ?

S24 Ag30 Ag16 49.49(11) . . ?
Ag32 Ag30 Ag16 73.93(4) . . ?
Ag16 Ag30 Ag16 147.86(8) 2_556 . ?
S20 Ag31 S31 158.47(16) 4_556 . ?
S20 Ag31 S16 91.0(2) 4_556 4_546 ?
S31 Ag31 S16 98.49(19) . 4_546 ?
S20 Ag31 S27 98.92(19) 4_556 . ?
S31 Ag31 S27 94.15(19) . . ?
S16 Ag31 S27 116.20(16) 4_546 . ?
S20 Ag31 Ag29 78.39(12) 4_556 4_556 ?
S31 Ag31 Ag29 80.22(11) . 4_556 ?
S16 Ag31 Ag29 122.50(13) 4_546 4_556 ?
S27 Ag31 Ag29 121.24(12) . 4_556 ?
S20 Ag31 Ag22 133.77(12) 4_556 . ?
S31 Ag31 Ag22 67.52(11) . . ?
S16 Ag31 Ag22 77.14(14) 4_546 . ?
S27 Ag31 Ag22 51.44(11) . . ?
Ag29 Ag31 Ag22 144.97(8) 4_556 . ?
S20 Ag31 Ag25 62.22(13) 4_556 4_546 ?
S31 Ag31 Ag25 137.61(12) . 4_546 ?
S16 Ag31 Ag25 50.63(11) 4_546 4_546 ?
S27 Ag31 Ag25 79.71(13) . 4_546 ?
Ag29 Ag31 Ag25 138.47(8) 4_556 4_546 ?
Ag22 Ag31 Ag25 76.54(6) . 4_546 ?
S20 Ag31 Ag18 113.27(18) 4_556 . ?
S31 Ag31 Ag18 60.80(16) . . ?
S16 Ag31 Ag18 51.13(11) 4_546 . ?
S27 Ag31 Ag18 144.31(12) . . ?
Ag29 Ag31 Ag18 81.63(5) 4_556 . ?
Ag22 Ag31 Ag18 93.67(5) . . ?
Ag25 Ag31 Ag18 101.37(7) 4_546 . ?
S20 Ag31 Ag26 61.86(18) 4_556 4_556 ?
S31 Ag31 Ag26 116.29(17) . 4_556 ?
S16 Ag31 Ag26 142.36(12) 4_546 4_556 ?
S27 Ag31 Ag26 50.81(10) . 4_556 ?
Ag29 Ag31 Ag26 79.57(5) 4_556 4_556 ?
Ag22 Ag31 Ag26 102.22(7) . 4_556 ?
Ag25 Ag31 Ag26 92.17(5) 4_546 4_556 ?
Ag18 Ag31 Ag26 161.18(6) . 4_556 ?
S29 Ag32 S29 176.2(2) 2_556 . ?
S29 Ag32 Ag30 91.92(12) 2_556 . ?
S29 Ag32 Ag30 91.92(12) . . ?
S29 Ag32 Cu1 112.15(13) 2_556 2_556 ?
S29 Ag32 Cu1 68.10(13) . 2_556 ?
Ag30 Ag32 Cu1 86.53(4) . 2_556 ?
S29 Ag32 Hg1 112.15(13) 2_556 2_556 ?
S29 Ag32 Hg1 68.10(13) . 2_556 ?
Ag30 Ag32 Hg1 86.53(4) . 2_556 ?
Cu1 Ag32 Hg1 0.000(3) 2_556 2_556 ?
S29 Ag32 Hg1 68.10(13) 2_556 . ?
S29 Ag32 Hg1 112.15(13) . . ?
Ag30 Ag32 Hg1 86.53(4) . . ?
Cu1 Ag32 Hg1 173.07(7) 2_556 . ?
Hg1 Ag32 Hg1 173.07(7) 2_556 . ?
S29 Ag32 Ag27 100.80(13) 2_556 2_556 ?
S29 Ag32 Ag27 75.93(13) . 2_556 ?
Ag30 Ag32 Ag27 146.32(3) . 2_556 ?
Cu1 Ag32 Ag27 59.79(4) 2_556 2_556 ?
Hg1 Ag32 Ag27 59.79(4) 2_556 2_556 ?
Hg1 Ag32 Ag27 127.14(6) . 2_556 ?
S29 Ag32 Ag27 75.93(13) 2_556 . ?

S29 Ag32 Ag27 100.80(13) . . ?
Ag30 Ag32 Ag27 146.32(3) . . ?
Cu1 Ag32 Ag27 127.14(6) 2_556 . ?
Hg1 Ag32 Ag27 127.14(6) 2_556 . ?
Hg1 Ag32 Ag27 59.79(4) . . ?
Ag27 Ag32 Ag27 67.36(6) 2_556 . ?
S22 Ag33 S24 160.4(2) . 2_556 ?
S22 Ag33 S31 100.6(2) . . ?
S24 Ag33 S31 97.4(2) 2_556 . ?
S22 Ag33 Ag30 104.36(17) . . ?
S24 Ag33 Ag30 61.41(14) 2_556 . ?
S31 Ag33 Ag30 149.71(13) . . ?
S22 Ag33 Ag34 75.42(13) . . ?
S24 Ag33 Ag34 92.44(13) 2_556 . ?
S31 Ag33 Ag34 105.11(11) . . ?
Ag30 Ag33 Ag34 97.64(6) . . ?
S22 Ag33 Hg2 71.93(15) . . ?
S24 Ag33 Hg2 117.45(13) 2_556 . ?
S31 Ag33 Hg2 44.34(11) . . ?
Ag30 Ag33 Hg2 163.32(7) . . ?
Ag34 Ag33 Hg2 65.69(4) . . ?
Ag20 Ag34 S25 86.17(11) . 2_556 ?
Ag20 Ag34 S25 86.17(11) . . ?
S25 Ag34 S25 172.3(2) 2_556 . ?
Ag20 Ag34 Ag33 141.40(3) . 2_556 ?
S25 Ag34 Ag33 107.05(12) 2_556 2_556 ?
S25 Ag34 Ag33 79.12(12) . 2_556 ?
Ag20 Ag34 Ag33 141.40(3) . . ?
S25 Ag34 Ag33 79.12(12) 2_556 . ?
S25 Ag34 Ag33 107.05(12) . . ?
Ag33 Ag34 Ag33 77.21(7) 2_556 . ?
S10 As1 S5 97.8(2) . . ?
S10 As1 S2 99.2(2) . . ?
S5 As1 S2 98.8(2) . . ?
S8 As2 S9 103.1(2) . . ?
S8 As2 S1 97.2(2) . . ?
S9 As2 S1 97.7(2) . . ?
S4 As3 S7 98.3(2) . . ?
S4 As3 S3 99.9(2) . . ?
S7 As3 S3 98.4(2) . . ?
S6 As4 S11 100.8(2) . . ?
S6 As4 S13 96.7(3) . . ?
S11 As4 S13 100.5(2) . . ?
S21 As5 S26 100.9(2) . 4_556 ?
S21 As5 S16 101.63(18) . . ?
S26 As5 S16 94.9(2) 4_556 . ?
S22 As6 S24 101.4(3) . . ?
S22 As6 S25 98.2(2) . . ?
S24 As6 S25 99.98(19) . . ?
S23 As7 S29 98.3(2) . 2_556 ?
S23 As7 S17 102.4(2) . 2_556 ?
S29 As7 S17 95.4(2) 2_556 2_556 ?
S28 As8 S27 100.44(18) 4_546 . ?
S28 As8 S30 98.5(2) 4_546 4_546 ?
S27 As8 S30 100.7(2) . 4_546 ?
As2 S1 Ag15 114.4(3) . . ?
As2 S1 Ag3 102.2(2) . 2 ?
Ag15 S1 Ag3 110.18(19) . 2 ?
As2 S1 Ag5 103.3(2) . 1_565 ?
Ag15 S1 Ag5 119.8(2) . 1_565 ?
Ag3 S1 Ag5 105.2(3) 2 1_565 ?

As1 S2 Ag19 117.4(2) . . ?
As1 S2 Ag9 102.5(2) . . ?
Ag19 S2 Ag9 109.7(3) . . ?
As1 S2 Ag6 104.0(3) . . ?
Ag19 S2 Ag6 120.9(2) . . ?
Ag9 S2 Ag6 99.64(19) . . ?
As3 S3 Ag9 103.6(2) . 4_556 ?
As3 S3 Ag10 106.8(2) . . ?
Ag9 S3 Ag10 112.5(3) 4_556 . ?
As3 S3 Ag18 113.0(3) . . ?
Ag9 S3 Ag18 104.1(2) 4_556 . ?
Ag10 S3 Ag18 116.2(2) . . ?
As3 S4 Ag3 104.92(19) . 1_556 ?
As3 S4 Ag23 111.13(19) . . ?
Ag3 S4 Ag23 111.1(3) 1_556 . ?
As3 S4 Ag11 108.6(3) . . ?
Ag3 S4 Ag11 102.45(17) 1_556 . ?
Ag23 S4 Ag11 117.62(18) . . ?
As1 S5 Ag16 114.8(3) . . ?
As1 S5 Ag4 108.3(2) . . ?
Ag16 S5 Ag4 114.2(2) . . ?
As1 S5 Ag7 107.9(2) . 2_556 ?
Ag16 S5 Ag7 103.1(2) . 2_556 ?
Ag4 S5 Ag7 108.1(3) . 2_556 ?
As4 S6 Ag5 115.9(2) . 2_556 ?
As4 S6 Ag13 115.1(2) . . ?
Ag5 S6 Ag13 105.3(2) 2_556 . ?
As4 S6 Ag11 103.7(3) . 1_545 ?
Ag5 S6 Ag11 117.09(18) 2_556 1_545 ?
Ag13 S6 Ag11 98.82(17) . 1_545 ?
As3 S7 Ag17 114.1(2) . . ?
As3 S7 Ag8 101.2(3) . . ?
Ag17 S7 Ag8 103.42(18) . . ?
As3 S7 Ag4 109.6(2) . 2_556 ?
Ag17 S7 Ag4 114.1(3) . 2_556 ?
Ag8 S7 Ag4 113.69(18) . 2_556 ?
As2 S8 Ag6 107.7(3) . 1_565 ?
As2 S8 Ag28 108.6(2) . . ?
Ag6 S8 Ag28 106.08(19) 1_565 . ?
As2 S8 Ag10 107.6(2) . 4_556 ?
Ag6 S8 Ag10 118.4(2) 1_565 4_556 ?
Ag28 S8 Ag10 108.2(3) . 4_556 ?
As2 S9 Ag12 100.17(19) . . ?
As2 S9 Ag14 116.1(2) . . ?
Ag12 S9 Ag14 107.4(3) . . ?
As2 S9 Ag2 110.5(3) . . ?
Ag12 S9 Ag2 102.29(18) . . ?
Ag14 S9 Ag2 117.8(2) . . ?
As1 S10 Ag2 103.5(3) . . ?
As1 S10 Ag1 109.9(2) . 4_546 ?
Ag2 S10 Ag1 113.3(2) . 4_546 ?
As1 S10 Ag24 109.3(2) . . ?
Ag2 S10 Ag24 106.18(19) . . ?
Ag1 S10 Ag24 114.0(3) 4_546 . ?
As4 S11 Ag1 104.4(2) . 1_545 ?
As4 S11 Ag26 115.4(4) . . ?
Ag1 S11 Ag26 116.4(2) 1_545 . ?
As4 S11 Ag12 105.1(2) . 4_546 ?
Ag1 S11 Ag12 108.9(3) 1_545 4_546 ?
Ag26 S11 Ag12 106.0(2) . 4_546 ?
Ag9 S12 Ag11 101.9(2) 4 1_554 ?

Ag9 S12 Ag12 105.1(2) 4 . ?
Ag11 S12 Ag12 91.13(19) 1_554 . ?
Ag9 S12 Ag1 96.00(17) 4 1_554 ?
Ag11 S12 Ag1 73.75(16) 1_554 1_554 ?
Ag12 S12 Ag1 156.3(2) . 1_554 ?
Ag9 S12 Ag10 173.4(2) 4 4_556 ?
Ag11 S12 Ag10 78.72(16) 1_554 4_556 ?
Ag12 S12 Ag10 81.38(15) . 4_556 ?
Ag1 S12 Ag10 77.85(15) 1_554 4_556 ?
Ag9 S12 Ag8 98.9(2) 4 4_556 ?
Ag11 S12 Ag8 149.6(2) 1_554 4_556 ?
Ag12 S12 Ag8 104.5(2) . 4_556 ?
Ag1 S12 Ag8 82.35(17) 1_554 4_556 ?
Ag10 S12 Ag8 78.15(16) 4_556 4_556 ?
As4 S13 Ag7 108.3(2) . . ?
As4 S13 Ag21 114.1(2) . . ?
Ag7 S13 Ag21 114.0(3) . . ?
As4 S13 Ag8 107.4(3) . . ?
Ag7 S13 Ag8 94.30(18) . . ?
Ag21 S13 Ag8 116.79(19) . . ?
Ag3 S14 Ag3 101.8(3) 2 . ?
Ag3 S14 Ag2 95.62(8) 2 2 ?
Ag3 S14 Ag2 105.58(9) . 2 ?
Ag3 S14 Ag2 105.58(9) 2 . ?
Ag3 S14 Ag2 95.62(8) . . ?
Ag2 S14 Ag2 146.2(3) 2 . ?
Ag3 S14 Ag4 90.87(5) 2 . ?
Ag3 S14 Ag4 165.4(2) . . ?
Ag2 S14 Ag4 79.94(16) 2 . ?
Ag2 S14 Ag4 73.82(14) . . ?
Ag3 S14 Ag4 165.4(2) 2 2 ?
Ag3 S14 Ag4 90.87(5) . 2 ?
Ag2 S14 Ag4 73.82(14) 2 2 ?
Ag2 S14 Ag4 79.94(16) . 2 ?
Ag4 S14 Ag4 77.5(2) . 2 ?
Ag7 S15 Ag7 101.9(3) 2_556 1_554 ?
Ag7 S15 Ag6 94.02(9) 2_556 2 ?
Ag7 S15 Ag6 103.30(9) 1_554 2 ?
Ag7 S15 Ag6 103.30(9) 2_556 . ?
Ag7 S15 Ag6 94.02(9) 1_554 . ?
Ag6 S15 Ag6 152.4(3) 2 . ?
Ag7 S15 Ag5 89.89(5) 2_556 . ?
Ag7 S15 Ag5 167.1(2) 1_554 . ?
Ag6 S15 Ag5 80.76(14) 2 . ?
Ag6 S15 Ag5 78.04(14) . . ?
Ag7 S15 Ag5 167.1(2) 2_556 2 ?
Ag7 S15 Ag5 89.89(5) 1_554 2 ?
Ag6 S15 Ag5 78.04(14) 2 2 ?
Ag6 S15 Ag5 80.76(14) . 2 ?
Ag5 S15 Ag5 78.9(2) . 2 ?
As5 S16 Ag25 111.3(2) . . ?
As5 S16 Ag18 102.0(2) . 4_556 ?
Ag25 S16 Ag18 137.4(3) . 4_556 ?
As5 S16 Ag28 96.5(2) . . ?
Ag25 S16 Ag28 87.4(2) . . ?
Ag18 S16 Ag28 114.9(2) 4_556 . ?
As5 S16 Ag31 131.1(3) . 4_556 ?
Ag25 S16 Ag31 67.35(16) . 4_556 ?
Ag18 S16 Ag31 70.93(16) 4_556 4_556 ?
Ag28 S16 Ag31 131.1(2) . 4_556 ?
As7 S17 Ag27 112.4(2) 2_556 . ?

As7 S17 Ag28 102.0(2) 2_556 1_545 ?
Ag27 S17 Ag28 93.80(19) . 1_545 ?
As7 S17 Ag19 104.3(2) 2_556 . ?
Ag27 S17 Ag19 125.8(3) . . ?
Ag28 S17 Ag19 116.3(2) 1_545 . ?
Hg2 S18 Ag20 109.11(19) . . ?
Hg2 S18 Ag25 75.4(2) . . ?
Ag20 S18 Ag25 142.9(2) . . ?
Hg2 S18 Ag27 139.4(3) . 1_565 ?
Ag20 S18 Ag27 79.65(15) . 1_565 ?
Ag25 S18 Ag27 75.26(14) . 1_565 ?
Hg2 S18 Ag15 119.48(19) . . ?
Ag20 S18 Ag15 69.90(18) . . ?
Ag25 S18 Ag15 141.46(19) . . ?
Ag27 S18 Ag15 100.90(19) 1_565 . ?
Hg2 S18 Ag28 120.34(19) . . ?
Ag20 S18 Ag28 123.4(3) . . ?
Ag25 S18 Ag28 78.72(14) . . ?
Ag27 S18 Ag28 80.16(13) 1_565 . ?
Ag15 S18 Ag28 62.99(13) . . ?
Hg1 S19 Ag30 121.1(2) . . ?
Hg1 S19 Ag19 72.40(15) . . ?
Ag30 S19 Ag19 140.7(3) . . ?
Hg1 S19 Ag24 126.7(2) . . ?
Ag30 S19 Ag24 112.2(2) . . ?
Ag19 S19 Ag24 65.05(12) . . ?
Hg1 S19 Ag16 125.1(2) . . ?
Ag30 S19 Ag16 76.29(19) . . ?
Ag19 S19 Ag16 67.41(14) . . ?
Ag24 S19 Ag16 64.39(14) . . ?
Hg1 S19 Ag22 74.5(2) . . ?
Ag30 S19 Ag22 123.1(2) . . ?
Ag19 S19 Ag22 95.63(19) . . ?
Ag24 S19 Ag22 79.21(15) . . ?
Ag16 S19 Ag22 143.49(19) . . ?
Ag31 S20 Hg1 119.5(2) 4_546 . ?
Ag31 S20 Ag25 68.92(13) 4_546 1_545 ?
Hg1 S20 Ag25 140.0(3) . 1_545 ?
Ag31 S20 Ag27 135.3(2) 4_546 . ?
Hg1 S20 Ag27 77.0(2) . . ?
Ag25 S20 Ag27 73.55(15) 1_545 . ?
Ag31 S20 Ag21 128.0(3) 4_546 . ?
Hg1 S20 Ag21 70.03(13) . . ?
Ag25 S20 Ag21 139.14(19) 1_545 . ?
Ag27 S20 Ag21 96.28(18) . . ?
Ag31 S20 Ag26 72.4(2) 4_546 . ?
Hg1 S20 Ag26 119.3(2) . . ?
Ag25 S20 Ag26 100.7(2) 1_545 . ?
Ag27 S20 Ag26 139.21(19) . . ?
Ag21 S20 Ag26 61.27(15) . . ?
As5 S21 Ag26 105.0(2) . 4_556 ?
As5 S21 Ag29 97.2(2) . 4_556 ?
Ag26 S21 Ag29 99.2(2) 4_556 4_556 ?
As5 S21 Ag14 102.7(2) . . ?
Ag26 S21 Ag14 119.5(2) 4_556 . ?
Ag29 S21 Ag14 129.1(2) 4_556 . ?
As6 S22 Ag33 114.7(2) . . ?
As6 S22 Ag24 101.7(3) . . ?
Ag33 S22 Ag24 91.14(18) . . ?
As6 S22 Ag14 104.5(2) . . ?
Ag33 S22 Ag14 124.2(3) . . ?

Ag24 S22 Ag14 118.6(2) . . ?
As7 S23 Ag13 104.7(2) . . ?
As7 S23 Ag27 109.4(2) . . ?
Ag13 S23 Ag27 95.0(2) . . ?
As7 S23 Ag15 100.3(2) . 2_546 ?
Ag13 S23 Ag15 118.3(2) . 2_546 ?
Ag27 S23 Ag15 127.5(2) . 2_546 ?
As6 S24 Ag16 101.7(2) . . ?
As6 S24 Ag17 102.4(2) . 2_556 ?
Ag16 S24 Ag17 116.0(2) . 2_556 ?
As6 S24 Ag33 108.3(2) . 2_556 ?
Ag16 S24 Ag33 137.1(2) . 2_556 ?
Ag17 S24 Ag33 86.83(18) 2_556 2_556 ?
As6 S24 Ag30 122.5(3) . . ?
Ag16 S24 Ag30 76.90(17) . . ?
Ag17 S24 Ag30 130.4(2) 2_556 . ?
Ag33 S24 Ag30 61.34(13) 2_556 . ?
As6 S25 Ag34 103.2(2) . . ?
As6 S25 Ag15 105.15(19) . . ?
Ag34 S25 Ag15 96.3(2) . . ?
As6 S25 Ag23 103.0(2) . 2_556 ?
Ag34 S25 Ag23 127.85(19) . 2_556 ?
Ag15 S25 Ag23 118.7(2) . 2_556 ?
As5 S26 Ag22 111.1(2) 4_546 . ?
As5 S26 Ag17 103.8(2) 4_546 . ?
Ag22 S26 Ag17 97.60(19) . . ?
As5 S26 Ag21 98.5(2) 4_546 . ?
Ag22 S26 Ag21 125.8(2) . . ?
Ag17 S26 Ag21 118.61(19) . . ?
As8 S27 Ag22 108.1(2) . . ?
As8 S27 Ag26 101.26(19) . 4_556 ?
Ag22 S27 Ag26 134.6(3) . 4_556 ?
As8 S27 Ag24 99.2(2) . . ?
Ag22 S27 Ag24 88.31(18) . . ?
Ag26 S27 Ag24 120.6(2) 4_556 . ?
As8 S27 Ag31 128.3(3) . . ?
Ag22 S27 Ag31 64.87(14) . . ?
Ag26 S27 Ag31 69.77(15) 4_556 . ?
Ag24 S27 Ag31 130.0(2) . . ?
As8 S28 Ag29 99.6(2) 4_556 4_556 ?
As8 S28 Ag18 105.6(2) 4_556 . ?
Ag29 S28 Ag18 102.3(2) 4_556 . ?
As8 S28 Ag19 103.6(2) 4_556 4_556 ?
Ag29 S28 Ag19 124.0(2) 4_556 4_556 ?
Ag18 S28 Ag19 118.7(2) . 4_556 ?
As7 S29 Ag32 111.9(2) 2_556 . ?
As7 S29 Ag16 102.41(19) 2_556 . ?
Ag32 S29 Ag16 98.7(2) . . ?
As7 S29 Ag21 98.6(2) 2_556 2_556 ?
Ag32 S29 Ag21 128.2(2) . 2_556 ?
Ag16 S29 Ag21 114.9(2) . 2_556 ?
As8 S30 Ag25 108.7(2) 4_556 . ?
As8 S30 Ag23 99.1(2) 4_556 . ?
Ag25 S30 Ag23 133.3(3) . . ?
As8 S30 Ag13 98.7(2) 4_556 1_565 ?
Ag25 S30 Ag13 93.25(18) . 1_565 ?
Ag23 S30 Ag13 119.2(2) . 1_565 ?
As8 S30 Hg2 130.7(2) 4_556 . ?
Ag25 S30 Hg2 67.09(15) . . ?
Ag23 S30 Hg2 66.28(14) . . ?
Ag13 S30 Hg2 130.0(3) 1_565 . ?

Hg2 S31 Ag31 109.57(18) . . ?
Hg2 S31 Ag23 77.05(13) . . ?
Ag31 S31 Ag23 127.3(3) . . ?
Hg2 S31 Ag33 83.4(2) . . ?
Ag31 S31 Ag33 126.9(2) . . ?
Ag23 S31 Ag33 105.7(2) . . ?
Hg2 S31 Ag18 121.0(2) . . ?
Ag31 S31 Ag18 69.53(18) . . ?
Ag23 S31 Ag18 63.67(15) . . ?
Ag33 S31 Ag18 146.68(19) . . ?
Hg2 S31 Ag17 134.4(2) . . ?
Ag31 S31 Ag17 114.2(2) . . ?
Ag23 S31 Ag17 66.92(12) . . ?
Ag33 S31 Ag17 80.53(14) . . ?
Ag18 S31 Ag17 66.19(15) . . ?

_diffrn_measured_fraction_theta_max 0.652
_diffrn_reflns_theta_full 34.79
_diffrn_measured_fraction_theta_full 0.652
_refine_diff_density_max 3.958
_refine_diff_density_min -1.227
_refine_diff_density_rms 0.341