


Redetermination of conichalcite, CaCu(AsO₄)(OH)

Rachel R. Henderson, Hexiong Yang, Robert T. Downs and Robert A. Jenkins

Acta Cryst. (2008). **E64**, i53–i54

This open-access article is distributed under the terms of the Creative Commons Attribution Licence
<http://creativecommons.org/licenses/by/2.0/uk/legalcode>, which permits unrestricted use, distribution, and reproduction in any medium, provided the original authors and source are cited.



Acta Crystallographica Section E: Structure Reports Online is the IUCr's highly popular open-access structural journal. It provides a simple and easily accessible publication mechanism for the growing number of inorganic, metal-organic and organic crystal structure determinations. The electronic submission, validation, refereeing and publication facilities of the journal ensure very rapid and high-quality publication, whilst key indicators and validation reports provide measures of structural reliability. In 2007, the journal published over 5000 structures. The average publication time is less than one month.

Crystallography Journals Online is available from journals.iucr.org

Redetermination of conichalcite, $\text{CaCu}(\text{AsO}_4)(\text{OH})$

Rachel R. Henderson, Hexiong Yang,* Robert T. Downs
 and Robert A. Jenkins

Department of Geosciences, University of Arizona, 1040 E. 4th Street, Tucson, AZ 85721-0077, USA

Correspondence e-mail: hyang@u.arizona.edu

Received 2 July 2008; accepted 29 July 2008

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(\text{As}-\text{O}) = 0.002 \text{ \AA}$; R factor = 0.018; wR factor = 0.038; data-to-parameter ratio = 20.3.

The crystal structure of conichalcite [calcium copper(II) arsenate(V) hydroxide], with ideal formula $\text{CaCu}(\text{AsO}_4)(\text{OH})$, was redetermined from a natural twinned specimen found in the Maria Catalina mine (Chile). In contrast to the previous refinement from photographic data [Qurashi & Barnes (1963). *Can. Mineral.* **7**, 561–577], all atoms were refined with anisotropic displacement parameters and with the H atom located. Conichalcite belongs to the adelite mineral group. The Jahn–Teller-distorted $[\text{CuO}_6]$ octahedra share edges, forming chains running parallel to $[010]$. These chains are cross-linked by eight-coordinate Ca atoms and by sharing vertices with isolated AsO_4 tetrahedra. Of five calcium arsenate minerals in the adelite group, the $[\text{MO}_6]$ ($M = \text{Cu}, \text{Zn}, \text{Co}, \text{Ni}$ and Mg) octahedron in conichalcite is the most distorted, and the donor–acceptor O–H···O distance is the shortest.

Related literature

For background on the adelite mineral family, see: Qurashi & Barnes (1963, 1964); Qurashi *et al.* (1953). For structure refinements in the adelite group, see: Effenberger *et al.* (2002) for adelite, $\text{CaMgAsO}_4(\text{OH})$; Clark *et al.* (1997) and Giuseppetti & Tadini (1988) for austinite, $\text{CaZnAsO}_4(\text{OH})$; Yang *et al.* (2007) for cobaltaustinite, $\text{CaCoAsO}_4(\text{OH})$; Cesbron *et al.* (1987) for nickelaustrinite, $\text{CaNiAsO}_4(\text{OH})$. Correlations between O–H stretching frequencies and O–H···O donor–acceptor distances are given by Libowitzky (1999). Raman spectroscopic data on some minerals of the adelite group have been reported by Martens *et al.* (2003); for general background, see: Robinson *et al.* (1971).

Experimental

Crystal data

$\text{CaCu}(\text{AsO}_4)(\text{OH})$	$V = 395.49 (2) \text{ \AA}^3$
$M_r = 259.57$	$Z = 4$
Orthorhombic, $P2_12_12_1$	Mo $K\alpha$ radiation
$a = 7.3822 (2) \text{ \AA}$	$\mu = 15.03 \text{ mm}^{-1}$
$b = 5.8146 (2) \text{ \AA}$	$T = 293 (2) \text{ K}$
$c = 9.2136 (3) \text{ \AA}$	$0.06 \times 0.05 \times 0.04 \text{ mm}$

Data collection

Bruker APEXII CCD diffractometer	7088 measured reflections
Absorption correction: multi-scan (<i>TWINABS</i> ; Sheldrick, 2008)	1602 independent reflections
$T_{\min} = 0.492$, $T_{\max} = 0.585$	1487 reflections with $I > 2\sigma(I)$
(expected range = 0.461–0.548)	$R_{\text{int}} = 0.023$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.018$	$\Delta\rho_{\text{max}} = 0.63 \text{ e \AA}^{-3}$
$wR(F^2) = 0.038$	$\Delta\rho_{\text{min}} = -0.49 \text{ e \AA}^{-3}$
$S = 1.03$	Absolute structure: Flack (1983),
1602 reflections	644 Friedel pairs
79 parameters	Flack parameter: 0.00 (2)
All H-atom parameters refined	

Table 1
 Selected bond lengths (Å).

$\text{Ca}–\text{O}^5$	2.3626 (13)	$\text{Cu}–\text{O}^5$	1.8855 (16)
$\text{Ca}–\text{O}^3$	2.3995 (17)	$\text{Cu}–\text{O}^1$	2.0666 (16)
$\text{Ca}–\text{O}^4$	2.4818 (16)	$\text{Cu}–\text{O}^1$	2.0688 (15)
$\text{Ca}–\text{O}^2$	2.5178 (17)	$\text{Cu}–\text{O}^3$	2.2976 (15)
$\text{Ca}–\text{O}^4$	2.5281 (16)	$\text{Cu}–\text{O}^4$	2.3882 (14)
$\text{Ca}–\text{O}^1$	2.5462 (14)	$\text{As}–\text{O}^4$	1.6749 (16)
$\text{Ca}–\text{O}^3$	2.5786 (17)	$\text{As}–\text{O}^3$	1.6779 (16)
$\text{Ca}–\text{O}^2$	2.6264 (17)	$\text{As}–\text{O}^2$	1.6796 (16)
$\text{Cu}–\text{O}^5$	1.8850 (15)	$\text{As}–\text{O}^1$	1.7099 (13)

Symmetry codes: (i) $-x + \frac{1}{2}, -y + 1, z - \frac{1}{2}$; (ii) $x + \frac{1}{2}, -y + \frac{3}{2}, -z$; (iii) $x, y + 1, z$; (iv) $-x + 1, y + \frac{1}{2}, -z + \frac{1}{2}$; (v) $x + \frac{1}{2}, -y + \frac{1}{2}, -z$; (vi) $-x, y - \frac{1}{2}, -z + \frac{1}{2}$; (vii) $x - \frac{1}{2}, -y + \frac{1}{2}, -z$; (viii) $-x + \frac{1}{2}, -y, z + \frac{1}{2}$.

Table 2
 Hydrogen-bond geometry (Å, °).

$D–\text{H} \cdots A$	$D–\text{H}$	$\text{H} \cdots A$	$D \cdots A$	$D–\text{H} \cdots A$
$\text{O}^5–\text{H} \cdots \text{O}^2$	0.86 (4)	1.91 (4)	2.678 (2)	149 (3)

Symmetry code: (ix) $x - 1, y, z$.

Data collection: *APEX2* (Bruker, 2003); cell refinement: *SAINT* (Bruker, 2005); data reduction: *SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *XtalDraw* (Downs & Hall-Wallace, 2003); software used to prepare material for publication: *SHELXTL* (Sheldrick, 2008).

The authors gratefully acknowledge support of this study by the RRUFF project.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: WM2185).

References

- Bruker (2003). *SMART*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Bruker (2005). *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Cesbron, F., Ginderow, D., Giraud, R., Pelisson, P. & Pillard, F. (1987). *Can. Mineral.* **25**, 401–407.
- Clark, L. A., Pluth, J. J., Steele, I., Smith, J. V. & Sutton, S. R. (1997). *Mineral Mag.* **61**, 677–683.
- Downs, R. T. & Hall-Wallace, M. (2003). *Am. Mineral.* **88**, 247–250.
- Effenberger, H., Krause, W. & Bernhardt, H. J. (2002). *Exp. Miner. Petrol. Geochem. Abstr.* **9**, 30.
- Flack, H. D. (1983). *Acta Cryst. A* **39**, 876–881.
- Giuseppetti, G. & Tadini, C. (1988). *Neues Jahrb. Mineral. Monatsh.* **1988**, 159–166.
- Libowitzky, E. (1999). *Monatsh. Chem.* **130**, 1047–1059.
- Martens, W., Frost, R. L. & Williams, P. A. (2003). *J. Raman Spectrosc.* **34**, 104–111.
- Qurashi, M. M. & Barnes, W. H. (1963). *Can. Mineral.* **7**, 561–577.
- Qurashi, M. M. & Barnes, W. H. (1964). *Can. Mineral.* **8**, 23–39.
- Qurashi, M. M., Barnes, W. H. & Berry, L. G. (1953). *Am. Mineral.* **38**, 557–559.
- Robinson, K., Gibbs, G. V. & Ribbe, P. H. (1971). *Science*, **172**, 567–570.
- Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
- Yang, H., Costin, G., Keogh, J., Lu, R. & Downs, R. T. (2007). *Acta Cryst. E* **63**, i53–i55.

supplementary materials

Acta Cryst. (2008). E64, i53-i54 [doi:10.1107/S1600536808024173]

Redetermination of conichalcite, CaCu(AsO₄)(OH)

R. R. Henderson, H. Yang, R. T. Downs and R. A. Jenkins

Comment

Minerals of the adelite group crystallize with orthorhombic symmetry in space group $P2_12_12_1$ (Qurashi & Barnes, 1963, 1964) and have a general chemical formula $A^{+2+}M^{2+,3+}(X^{4+,5+,6+}O_4)(OH)$, where $A = Na, Ca, Pb$, $M = Al, Mg, Zn, Mn, Fe, Co, Cu, Ni$, and $X = Si, P, V, As$. There are five calcium arsenates in this group: adelite $CaMgAsO_4(OH)$, austinite $CaZnAsO_4(OH)$, conichalcite $CaCuAsO_4(OH)$, nickelaustinite $CaNiAsO_4(OH)$, and cobaltaustinite, $CaCoAsO_4(OH)$. All structures of these calcium arsenate minerals have been determined previously (Qurashi & Barnes, 1963; Cesbron *et al.*, 1987; Giuseppetti & Tadini, 1988; Clark *et al.*, 1997; Effenberger *et al.*, 2002; Yang *et al.*, 2007). However, in our efforts to understand the relationships between the hydrogen bonding schemes and Raman spectra of hydrous minerals, we noted that the structural information of conichalcite needs to be improved, because this structure was refined by Qurashi & Barnes (1963) with X-ray intensity data collected by Qurashi *et al.* (1953) from precession photographs without anisotropic displacement parameters and localisation of the H atom position.

Conichalcite can be compared with the other Ca-arsenate minerals in the adelite group. The distorted $[CuO_6]$ octahedra (i.e. elongated tetragonal bipyramids) share edges to form chains running parallel to $[010]$, which are cross-linked by Ca atoms and by sharing vertices with isolated AsO_4 tetrahedra (Fig. 1). The principal difference among the five calcium arsenates in the group is manifested in the bonding environments around the octahedrally coordinated M cations. The average $M—O$ bond lengths appear to decrease from $\langle Zn—O \rangle$ ($= 2.106 \text{ \AA}$) in austinite (Clark *et al.*, 1997), to $\langle Cu—O \rangle$ ($= 2.099 \text{ \AA}$) in conichalcite, $\langle Co—O \rangle$ ($= 2.092 \text{ \AA}$) in cobaltaustinite (Yang *et al.*, 2007), $\langle Ni—O \rangle$ ($= 2.085 \text{ \AA}$) in nickelaustinite (Cesbron *et al.*, 1987), and to $\langle Mg—O \rangle$ ($= 2.075 \text{ \AA}$) in adelite (Effenberger *et al.*, 2002). Of these $[MO_6]$ octahedra, the Cu-octahedron, due to its strong Jahn-Teller effect, displays the greatest distortion in terms of the tetragonal elongation and angle variance (Robinson *et al.*, 1971), which are 1.0229 and 23.58, respectively.

The donor-acceptor O5—H···O2 distance in conichalcite is 2.678 (2) \AA , which is the shortest of all five Ca-arsenates in the adelite group [2.723 (2) \AA in austinite (Clark *et al.*, 1997), 2.721 (7) \AA in cobaltaustinite (Yang *et al.*, 2007), 2.73 (1) \AA in nickelaustinite (Cesbron *et al.*, 1987), and 2.766 (2) \AA in adelite (Effenberger *et al.*, 2002)]. As the O—H stretching frequencies (ν_{OH}) increase with the O—H···O distance (Libowitzky, 1999), we should expect the smallest ν_{OH} value for conichalcite and the largest for adelite among the five calcium arsenates in the adelite group. Indeed, the major ν_{OH} band positions determined from Raman spectra for conichalcite and adelite are, respectively, 3158 and 3550 cm^{-1} from Martens *et al.* (2003), or 3161 and 3423 cm^{-1} from the RRUFF project (<http://rruff.info>), with intermediate ν_{OH} values for the other three minerals (austinite, cobaltaustinite, and nickelaustinite).

supplementary materials

Experimental

The conichalcite crystal used in this study is from Maria Catalina mine, Pampa Larga Mining District, Tierra Amarilla, Chile, and is a sample from the RRUFF project (deposition No. R070430; <http://rruff.info>). The chemical composition, $\text{Ca}(\text{Cu}_{0.99}\text{Zn}_{0.01})(\text{AsO}_4)(\text{OH})$, was determined with a CAMECA SX50 electron microprobe (<http://rruff.info>).

Refinement

The final refinement assumed a full occupancy of the metal site by Cu only, as the overall effects of the trace amount of Zn on the final structure results are negligible. In the final stages of the refinement it turned out that the measured crystal was racemically twinned with an approximate twin fraction of 4:1 (BASF = 0.21). The H atom was located from difference Fourier maps and its position was refined freely. The highest residual peak in is located 1.60 Å from the H atom, and the deepest hole is 0.63 Å from the Ca atom.

Figures

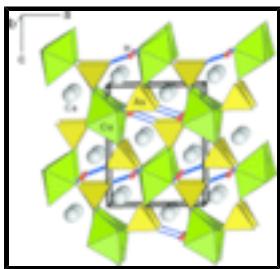


Fig. 1. The crystal structure of conichalcite. Green octahedra, yellow tetrahedra, grey large spheres, and red small spheres represent $[\text{CuO}_6]$, $[\text{AsO}_4]$, Ca, and H, respectively. Hydrogen bonding is indicated with blue lines.

calcium copper(II) arsenate(V) hydroxide

Crystal data

$\text{CaCu}(\text{AsO}_4)(\text{OH})$	$F_{000} = 492$
$M_r = 259.57$	$D_x = 4.359 \text{ Mg m}^{-3}$
Orthorhombic, $P2_12_12_1$	Mo $K\alpha$ radiation
Hall symbol: P 2ac 2ab	$\lambda = 0.71073 \text{ \AA}$
$a = 7.3822 (2) \text{ \AA}$	Cell parameters from 3371 reflections
$b = 5.8146 (2) \text{ \AA}$	$\theta = 3.6\text{--}34.0^\circ$
$c = 9.2136 (3) \text{ \AA}$	$\mu = 15.03 \text{ mm}^{-1}$
$V = 395.49 (2) \text{ \AA}^3$	$T = 293 (2) \text{ K}$
$Z = 4$	Euhedral, equant, green
	$0.06 \times 0.05 \times 0.04 \text{ mm}$

Data collection

Bruker APEX2 CCD diffractometer	1602 independent reflections
Radiation source: fine-focus sealed tube	1487 reflections with $I > 2\sigma(I)$
Monochromator: graphite	$R_{\text{int}} = 0.023$

$T = 293(2)$ K	$\theta_{\max} = 34.0^\circ$
φ and ω scans	$\theta_{\min} = 3.5^\circ$
Absorption correction: multi-scan (TWINABS; Sheldrick, 2008)	$h = -9 \rightarrow 11$
$T_{\min} = 0.492$, $T_{\max} = 0.585$	$k = -9 \rightarrow 9$
7088 measured reflections	$l = -14 \rightarrow 14$

Refinement

Refinement on F^2	All H-atom parameters refined
Least-squares matrix: full	$w = 1/[\sigma^2(F_o^2) + (0.0151P)^2 + 0.1227P]$ where $P = (F_o^2 + 2F_c^2)/3$
$R[F^2 > 2\sigma(F^2)] = 0.018$	$(\Delta/\sigma)_{\max} < 0.001$
$wR(F^2) = 0.038$	$\Delta\rho_{\max} = 0.63 \text{ e \AA}^{-3}$
$S = 1.03$	$\Delta\rho_{\min} = -0.49 \text{ e \AA}^{-3}$
1602 reflections	Extinction correction: SHELXL97 (Sheldrick, 2008), $F_c^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$
79 parameters	Extinction coefficient: 0.0029 (5)
Primary atom site location: structure-invariant direct methods	Absolute structure: Flack (1983), 644 Friedel pairs
Secondary atom site location: difference Fourier map	Flack parameter: 0.00 (2)
Hydrogen site location: difference Fourier map	

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Ca	0.61727 (5)	0.72961 (8)	0.07340 (4)	0.01133 (12)
Cu	-0.00416 (4)	-0.00002 (6)	0.25029 (4)	0.00898 (8)
As	0.36728 (2)	0.26438 (4)	0.08118 (2)	0.00768 (6)
O1	0.18844 (17)	0.2450 (3)	0.19847 (15)	0.0135 (3)
O2	0.5395 (2)	0.3313 (3)	0.19256 (18)	0.0187 (4)
O3	0.3514 (2)	0.4927 (3)	-0.02947 (17)	0.0157 (3)
O4	0.3885 (2)	0.0147 (3)	-0.00782 (15)	0.0145 (4)
O5	-0.13880 (18)	0.2539 (3)	0.31777 (14)	0.0113 (3)
H1	-0.229 (5)	0.232 (6)	0.260 (3)	0.055 (11)*

supplementary materials

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ca	0.01169 (18)	0.0119 (2)	0.01041 (18)	-0.00064 (17)	-0.00072 (13)	0.00020 (18)
Cu	0.00885 (11)	0.00621 (12)	0.01190 (12)	0.00029 (9)	0.00211 (8)	-0.00121 (8)
As	0.00801 (8)	0.00659 (9)	0.00845 (9)	0.00006 (8)	0.00059 (7)	0.00014 (9)
O1	0.0141 (6)	0.0107 (7)	0.0157 (6)	-0.0025 (7)	0.0035 (5)	-0.0006 (7)
O2	0.0146 (7)	0.0212 (9)	0.0205 (8)	-0.0029 (6)	-0.0048 (6)	0.0004 (7)
O3	0.0201 (7)	0.0107 (7)	0.0164 (7)	0.0011 (7)	0.0044 (7)	0.0035 (6)
O4	0.0181 (8)	0.0096 (7)	0.0158 (8)	0.0018 (6)	0.0022 (7)	-0.0018 (6)
O5	0.0106 (5)	0.0102 (6)	0.0132 (6)	0.0000 (8)	0.0002 (5)	-0.0003 (6)

Geometric parameters (\AA , $^\circ$)

Ca—O5 ⁱ	2.3626 (13)	Cu—O5 ^{vi}	1.8855 (16)
Ca—O3 ⁱⁱ	2.3995 (17)	Cu—O1 ^{vi}	2.0666 (16)
Ca—O4 ⁱⁱⁱ	2.4818 (16)	Cu—O1	2.0688 (15)
Ca—O2 ^{iv}	2.5178 (17)	Cu—O3 ^{vii}	2.2976 (15)
Ca—O4 ^v	2.5281 (16)	Cu—O4 ^{viii}	2.3882 (14)
Ca—O1 ^{iv}	2.5462 (14)	As—O4	1.6749 (16)
Ca—O3	2.5786 (17)	As—O3	1.6779 (16)
Ca—O2	2.6264 (17)	As—O2	1.6796 (16)
Cu—O5	1.8850 (15)	As—O1	1.7099 (13)
O5 ⁱ —Ca—O3 ⁱⁱ	75.88 (5)	O4 ^v —Ca—O2	77.15 (5)
O5 ⁱ —Ca—O4 ⁱⁱⁱ	73.62 (5)	O1 ^{iv} —Ca—O2	79.00 (5)
O3 ⁱⁱ —Ca—O4 ⁱⁱⁱ	89.42 (5)	O3—Ca—O2	61.06 (5)
O5 ⁱ —Ca—O2 ^{iv}	151.07 (5)	O5—Cu—O5 ^{vi}	177.68 (6)
O3 ⁱⁱ —Ca—O2 ^{iv}	108.51 (6)	O5—Cu—O1 ^{vi}	98.01 (6)
O4 ⁱⁱⁱ —Ca—O2 ^{iv}	77.79 (5)	O5 ^{vi} —Cu—O1 ^{vi}	84.26 (6)
O5 ⁱ —Ca—O4 ^v	74.41 (5)	O5—Cu—O1	84.21 (6)
O3 ⁱⁱ —Ca—O4 ^v	76.55 (5)	O5 ^{vi} —Cu—O1	93.52 (6)
O4 ⁱⁱⁱ —Ca—O4 ^v	147.36 (3)	O1 ^{vi} —Cu—O1	177.66 (7)
O2 ^{iv} —Ca—O4 ^v	134.48 (5)	O5—Cu—O3 ^{vii}	91.88 (6)
O5 ⁱ —Ca—O1 ^{iv}	141.59 (5)	O5 ^{vi} —Cu—O3 ^{vii}	88.82 (6)
O3 ⁱⁱ —Ca—O1 ^{iv}	73.13 (5)	O1 ^{vi} —Cu—O3 ^{vii}	84.84 (6)
O4 ⁱⁱⁱ —Ca—O1 ^{iv}	127.50 (5)	O1—Cu—O3 ^{vii}	95.85 (6)
O2 ^{iv} —Ca—O1 ^{iv}	62.85 (5)	O5—Cu—O4 ^{viii}	84.76 (6)
O4 ^v —Ca—O1 ^{iv}	76.76 (5)	O5 ^{vi} —Cu—O4 ^{viii}	94.77 (6)
O5 ⁱ —Ca—O3	72.94 (5)	O1 ^{vi} —Cu—O4 ^{viii}	89.81 (6)
O3 ⁱⁱ —Ca—O3	147.75 (2)	O1—Cu—O4 ^{viii}	89.67 (5)
O4 ⁱⁱⁱ —Ca—O3	74.21 (5)	O3 ^{vii} —Cu—O4 ^{viii}	173.23 (6)
O2 ^{iv} —Ca—O3	95.19 (5)	O4—As—O3	113.27 (7)

O4 ^v —Ca—O3	102.41 (5)	O4—As—O2	115.43 (8)
O1 ^{iv} —Ca—O3	138.68 (5)	O3—As—O2	103.94 (8)
O5 ⁱ —Ca—O2	117.86 (6)	O4—As—O1	108.94 (8)
O3 ⁱⁱ —Ca—O2	145.22 (5)	O3—As—O1	112.45 (8)
O4 ⁱⁱⁱ —Ca—O2	124.48 (5)	O2—As—O1	102.33 (7)
O2 ^{iv} —Ca—O2	75.44 (3)		

Symmetry codes: (i) $-x+1/2, -y+1, z-1/2$; (ii) $x+1/2, -y+3/2, -z$; (iii) $x, y+1, z$; (iv) $-x+1, y+1/2, -z+1/2$; (v) $x+1/2, -y+1/2, -z$; (vi) $-x, y-1/2, -z+1/2$; (vii) $x-1/2, -y+1/2, -z$; (viii) $-x+1/2, -y, z+1/2$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D\text{—H}\cdots A$	$D\text{—H}$	$H\cdots A$	$D\cdots A$	$D\text{—H}\cdots A$
O5—H1 \cdots O2 ^{ix}	0.86 (4)	1.91 (4)	2.678 (2)	149 (3)

Symmetry codes: (ix) $x-1, y, z$.

supplementary materials

Fig. 1

