

Jurbanite, a new post-mine aluminum sulfate mineral from San Manuel, Arizona

JOHN W. ANTHONY AND W. JOHN MCLEAN

Department of Geosciences, University of Arizona,
Tucson, Arizona 85721

Abstract

Jurbanite, $\text{AlSO}_4\text{OH}\cdot 5\text{H}_2\text{O}$, is a new species discovered at the San Manuel underground porphyry copper mine, Pinal County, Arizona. It occurs as tiny, clear, colorless crystals in a post-mine stalactitic assemblage which includes epsomite, hexahydrate, pickeringite, starkeyite, and other hydrated sulfates. The crystals are monoclinic and show only {110} and {011}. Morphological measurements gave $\phi(110) = 56.44^\circ$, $\phi(011) = 18.79^\circ$, and $\rho(011) = 34.53^\circ$, from which $a:b:c = .679:1:.647$ and $\beta = 102.2^\circ$. The mineral is biaxial and optically negative with $\alpha = 1.459$, $\beta = 1.473$, $\gamma = 1.483$. The optic angle is $2V(\text{obs}) = 80^\circ$; $2V(\text{calc}) = 80^\circ$. The optical orientation is $b = Y$, $a \wedge Z = -5^\circ$. Unit cell data are: $P2_1/n$; $a = 8.3913(14)$, $b = 12.4846(18)$, $c = 8.1545(13)\text{\AA}$, and $\beta = 101.90(3)^\circ$. The X-ray derived axial ratio is $a:b:c = .67213:1:.65317$. The most intense powder X-ray lines are: 3.723 **100** *130,031*; 4.013 **90** *121,002*; 6.80 **80** *110,011*; 4.954 **80** *120,021*; 4.494 **80** *12\bar{1}*; 5.74 **70** *11\bar{1}*; 3.922 **70** *210*; 3.823 **70** *21\bar{1},012*.

The mineral is brittle and exhibits no discernible cleavage. Specific gravity is $1.786 \pm 0.008(\text{obs})$ and $1.828(\text{calc})$, on the basis of 4 formula units in the cell. The ideal chemical composition is established as $\text{AlSO}_4\text{OH}\cdot 5\text{H}_2\text{O}$ by X-ray proof that jurbanite is identical with that compound (Johansson, 1962). The mineral is named for Mr. Joseph E. Urban who first observed it.

Introduction

The new mineral species herein described is one of at least seven phases in post-mine stalactitic material found on the 2075 foot level of the Magma Copper Company's San Manuel mine, Pinal County, Arizona. The minute, clear crystals were recognized as unusual in such a mineralogical mélange by Mr. Joseph E. Urban, a mineral collector residing in Tucson, Arizona. X-ray diffraction shows the mineral to be identical with the compound $\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8(\text{SO}_4)_2\cdot 2\text{H}_2\text{O}$ (Johansson, 1962). The mineral is named in honor of Mr. Urban. The name and species have been approved by the IMA Commission on New Minerals and Mineral Names.

Occurrence

Jurbanite occurs as small, clear, colorless crystals with at least six other phases in post-mine stalactitic material deposited on lagging and overhead pipes. Other identified phases are epsomite, hexahydrate, pickeringite, starkeyite, and $\text{NH}_4\text{Fe}(\text{SO}_4)_2\cdot 12\text{H}_2\text{O}$. One additional phase, a white, fluffy, powdery mineral, was not identified from its powder pattern and

apparently represents at least one other species, although it may be a mixture of more than one phase. Jurbanite is found in intimate association with the unidentified fluffy mineral as isolated crystals and as clumps of crystals. Exceptional clumps may contain about 50 to 100 tiny individual crystals.

We obtained the specimen containing these minerals only after it had undergone some dehydration. The original material, which apparently formed by precipitation from mine water at about 27°C and 100 percent relative humidity, was probably dominantly epsomite and the precursor to the fluffy mineral, together with minor pickeringite and jurbanite. Dehydration then apparently produced hexahydrate and starkeyite from the epsomite, and the fluffy material from its precursor. It is not certain if jurbanite and pickeringite were original precipitates or the products of the decomposition of original phases; however both occur as clear crystals and an origin as primary precipitates may thus be favored. Jurbanite shows no sign of decomposition under the normal low humidity conditions prevailing in the southwestern desert. The phase $\text{NH}_4\text{Fe}(\text{SO}_4)_2\cdot 12\text{H}_2\text{O}$ occurs as very thin, yellowish crusts on starkeyite. The source of ammo-

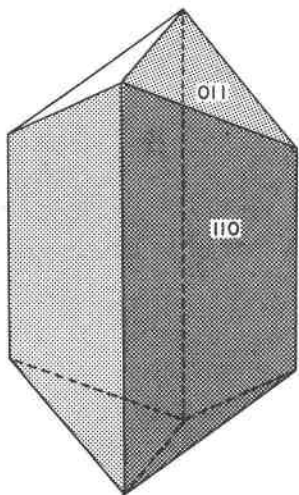


FIG. 1. Typical morphological development of jurbanite.

nium ion is probably NH_4NO_3 used for blasting in the mine.

Physical, crystal, and optical properties

Crystals of jurbanite are colorless and transparent and vary in size from about 0.03 to 0.3 mm in maximum dimension and are generally about twice as long as wide. Crystals are brittle and fracture without apparent cleavage. The Mohs scale hardness is about two and one half. The specific gravity was determined in toluene on the Berman density balance by averaging repeated measurements made with the powder basket attachment on a mass of single crystals weighing 7 mg. A value of 1.786 ± 0.008 was obtained.

The crystals exhibit relatively high luster and, although they appear to be sharp, detailed microscopic,

optical goniometric, and single crystal X-ray examination shows them to be rather imperfect, a crystal usually being composed of an almost parallel intergrowth of several individuals. Crystal morphology is very simple; only the forms $\{110\}$ and $\{011\}$ were observed. $\{110\}$ is usually slightly dominant as shown in Figure 1. The axial ratio and β resulting from the averaging of inferior optical goniometric measurements of six faces on each of four crystals are: $a:b:c = 0.679:1:0.647$ and $\beta = 102.2^\circ$. These are based on average measurements with c polar as follows: $\phi(110) = 56.44^\circ$ (14 faces), $\phi(011) = 18.79^\circ$ (10 faces), and $\rho(011) = 34.53^\circ$.

The optical properties of jurbanite were determined in white light with the aid of a spindle stage. It was found to be biaxial negative with indices of refraction $\alpha = 1.459$, $\beta = 1.473$, and $\gamma = 1.483$, all ± 0.002 . The birefringence is thus 0.024. The optic angle is $2V(\text{obs}) = 80^\circ$; $2V(\text{calc}) = 80^\circ$. The optic orientation is $b = Y$, $a \wedge Z = -5^\circ$, and is shown in Figure 2. Data of the physical parameters are summarized in Table 1.

X-ray diffraction results

A powder diffraction pattern was prepared using $\text{CuK}\alpha$ ($\lambda = 1.5418 \text{ \AA}$) radiation and a 114.59 mm Debye-Scherrer camera with Wilson mounting. Relative intensities were obtained by visual comparison to a standard scale. The resulting pattern was shown to match that of $\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8(\text{SO}_4)_2 \cdot 2\text{H}_2\text{O}$ (Johansson, 1962) by the use of a computer pattern search program (Nichols, private communication).¹ The two patterns are compared in Table 2.

Single crystals were examined by oscillation and Weissenberg techniques using $\text{CuK}\alpha$ radiation. Systematic omissions on Weissenberg films, coupled with the diffraction symmetry $2/m$, showed the space group to be $P2_1/n$. Measurements of 2θ for 97 Weissenberg reflections were used to refine the unit cell by the method of least squares. A quartz single crystal ($a = 4.9131 \text{ \AA}$ at 22°C) was used for film calibration. The cell dimensions are: $a = 8.3913(14)$, $b = 12.4846(18)$, $c = 8.1545(13) \text{ \AA}$, and $\beta = 101.90(3)^\circ$. The X-ray axial ratio is $a:b:c = 0.67213:1:0.65317$.

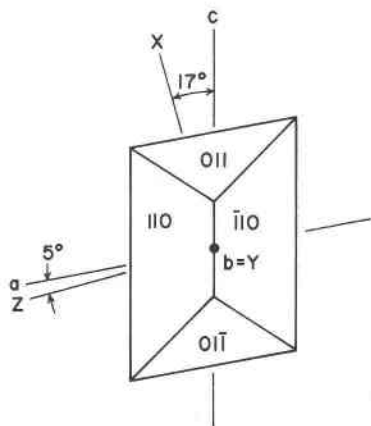


FIG. 2. The optic orientation of jurbanite.

¹ Our initial search through the JCPDS file failed to show a match of the jurbanite pattern with any listed compound. Subsequently, Monte C. Nichols of Sandia Laboratories, Livermore, California, processed the pattern data through his search program and obtained a match with the compound $\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8(\text{SO}_4)_2 \cdot 2\text{H}_2\text{O}$. Our failure to establish the match initially seems to arise from the fact that Johansson (1962) reported the intensities of the eight strongest lines as "S".

TABLE 1. Data for Jurbanite

Crystal system	Monoclinic	Forms	{110}, {011}
Color	Colorless	Hardness	2-1/2
α	1.459	Optic sign	Negative
β	1.473	B	.024
γ	1.483	2V	80°
Optic orientation	b = Y, aAz = -5°		
a	8.3913(14)Å*	B	101.90°(3)
b	12.4846(18)	Cell volume	835.92
c	8.1545(13)		
a:b:c (X-ray)	.67213:1:65317		
a:b:c (morphology)	.679:1:647		
Space group	P2 ₁ /n		
Composition	AlSO ₄ OH·5H ₂ O	Cell content	4
Density(obs.)	1.786(8)	Density(calc.)	1.828

* Numbers in parentheses are estimated standard errors and refer to the last places.

These results are compared with those of Johansson (1962) in Table 3.

Chemical composition

Comparison of the X-ray diffraction data proves beyond a reasonable doubt that jurbanite is chem-

TABLE 2. Comparison of X-Ray Data of Al₂(OH)₂(H₂O)₈(SO₄)₂·2H₂O and Jurbanite

Al ₂ (OH) ₂ (H ₂ O) ₈ (SO ₄) ₂ ·2H ₂ O			Jurbanite				
I(obs)	d(obs)	hkl	I(obs)	I(calc)	d(obs)	d(calc)	hkl
m	6.90	011		43	6.86	6.86	110
s	6.76	110	80B	58	6.72	6.72	011
vw	6.44	101		2	6.42	6.42	101
s	5.73	111	70	72	5.74	5.71	111
vwv	5.22	101	10	14	5.23	5.21	101
m	4.976	021		36	4.969	4.969	120
m	4.935	120	80	64	4.954	4.917	021
vwv	4.828	111		8	4.809	4.809	111
s	4.481	121	80	83	4.494	4.476	121
s	4.002	121		55	4.013	4.000	121
s	3.992	200		65	3.990	3.990	002
s	3.909	012	70	74	3.922	3.900	210
m	3.817	112	70	44	3.811	3.811	211
w	3.807	210		22	3.823	3.800	012
vw	3.748	211		9	3.740	3.740	112
s	3.713	031		100	3.723	3.712	130
m	3.692	130	100	31	3.692	3.690	031
w	3.365	220	30	16	3.376	3.361	022
w	3.218	211	25	7	3.227	3.216	112
m	3.114	212	40	25	3.127	3.110	212
vwv	2.939	221		3	2.937	2.937	122
vwv	2.908	140		3	2.917	2.917	140
m	2.887	132	70B	7	2.907	2.907	041
				20	2.884	2.884	231
				12	2.880	2.880	032
				4	2.856	2.856	222
m	2.857	222		13	2.854	2.854	132
w	2.709	113	30	14	2.714	2.704	311
s	2.602	310		7	2.601	2.601	013
s	2.602	231	50	18	2.612	2.599	132
w	2.554	212		25	2.550	2.550	212
vw	2.546	232	50	6	2.542	2.542	232
vwv	2.466	213		6	2.462	2.462	312
vw	2.444	241	30	6	2.442	2.442	142
vwv	2.432	103		7	2.439	2.439	301
vw	2.407	312		3	2.430	2.430	213
			20	14	2.412	2.404	222
			5	1	2.337	2.330	322
			10	3	2.291	2.287	330
			10	3	2.277	2.277	241
			10	4	2.244	2.241	033
				2	2.238	2.238	242
vwv	2.144	303	20	2	2.151	2.150	332
vwv	2.131	332		10	2.141	2.141	303
				7	2.129	2.129	233

TABLE 2, Continued

I(obs)	d(obs)	hkl	I(obs)	I(calc)	d(obs)	d(calc)	hkl
vwv	2.119	250		6		2.116	052
		152		6		2.110	313
		251	40	4	2.112	2.106	152
vwv	2.108	133		15		2.104	331
			5	3	2.055	2.058	340
vwv	2.027	323		3		2.025	323
		340		1		2.024	043
vwv	2.010	411		1		2.011	114
		152	40B	9	2.009	2.008	251
				3		2.001	402
vw	2.001	242		7		2.000	242
		251		9		1.997	152
vwv	1.959	402		5	1.967	1.957	342
		243		5			
vwv	1.938	412		2		1.937	124
vwv	1.923	143	5	5	1.923	1.922	341
m	1.900	420					
		341	30	14	1.905	1.898	143
		162					
vwv	1.848	260	10	3	1.845	1.845	062
		053					
w	1.800	430					
		314	40	13	1.801	1.797	413
m	1.766	343					
		261	30	10	1.767	1.764	162
		262					
vwv	1.746	153		8		1.744	423
		324	35	3	1.746	1.743	170

(Plus 21 additional lines to d = 1.299.)

Data for Al₂(OH)₂(H₂O)₈(SO₄)₂·2H₂O are from Johansson (1962).

Observed data for jurbanite were obtained with Ni filtered CuK α radiation in a 114.59 mm camera with Wilson mounting. Calculated intensities are based on the crystal structure of Johansson, and calculated d are based on the cell found in the present study. Indexing of the jurbanite pattern is based on the conventional (c<a) cell used in the present work. The transformation matrix from Johansson's cell to the jurbanite cell is 001/010/100.

ically and structurally identical with the compound described by Johansson (1962). Further chemical verification was obtained from qualitative chemical tests. An emission spectrographic analysis showed major Al, very minor Fe, Mg, Mn, Si, Cu, and Ca, and traces of B, Ni, and Cr.² Loss on ignition is comparable to the water content found by Johansson in his analysis of the compound. A qualitative microchemical test for selenium gave a positive result. Examination of the unit cell parameters of the sulfate and of the selenate isotype, Al₂(OH)₂(H₂O)₈(SeO₄)₂·2H₂O, for which a = 8.26, b = 12.76, c = 8.48Å, and β = 102.1° (Johansson, 1962), shows that jurbanite cannot contain more than small amounts of Se. Cast in conventional mineralogical form, the idealized composition of jurbanite is 4[AlSO₄OH·5H₂O]. The density calculated on the basis of this unit cell content is 1.828. The lower value obtained by the measurement of specific gravity (1.786) in part may be due to partial dehydration of the mineral which was exposed to

² Spectrographic analysis and loss on ignition performed by Pacific Spectrochemical Laboratory, Los Angeles.

TABLE 3. Comparison of Unit Cell and Axial Ratio of $\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8(\text{SO}_4)_2 \cdot 2\text{H}_2\text{O}$ and Jurbanite

$\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8(\text{SO}_4)_2 \cdot 2\text{H}_2\text{O}$ (Johansson, 1962)		Jurbanite	
		X-ray	morphology
$\frac{a}{b}$	8.15Å	$\frac{c}{b}$	8.1545Å
$\frac{c}{b}$	12.48	$\frac{a}{b}$	12.4846
β	101.9°	$\frac{c}{b}$	8.3913
$\frac{a/b}{c/b}$.6530	β	101.90°
$\frac{c/b}{a/b}$.6731	$\frac{c/b}{a/b}$	102.2°
		$\frac{a/b}{c/b}$.647
		$\frac{c/b}{a/b}$.679

conditions of low atmospheric relative humidity for some months before the measurements were made.

Note added in proof

Khademite (Bariand, Berthelon, Cesbron, and Sadrzadeh, 1973) has the same chemical formula as jurbanite, and the two are thus dimorphs.

Acknowledgments

We are grateful to Monte Nichols for identifying the powder pattern of the new mineral. We also thank Joseph Urban for calling our attention to the species and for providing the specimen material. Lloyd Thomas, Chief Geologist of the Magma Copper Company's San Manuel mine, kindly arranged for us to visit and sample the underground locality.

References

- BARIAND, PIERRE, JEAN-PAUL BERTHELON, FABIEN CESBRON, AND MANOUCHER SADRZADEH (1973) Un nouveau sulfate hydrate d'aluminium: la khademite de Saghand (Iran). *C. R. Acad. Sci. Paris*, **277D**, 1585-1588.
- JOHANSSON, GEORG (1962) The crystal structure of $[\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8](\text{SO}_4)_2 \cdot 2\text{H}_2\text{O}$ and $[\text{Al}_2(\text{OH})_2(\text{H}_2\text{O})_8](\text{SeO}_4)_2 \cdot 2\text{H}_2\text{O}$. *Acta Chem. Scand.* **16**, 403-420.

Manuscript received, July 28, 1975; accepted for publication, September 24, 1975.