

# Heyerdahlite, $\text{Na}_3\text{Mn}_7\text{Ti}_2(\text{Si}_4\text{O}_{12})_2\text{O}_2(\text{OH})_4\text{F}(\text{H}_2\text{O})_2$ , a new mineral of the astrophyllite supergroup from the Larvik Plutonic complex, Norway: Description and crystal structure

ELENA SOKOLOVA<sup>1,\*</sup>, MAXWELL C. DAY<sup>1</sup>, FRANK C. HAWTHORNE<sup>1</sup> AND ROY KRISTIANSEN<sup>2</sup>

<sup>1</sup> Department of Geological Sciences, University of Manitoba, 125 Dysart Road, Winnipeg, MB, R3T 2N2 Canada

<sup>2</sup> PO Box 32, N-1650, Sellesbakk, Norway

[Received 12 April 2017; Accepted 13 June 2017; Associate Editor: Ed Grew]

## ABSTRACT

Heyerdahlite, ideally  $\text{Na}_3\text{Mn}_7\text{Ti}_2(\text{Si}_4\text{O}_{12})_2\text{O}_2(\text{OH})_4\text{F}(\text{H}_2\text{O})_2$ , is a new astrophyllite-supergroup mineral from the Larvik Plutonic complex, Norway. Heyerdahlite was found in a nepheline-syenite pegmatite with albite, aegirine, hastingsite/magnesio-hastingsite, kupletskite, lorenzenite and pyrophanite. Heyerdahlite is colourless to pale brown, transparent and has a vitreous lustre. Mohs hardness is 3,  $D_{\text{calc.}} = 3.245 \text{ g/cm}^3$ . Heyerdahlite is biaxial (+),  $\alpha = 1.694(2)$ ,  $\beta = 1.710(5)$ ,  $\gamma = 1.730(5)$ ,  $2V_{\text{meas.}} = 80(4)^\circ$  and  $2V_{\text{calc.}} = 84.5^\circ$ . Cleavage is perfect parallel to  $\{001\}$ . The empirical formula based on 32.18 (O + F) apfu is  $(\text{Na}_{1.18}\text{K}_{0.68}\text{Rb}_{0.12}\text{Cs}_{0.01}\text{Pb}_{0.01})_{\Sigma 2}\text{Na}_{1.00}(\text{Mn}_{6.29}\text{Zn}_{0.23}\text{Mg}_{0.07}\text{Zr}_{0.04}\text{Fe}_{0.03}^{2+}\text{Ca}_{0.01}\text{Na}_{0.34})_{\Sigma 7.01}(\text{Ti}_{1.78}\text{Nb}_{0.17}\text{Mg}_{0.03}\text{Zr}_{0.02})_{\Sigma 2}(\text{Si}_{8.03}\text{O}_{24})\text{O}_2[(\text{OH})_{3.92}\text{F}_{0.08}]_{\Sigma 4}\text{F}_{1.00}[\text{H}_2\text{O}]_{1.18}\square_{0.82}]_{\Sigma 2}$ , for  $Z = 1$ . Heyerdahlite is triclinic, space group  $P1$ ,  $a = 5.392(2)$ ,  $b = 11.968(4)$ ,  $c = 11.868(4) \text{ \AA}$ ,  $\alpha = 112.743(8)$ ,  $\beta = 94.816(7)$ ,  $\gamma = 103.037(8)^\circ$  and  $V = 675.6(7) \text{ \AA}^3$ . The crystal structure was refined to  $R_1 = 4.44\%$  for 3577 unique ( $F_o > 4\sigma F$ ) reflections. In the crystal structure of heyerdahlite, there are four  $^{[4]}T$  sites occupied by Si. The  $^{[6]}D$  site is occupied mainly by Ti. The  $\text{T}_4\text{O}_{12}$  astrophyllite ribbons composed of  $\text{SiO}_4$  tetrahedra and D octahedra constitute the H (Heteropolyhedral) sheet. In the O (Octahedral) sheet, there are four Mn-dominant  $^{[6]}M(1-4)$  sites. Two H sheets and one central O sheet form the HOH block, and adjacent HOH blocks link via a common  $\text{X}_D^{\text{p}}$  anion of the two D octahedra. In the I (Intermediate) block between HOH blocks, there are two interstitial cation sites,  $A$  and  $B$ , and a  $W_A$  site, partly occupied by  $\text{H}_2\text{O}$ . The  $A$  site splits into two sites,  $^{[12]}A(1)$  and  $^{[6]}A(2)$ , partly occupied by K and Na, respectively, with  $A(1)-A(2) = 0.754 \text{ \AA}$ . The aggregate content of the  $A$  site is ideally  $\text{Na}_2$  apfu. The  $^{[10]}B$  site is occupied by Na. The  $W_A$  site is ideally occupied by  $(\text{H}_2\text{O})_2$  pfu. The mineral is named after the Norwegian explorer Thor Heyerdahl (1914–2002), who was born in Larvik.

**KEYWORDS:** heyerdahlite, new mineral, astrophyllite supergroup, Larvik Plutonic complex, electron microprobe analysis, crystal structure, FTIR spectroscopy.

## Introduction

HEYERDAHLITE, ideally  $\text{Na}_3\text{Mn}_7\text{Ti}_2(\text{Si}_4\text{O}_{12})_2\text{O}_2(\text{OH})_4\text{F}(\text{H}_2\text{O})_2$ , is a new astrophyllite-supergroup mineral from the Larvik Plutonic complex, Norway. The mineral is named heyerdahlite (pronunciation is HEY-AIR-DAL-'AIT) after the Norwegian explorer

Thor Heyerdahl (1914–2002), who was born and raised in the city of Larvik, which is within the Larvik Plutonic complex. The new mineral species and its name were approved by the Commission on New Minerals, Nomenclature and Classification of the International Mineralogical Association (IMA2016-108). The holotype specimen of heyerdahlite has been deposited in the collections of Royal Ontario Museum, Toronto, Ontario, Canada; the accession number is M57516. Here we report the description and crystal structure of heyerdahlite.

\*E-mail: [elena.sokolova@umanitoba.ca](mailto:elena.sokolova@umanitoba.ca)

<https://doi.org/10.1180/minmag.2017.081.051>

## The astrophyllite supergroup

General information on the astrophyllite supergroup (Sokolova *et al.*, 2017a), is given here to explain the site nomenclature and details of the structure used in the sections on infrared spectroscopy, chemical analysis and structure refinement below. The HOH block is the main structural unit in all astrophyllite-supergroup structures; it consists of three H–O–H sheets where the  $T_4O_{12}$  astrophyllite ribbons occur in the H sheets. In each structure, HOH blocks alternate with **I** (Intermediate) blocks along [001].

The general formula for the astrophyllite-supergroup minerals is of the form  $A_{2p}B_rC_7D_2(T_4O_{12})_2IX_{D2}^O X_{A4}^O X_{Dn}^P W_{A2}$ , where C [cations at the M(1–4) sites in the O sheet] =  $Fe^{2+}$ , Mn, Na, Mg, Zn,  $Fe^{3+}$ , Ca, Zr and Li; D (cations in the H sheets) =  $[^{6,5}]Ti$ , Nb, Zr,  $Sn^{4+}$ ,  $[^5]Fe^{3+}$ , Mg and Al; T = Si with minor Al;  $A_{2p}B_rIW_{A2}$  (**I** block) where p = 1 or 2; r = 1 or 2; A = K, Cs, Ba,  $H_2O$ , Li, Rb,  $Pb^{2+}$ , Na and  $\square$ ; B = Na, Ca, Ba,  $H_2O$  and  $\square$ ; I represents the composition of the central part of the **I** block (excluding peripheral layers of the form  $A_{2p}B_rW_{A2}$ ), e.g.  $(PO_4)_2(CO_3)$  (devitoite);  $X_D^O = O$ ;  $X_A^O = OH$  or F;  $X_D^P = F, O, OH, H_2O$  and  $\square$ , where n = 0, 1 or 2 for  $(X_D^P)_n$ ;  $W_A = H_2O$  or  $\square$ .

The thirteen minerals of the astrophyllite supergroup are divided into three groups based on (1) the type of self-linkage of HOH blocks, i.e. (a) HOH blocks link directly via  $D-X_D^P-D$  bridges, or (b) HOH blocks do not link directly; and (2) the dominant cation of the O sheet [the C group:  $C_7$  apfu (atoms per formula unit)]. In the astrophyllite group, HOH blocks connect via  $D-X_D^P-D$  bridges,  $Fe^{2+}$  is dominant at  $C_7$ ; in the kupletskite group, HOH blocks connect via  $D-X_D^P-D$  bridges,  $Mn^{2+}$  is dominant at  $C_7$ ; in the devitoite group, HOH blocks do not connect via  $D-X_D^P-D$  bridges. The ideal structural formulae for the astrophyllite-supergroup minerals are given in Table 1.

## Occurrence and mineral association

Heyerdahlite occurs in the Bratthagen nepheline syenite pegmatite of the Larvik Plutonic complex, Norway (Larsen 2010, 2013; Khomyakov *et al.*, 2011; Oberti *et al.*, 2014). The pegmatite is situated in a road cut on the main road RV8, ~200 m SE of the Bratthagen farm (59°09'26"N 10°00'39"E) in Lågendalen, Hedrum, Vestfold County, Norway.

The lardalite/foyaite rocks at Lågendalen contain the last segment of the Larvik Plutonic complex.

The foyaite are younger than the lardalites and belong to the igneous rock complex of the Oslo region. The extreme mineral association in the Bratthagen syenite pegmatite shows mineralogical and geochemical features rather different from most of the syenite pegmatites in the Larvik Plutonic complex. Textural features suggest that these pegmatites are related to the host foyaite, which is younger than the lardalites. The mineral association is diagnostic of agpaitic pegmatites (Dahlgren, 2010). The locality has been protected by law since 1984, and mineral collecting is now prohibited.

Heyerdahlite formed as a late-stage hydrothermal mineral in a nepheline-syenite pegmatite. It occurs as radiating fans up to 2 mm in diameter, consisting of transparent colourless to pale-brown elongated lath-like crystals (Figs 1a,b). The heyerdahlite crystals are ~1 mm long and only 50  $\mu m$  wide. Associated minerals are albite, aegirine, hastingsite/magnesio-hastingsite, kupletskite, lorenzenite and pyrophanite.

Almost 60 different species have been characterized in this area, many of which are typical of late-stage mineralization in highly evolved agpaitic intrusions (Oberti *et al.*, 2014).

## Physical properties

Heyerdahlite is colourless to pale brown, it is transparent and has a vitreous lustre and a pale-brown streak. Cleavage is perfect parallel to {001}, heyerdahlite is brittle and has a hackly fracture. The Mohs hardness is 3. Heyerdahlite does not fluoresce under ultraviolet light. We did not measure density due to paucity of material,  $D_{calc.} = 3.245 \text{ g/cm}^3$  (from the empirical formula). A spindle stage was used to orient a crystal for measurement of refraction indices and 2V by the extinction-curve method (Bartelmehs *et al.*, 1992). Heyerdahlite is biaxial (+), with refractive indices ( $\lambda = 589 \text{ nm}$ )  $\alpha = 1.694(2)$ ,  $\beta = 1.710(5)$ ,  $\gamma = 1.730(5)$ ;  $2V_{meas.} = 80(4)^\circ$  and  $2V_{calc.} = 84.5^\circ$ . The optical orientation was determined by transferring the crystal from the spindle stage to a single-crystal diffractometer and measuring the relative axial relations by X-ray diffraction; these values are given in Table 2. The dispersion is strong,  $r > v$ . It is pleochroic according to the scheme  $X > Y > Z$ , where  $X$  = yellowish brown,  $Y$  = brownish yellow and  $Z$  = pale yellow. The compatibility index ( $1 - Kp/Kc$ ) = 0.028 (for  $D_{calc.}$ ) is rated as excellent (Mandarino, 1981).

TABLE 1. Ideal structural formulae of the form  $A_{2p}B_rC_7D_2(T_4O_{12})_2IX_{D2}^OX_{A4}^OX_{Dn}^PW_{A2}$  for the astrophyllite-supergroup minerals\*.

| Mineral                    | Ideal structural formula |              |                       |             |                  |                  |            |            |                |            | Ref.** |   |   |          |
|----------------------------|--------------------------|--------------|-----------------------|-------------|------------------|------------------|------------|------------|----------------|------------|--------|---|---|----------|
|                            | $A_2$                    | B            | $C_7$                 | $D_2$       | $(T_4O_{12})_2$  | I                | $X_{D2}^O$ | $X_{A4}^O$ | $X_D^P$        | $W_{A2}$   | p      | r | n |          |
| <b>Astrophyllite group</b> |                          |              |                       |             |                  |                  |            |            |                |            |        |   |   |          |
| Astrophyllite              | $K_2$                    | Na           | $Fe_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | F              |            | 1      | 1 | 1 | (1)      |
| Niobophyllite              | $K_2$                    | Na           | $Fe_7^{2+}$           | $(Nb,Ti)_2$ | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | (O,F)          |            | 1      | 1 | 1 | (1)      |
| Zircophyllite              | $K_2$                    | Na           | $Fe_7^{2+}$           | $Zr_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | F              |            | 1      | 1 | 1 | (2)      |
| Tarbagataite               | $(K\Box)$                | Ca           | $Fe_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | (OH)           |            | 1      | 1 | 1 | (3)      |
| Nalivkinitite              | $Li_2$                   | Na           | $Fe_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | F              | $(H_2O)_2$ | 1      | 1 | 1 | (4)      |
| Bulgakite                  | $Li_2$                   | (Ca,Na)      | $Fe_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | (O,F)          | $(H_2O)_2$ | 1      | 1 | 1 | (4)      |
| <b>Kupletskite group</b>   |                          |              |                       |             |                  |                  |            |            |                |            |        |   |   |          |
| Kupletskite                | $K_2$                    | Na           | $Mn_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | F              |            | 1      | 1 | 1 | (5)      |
| Niobokupletskite           | $K_2$                    | Na           | $Mn_7^{2+}$           | $(Nb,Ti)_2$ | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | (O,F)          |            | 1      | 1 | 1 | (6)      |
| Kupletskite-(Cs)           | $Cs_2$                   | Na           | $Mn_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | F              |            | 1      | 1 | 1 | (1)      |
| Heyerdahlite               | $Na_2$                   | Na           | $Mn_7^{2+}$           | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | F              | $(H_2O)_2$ | 1      | 1 | 1 | (7)      |
| <b>Devitoite group</b>     |                          |              |                       |             |                  |                  |            |            |                |            |        |   |   |          |
| Devitoite                  | $Ba_4$                   | $Ba_2$       | $Fe_7^{2+}$           | $Fe_2^{3+}$ | $(Si_4O_{12})_2$ | $(PO_4)_2(CO_3)$ | $O_2$      | $(OH)_4$   | $\Box_2$       |            | 2      | 2 | 0 | (8)      |
| Sveinbergeite              | $(H_2O)_2$               | $[Ca(H_2O)]$ | $(Fe_6^{2+} Fe^{3+})$ | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | $[(OH)(H_2O)]$ |            | 1      | 2 | 2 | (9)      |
| Lobanovite                 | $K_2$                    | Na           | $(Fe_4^{2+} Mg_2Na)$  | $Ti_2$      | $(Si_4O_{12})_2$ |                  | $O_2$      | $(OH)_4$   | $\Box$         |            | 1      | 1 | 0 | (10, 11) |

\*After Sokolova *et al.* (2017a);\*\*References (the most recent work on the structure): (1) Cámara *et al.* (2010); (2) Sokolova and Hawthorne (2016); (3) Stepanov *et al.* (2012); (4) Agakhanov *et al.* (2016); (5) Piilonen *et al.* (2000); (6) Piilonen *et al.* (2001); (7) this work; (8) Kampf *et al.* (2010); (9) Khomyakov *et al.* (2011); (10) Sokolova and Cámara (2008); (11) Sokolova *et al.* (2017b).



FIG. 1. (a) A fan of transparent colourless to pale-brown elongated crystals of heyerdahlite on albite, the black crystal is aegirine; (b) scanning electron microscopy image of heyerdahlite crystals.

### Infrared spectroscopy

The Fourier-transform infrared (FTIR) spectra of heyerdahlite (Fig. 2) were collected on crystal fragments using a Bruker Hyperion 2000 IR microscope equipped with a liquid-nitrogen-cooled MCT detector (University of Manitoba). A single-crystal fragment was pressed into a homogeneous film with a thickness of 10  $\mu\text{m}$  with a diamond anvil and used to collect the powder spectrum shown in Fig. 2a. Single-crystal

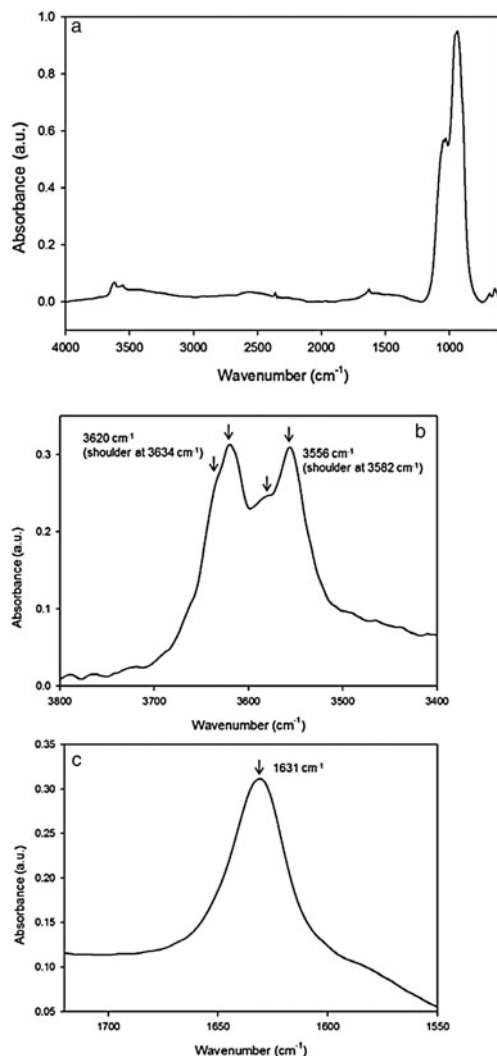


FIG. 2. FTIR spectra of heyerdahlite collected on (a) powder and (b,c) a single crystal.

fragments with thicknesses of  $\sim 50 \mu\text{m}$  were used to collect the spectra shown in Figs 2b and 2c. Data over the range 4000–650  $\text{cm}^{-1}$  were obtained by averaging 100 scans with a resolution of 4  $\text{cm}^{-1}$ . Base-line correction was carried out using the OPUS spectroscopic software (Bruker Optic GmbH).

In the powder (Fig. 2a) and single-crystal (Figs. 2b,c) FTIR spectra, two strong OH bands are observed at  $\sim 3620 \text{ cm}^{-1}$  (with a shoulder at  $\sim 3634 \text{ cm}^{-1}$ ) and  $\sim 3556 \text{ cm}^{-1}$  (with a shoulder at

TABLE 2. Optical orientation ( $^\circ$ ).

|          | <i>a</i> | <i>b</i> | <i>c</i> |
|----------|----------|----------|----------|
| <i>X</i> | 89.9     | 23.9     | 95.1     |
| <i>Y</i> | 86.5     | 110.1    | 9.8      |
| <i>Z</i> | 3.5      | 102.0    | 98.3     |

$\sim 3582\text{ cm}^{-1}$ ) (Figs 2a,b). These two bands correspond to principal OH stretching bands where OH groups occur at the  $X_A^O(1)$  and  $X_A^O(2)$  sites. There is a sharp peak at  $\sim 1631\text{ cm}^{-1}$  (Fig. 2c) that may be assigned to an H–O–H bending mode of an  $\text{H}_2\text{O}$  group. The corresponding  $\text{H}_2\text{O}$  stretching bands are extremely broad (at  $\sim 3440\text{ cm}^{-1}$ ) (Fig. 2b) and underlie the sharper OH-stretching bands. In the lower-frequency region (Fig. 2a), two strong bands at  $\sim 1040$  and  $\sim 940\text{ cm}^{-1}$  may be assigned to symmetric and asymmetric Si–O stretches and a less intense, broad band at  $\sim 635\text{ cm}^{-1}$  (with shoulder at  $\sim 685\text{ cm}^{-1}$ ) is due to an Si–O–Si deformation. Multiple low-intensity bands observed in the range  $2380\text{--}2301\text{ cm}^{-1}$  are due to atmospheric  $\text{CO}_2$  transitions (Fig. 2a).

### Chemical analysis

A crystal of heyerdahlite was analysed with a Cameca SX-100 electron-microprobe (University of Manitoba) operating in wavelength-dispersion mode with an accelerating voltage of 15 kV, a specimen current of 15 nA, a beam size of  $10\text{ }\mu\text{m}$  and count times on peak and background of 20 and 10 s, respectively. The following standards were

used: Si and Ca: diopside; F: fluoro-riebeckite; Na: albite; Nb:  $\text{Ba}_2\text{NaNb}_5\text{O}_{15}$ ; Fe: fayalite; Mn: spessartine; Zr: zircon; Ti: titanite; Pb: PbTe; Mg: forsterite; Zn: gahnite; Cs: pollucite; K: orthoclase; and Rb: Rb-leucite. Tantalum, Al, Sn and Cr were sought but not detected. Data were reduced using the  $\phi(\rho Z)$  procedure of Pouchou and Pichoir (1985). The chemical composition of heyerdahlite is the mean of 8 determinations and is given in Table 3. The amount of  $\text{H}_2\text{O}$  was calculated from structure refinement. Table 3 gives the empirical formula unit based on 32.18 (O + F) apfu, with constraints  $\text{OH} + \text{F} = 5\text{ pfu}$  and  $\text{H}_2\text{O} = 1.18\text{ pfu}$ :  $(\text{Na}_{1.18}\text{K}_{0.68}\text{Rb}_{0.12}\text{Cs}_{0.01}\text{Pb}_{0.01})_{\Sigma 2}\text{Na}_{1.00}(\text{Mn}_{6.29}\text{Zn}_{0.23}\text{Mg}_{0.07}\text{Zr}_{0.04}\text{Fe}_{0.03}^{2+}\text{Ca}_{0.01}\text{Na}_{0.34})_{\Sigma 7.01}(\text{Ti}_{1.78}\text{Nb}_{0.17}\text{Mg}_{0.03}\text{Zr}_{0.02})_{\Sigma 2}(\text{Si}_{8.03}\text{O}_{24})\text{O}_2[(\text{OH})_{3.92}\text{F}_{0.08}]_{\Sigma 4}\text{F}_{1.00}[(\text{H}_2\text{O})_{1.18}\square_{0.82}]_{\Sigma 2}$  for  $Z = 1$ . The basis of 32.18 (anions +  $\text{H}_2\text{O}$  groups) for calculation of the empirical formula unit was derived from the structure-refinement results: 31 anions (the established basis for calculation of the formula unit for the astrophyllite and kupletskite groups of the astrophyllite-superfgroup minerals, Piilonen *et al.*, 2003) plus 1.18  $\text{H}_2\text{O}$  pfu. Note that 1.18  $\text{H}_2\text{O}$  pfu at the  $W_A$  site is necessary to complete the coordination of  $\text{Na}_{1.18}$  apfu at the  $A(2)$  site (see below).

TABLE 3. Chemical composition (wt.%) and unit formula\* (apfu) for heyerdahlite.

| Constituent               |       |                  | Atoms per formula unit |                           |      |
|---------------------------|-------|------------------|------------------------|---------------------------|------|
| $\text{Nb}_2\text{O}_5$   | 1.67  | Si               | 8.03                   | Ti                        | 1.78 |
| $\text{ZrO}_2$            | 0.53  |                  |                        | Nb                        | 0.17 |
| $\text{TiO}_2$            | 10.37 | Mn               | 6.29                   | Mg                        | 0.03 |
| $\text{SiO}_2$            | 35.17 | Na               | 0.34                   | Zr                        | 0.02 |
| PbO                       | 0.22  | Zn               | 0.23                   | $\Sigma\text{D}$          | 2.00 |
| ZnO                       | 1.34  | Mg               | 0.07                   |                           |      |
| FeO                       | 0.14  | Zr               | 0.04                   | Na                        | 1.18 |
| MnO                       | 32.50 | $\text{Fe}^{2+}$ | 0.03                   | K                         | 0.68 |
| CaO                       | 0.03  | Ca               | 0.01                   | Rb                        | 0.12 |
| MgO                       | 0.30  | $\Sigma\text{M}$ | 7.01                   | Cs                        | 0.01 |
| $\text{Cs}_2\text{O}$     | 0.12  |                  |                        | Pb                        | 0.01 |
| $\text{Rb}_2\text{O}$     | 0.82  | Na(B)            | 1.00                   | $\Sigma\text{A}$          | 2.00 |
| $\text{K}_2\text{O}$      | 2.33  |                  |                        |                           |      |
| $\text{Na}_2\text{O}$     | 5.70  | OH               | 3.92                   | $\text{F}(X_D^P)$         | 1.00 |
| F                         | 1.49  | F                | 0.08                   |                           |      |
| $\text{H}_2\text{O}^{**}$ | 4.12  | $\Sigma X_A^O$   | 4.00                   | $\text{H}_2\text{O}(W_A)$ | 1.18 |
| F = O                     | −0.63 |                  |                        |                           |      |
| Total                     | 96.22 |                  |                        |                           |      |

\*Unit formula calculated on 32.18 (O + F) apfu, with  $\text{OH} + \text{F} = 5\text{ pfu}$  and  $\text{H}_2\text{O} = 1.18\text{ pfu}$ ;

\*\*calculated from the structure-refinement results.

## X-ray data collection and structure refinement

X-ray data for heyerdahlite were collected from a twinned crystal with a single-crystal Bruker D8 three-circle diffractometer equipped with a rotating-anode generator (MoK $\alpha$  radiation), multilayer optics and an APEX-II detector (University of Manitoba). Powder X-ray diffraction data were obtained by collapsing experimental data from the twinned crystal into two dimensions and are presented in Table 4. Details of data collection and structure refinement are given in Table 5. The intensities of reflections were collected with a frame width of 0.3° and a frame time of 6 s, and an empirical absorption correction (*TWINABS*, Sheldrick, 2008) was applied. *CELL\_NOW* (Sheldrick, 2004) was used to obtain an HKLF5 file, and the Bruker *SHELXTL Version 5.1* was used for the refinement of the crystal structure in space group *P* $\bar{1}$  using the atom coordinates of zircophyllite (Sokolova and Hawthorne, 2016); coordinates of the A(2) and W<sub>A</sub> atoms were taken from the difference-Fourier map. The crystal structure of heyerdahlite was refined to  $R_1 = 4.44\%$ . The twin

law is 180° rotation around the real axis [120] and the twin ratio is 0.572(3):0.428(3). The occupancies of eight cation sites were refined with the following scattering curves: *M*(1–4) and *D* sites: Mn and Ti; *A*(1) and *A*(2) sites: K and Na; *B* site: Na; and the W<sub>A</sub> site: O. We observed disorder of K and Na at the *A*(1) and *A*(2) sites, with K–Na = 0.754 Å. The refinement of the site occupancy for the *B* site converged to 1.0 and was fixed. At the last stages of the refinement, occupancies of the *A*(1), *A*(2) and W<sub>A</sub> sites were fixed in accord with chemical composition (Table 3). Scattering curves for neutral atoms were taken from the *International Tables for Crystallography* (Wilson, 1992). Final atom coordinates and equivalent displacement parameters are given in Table 6, selected interatomic distances and angles in Table 7, refined site-scattering values and assigned site-populations in Table 8, details of hydrogen bonding in Table 9 and bond-valence values for selected anions in Table 10. A list of observed and calculated structure factors, Crystallography Information File (CIF) and a table of anisotropic displacement parameters have been deposited as Supplementary material (see below).

TABLE 4. Powder X-ray diffraction data\* for heyerdahlite.

| $I_{\text{est.}}$ | $d_{\text{calc}}$ (Å) | $h$       | $k$       | $l$ | $I_{\text{est.}}$ | $d_{\text{calc}}$ (Å) | $h$       | $k$       | $l$ | $I_{\text{est.}}$ | $d_{\text{calc}}$ (Å) | $h$       | $k$       | $l$ |
|-------------------|-----------------------|-----------|-----------|-----|-------------------|-----------------------|-----------|-----------|-----|-------------------|-----------------------|-----------|-----------|-----|
| 100               | 10.745                | 0         | 0         | 1   | 65                | 2.594                 | 1         | 3         | 0   | 18                | 1.666                 | 0         | $\bar{7}$ | 3   |
| 10                | 9.886                 | 0         | $\bar{1}$ | 1   |                   | 2.586                 | 1         | $\bar{4}$ | 3   | 14                | 1.650                 | $\bar{1}$ | $\bar{2}$ | 7   |
| 12                | 3.734                 | 1         | $\bar{2}$ | 2   | 33                | 2.496                 | $\bar{2}$ | 1         | 2   |                   | 1.6494                | $\bar{1}$ | 4         | 4   |
|                   | 3.732                 | $\bar{1}$ | 1         | 2   | 14                | 2.424                 | $\bar{1}$ | 4         | 1   |                   | 1.6491                | 3         | 0         | 1   |
| 43                | 3.582                 | 0         | 0         | 3   | 14                | 2.414                 | $\bar{1}$ | $\bar{3}$ | 4   |                   | 1.6470                | 0         | $\bar{7}$ | 2   |
| 14                | 3.546                 | 1         | 1         | 1   | 20                | 2.318                 | 1         | 3         | 1   |                   | 1.6450                | 0         | $\bar{7}$ | 4   |
| 14                | 3.295                 | 0         | $\bar{3}$ | 3   |                   | 2.317                 | 2         | $\bar{1}$ | 2   | 29                | 1.5820                | 3         | $\bar{5}$ | 1   |
|                   | 3.295                 | $\bar{1}$ | $\bar{1}$ | 3   | 10                | 2.308                 | 1         | $\bar{4}$ | 4   |                   | 1.5816                | $\bar{3}$ | $\bar{2}$ | 2   |
| 10                | 3.117                 | $\bar{1}$ | 2         | 2   | 23                | 2.250                 | $\bar{2}$ | 1         | 3   | 18                | 1.5680                | $\bar{3}$ | 5         | 0   |
| 10                | 3.054                 | 1         | $\bar{2}$ | 3   | 14                | 2.059                 | 2         | $\bar{1}$ | 3   |                   | 1.5660                | $\bar{3}$ | $\bar{2}$ | 3   |
| 14                | 2.893                 | 1         | $\bar{3}$ | 3   | 10                | 1.791                 | 0         | 0         | 6   |                   | 1.5656                | 1         | 4         | 3   |
|                   | 2.888                 | 1         | 1         | 2   |                   | 1.787                 | 1         | 3         | 3   |                   | 1.5635                | $\bar{3}$ | $\bar{2}$ | 1   |
| 55                | 2.791                 | $\bar{1}$ | $\bar{3}$ | 1   | 10                | 1.779                 | 1         | $\bar{4}$ | 6   |                   | 1.5627                | 3         | $\bar{5}$ | 2   |
|                   | 2.787                 | 1         | $\bar{4}$ | 2   | 18                | 1.763                 | 2         | $\bar{6}$ | 2   |                   |                       |           |           |     |
| 29                | 2.686                 | 0         | 0         | 4   |                   | 1.759                 | $\bar{2}$ | 1         | 5   |                   |                       |           |           |     |
| 42                | 2.663                 | $\bar{2}$ | 1         | 1   |                   | 1.758                 | $\bar{2}$ | $\bar{4}$ | 2   |                   |                       |           |           |     |
|                   |                       |           |           |     |                   | 1.757                 | 2         | $\bar{4}$ | 3   |                   |                       |           |           |     |

\*Powder data were obtained by collapsing the experimental data from the single-crystal experiment into two dimensions. The most intense reflection (001) was covered by the beam stop. Therefore intensity was taken from the calculated powder diffraction pattern and all intensities rescaled accordingly. Intensities with  $I_{\text{est.}} < 10$  are not listed.



# DESCRIPTION AND CRYSTAL STRUCTURE OF HEYERDAHLITE

TABLE 5. Miscellaneous refinement data for heyerdahlite.

|   |   |
|---|---|
| <i>a</i> (Å)  | 5.392(2)  |
| <i>b</i>  | 11.968(4)   |
| <i>c</i>  | 11.868(4)   |
| $\alpha$ (°)  | 112.743(8)  |
| $\beta$   | 94.816(7)   |
| $\gamma$  | 103.037(8)  |
| <i>V</i> (Å <sup>3</sup> )  | 675.6(7)  |
| Space group   | <i>P</i> 1  |
| <i>Z</i>  | 1   |
| Reflections ( <i>I</i> > 10 $\sigma$ <i>I</i> )                       | 5374  |
| Absorption coefficient (mm <sup>-1</sup> )                            | 4.58  |
| <i>F</i> (000)  | 638.5   |
| <i>D</i> <sub>calc.</sub> (g/cm <sup>3</sup> )                        | 3.245   |
| Second twin component (%)   | 42.8(3)   |
| Crystal size (mm)   | 0.14 × 0.03 × 0.007   |
| Radiation/monochromator   | MoK $\alpha$ /graphite  |
| 2 $\theta$ -range for data collection (°)                             | 3.79–60.40  |
| <i>h</i>  | −7 ≤ <i>h</i> ≤ 7   |
| <i>k</i>  | −16 ≤ <i>k</i> ≤ 15   |
| <i>l</i>  | 0 ≤ <i>l</i> ≤ 16   |
| <i>R</i> ( $\sigma$ ) (%)   | 2.76  |
| Reflections collected   | 29,899  |
| Independent reflections   | 3993  |
| <i>F</i> <sub>o</sub> > 4 $\sigma$ <i>F</i>                           | 3577  |
| Refinement method   | Full-matrix least squares<br>on <i>F</i> <sup>2</sup> , fixed weights<br>proportional to 1/ $\sigma$ <i>F</i> <sub>o</sub> <sup>2</sup> |
| Refined parameters  | 262   |
| Final <i>R</i> (obs) (%)  |   |
| <i>R</i> <sub>1</sub> ( <i>F</i> <sub>o</sub> > 4 $\sigma$ <i>F</i> ) | 4.44  |
| <i>R</i> <sub>1</sub> (independent refl.)                             | 5.12  |
| <i>wR</i> <sub>1</sub>  | 11.36   |
| <i>wR</i> <sub>2</sub>  | 11.72   |
| Highest peak, deepest hole ( <i>e</i> Å <sup>-3</sup> )               | 1.31, −1.21   |
| Goodness of fit on <i>F</i> <sup>2</sup>                              | 1.128   |

## Structure description

In the crystal structure of heyerdahlite, there are four *T* sites occupied by Si (Table 6) and tetrahedrally coordinated by O atoms, with <Si–O> = 1.624 Å (Table 7). There is one Ti-dominant *D* site coordinated by five O atoms and an X<sub>D</sub><sup>P</sup> anion [X<sub>D</sub><sup>P</sup> = F<sub>1.00</sub>], with <D– $\phi$ > = 1.962 Å ( $\phi$  = O, F); and its composition is (Ti<sub>1.78</sub>Nb<sub>0.17</sub>Mg<sub>0.03</sub>Zr<sub>0.02</sub>), ideally Ti<sub>2</sub> apfu (Table 7). There are four Mn-dominant *M* sites octahedrally coordinated by O atoms and OH groups (plus minor F) at the X<sub>A</sub><sup>Q</sup>(1,2) sites (Tables 6–8), with <M(1–4)– $\phi$ > = 2.200–2.156 Å ( $\phi$  = O, OH). These four *M* sites give (Mn<sub>6.29</sub>Na<sub>0.33</sub>Zn<sub>0.23</sub>Mg<sub>0.07</sub>Zr<sub>0.04</sub>Fe<sub>0.03</sub><sup>2+</sup>Ca<sub>0.01</sub>)<sub>Σ7</sub>,

ideally Mn<sub>7</sub> apfu (Table 2). Details of hydrogen bonding involving H atoms of OH groups are given in Table 9. M(1–4) octahedra share common edges to form a trioctahedral O sheet. As in most astrophyllite-supergroup structures, the sizes of M octahedra follow the pattern M(1) > M(2) > M(3) > M(4) due to the different linkages of M octahedra and the polyhedra of the H sheets (Sokolova, 2012). The T tetrahedra share vertices to form the T<sub>4</sub>O<sub>12</sub>(Si<sub>4</sub>O<sub>12</sub>) astrophyllite ribbon along [100]. Astrophyllite ribbons and D octahedra share common vertices to form an H sheet. Two H and one O sheets form an HOH block identical to that in kupletskite (Fig. 3a). In the heyerdahlite structure, D octahedra share a common X<sub>D</sub><sup>P</sup> anion where X<sub>D</sub><sup>P</sup> = F (Tables 8, 10).

TABLE 6. Atom coordinates and equivalent displacement parameters ( $\text{\AA}^2$ ) for heyerdahlite.

| Atom                            | <i>x</i>    | <i>y</i>    | <i>z</i>    | <i>U</i> <sub>eq</sub> |
|---------------------------------|-------------|-------------|-------------|------------------------|
| M(1)                            | 0.84915(13) | 0.20477(11) | 0.47536(7)  | 0.0110(2)              |
| M(2)                            | 0.27856(18) | 0.06551(9)  | 0.48484(10) | 0.0119(3)              |
| M(3)                            | 0.42152(19) | 0.35065(9)  | 0.48036(10) | 0.0119(3)              |
| M(4)                            | 0           | ½           | ½           | 0.0107(4)              |
| D                               | 0.07928(13) | 0.08646(10) | 0.19710(6)  | 0.0093(2)              |
| T(1)                            | 0.6788(4)   | 0.27171(15) | 0.23029(17) | 0.0102(3)              |
| T(2)                            | 0.8145(3)   | 0.54827(16) | 0.25964(15) | 0.0102(3)              |
| T(3)                            | 0.3800(3)   | 0.67861(17) | 0.26241(14) | 0.0106(3)              |
| T(4)                            | 0.5082(3)   | 0.93209(15) | 0.23523(16) | 0.0083(3)              |
| A(1)                            | 0.1307(12)  | 0.2633(4)   | 0.9946(5)   | 0.0413(7)              |
| A(2)                            | 0.0992(14)  | 0.1991(5)   | 0.9956(6)   | 0.0238(7)              |
| B                               | ½           | 0           | 0           | 0.0205(5)              |
| O(1)                            | 0.7293(9)   | 0.3177(5)   | 0.3807(5)   | 0.0122(9)              |
| O(2)                            | 0.1261(9)   | 0.3883(5)   | 0.5905(4)   | 0.0105(8)              |
| O(3)                            | 0.5558(7)   | 0.2514(5)   | 0.5879(3)   | 0.0129(7)              |
| O(4)                            | 0.5761(9)   | 0.0144(5)   | 0.3848(4)   | 0.0116(9)              |
| O(5)                            | 0.0748(8)   | 0.5956(4)   | 0.2101(5)   | 0.0163(9)              |
| O(6)                            | 0.2464(10)  | 0.0397(5)   | 0.8280(5)   | 0.0225(11)             |
| O(7)                            | 0.4278(9)   | 0.4107(4)   | 0.7905(4)   | 0.0160(9)              |
| O(8)                            | 0.1243(11)  | 0.8065(5)   | 0.8311(5)   | 0.0212(10)             |
| O(9)                            | 0.2621(10)  | 0.9580(5)   | 0.1736(5)   | 0.0212(10)             |
| O(10)                           | 0.2631(10)  | 0.6038(4)   | 0.8008(5)   | 0.0170(10)             |
| O(11)                           | 0.5720(11)  | 0.2189(4)   | 0.7968(5)   | 0.0185(10)             |
| O(12)                           | 0.3822(9)   | 0.1920(5)   | 0.1684(5)   | 0.0222(11)             |
| X <sub>D</sub> <sup>O</sup>     | 0.1469(6)   | 0.1605(5)   | 0.3656(3)   | 0.0116(6)              |
| X <sub>A</sub> <sup>O</sup> (1) | 0.2993(9)   | 0.4668(5)   | 0.3995(4)   | 0.0125(10)             |
| X <sub>A</sub> <sup>O</sup> (2) | 0.9899(10)  | 0.1183(5)   | 0.5938(5)   | 0.0160(10)             |
| X <sub>D</sub> <sup>P</sup>     | 0           | 0           | 0           | 0.0154(7)              |
| W <sub>A</sub>                  | 0.156(3)    | 0.3853(12)  | 0.0026(15)  | 0.059(3)*              |
| H(1)                            | 0.300(14)   | 0.431(6)    | 0.3102(17)  | 0.01503*               |
| H(2)                            | 1.067(14)   | 0.171(6)    | 0.682(2)    | 0.01920*               |

\**U*<sub>iso</sub>.

In the **I** block between adjacent HOH blocks, there are two interstitial cation sites, *A* and *B*, and a *W<sub>A</sub>* site partly occupied by H<sub>2</sub>O. The *A* site splits into two sites, [12]-coordinated *A*(1) and [6]-coordinated *A*(2), separated by a short distance of 0.754 Å (Table 7). The *A*(1) site is coordinated by eleven O atoms and a F atom at the X<sub>D</sub><sup>P</sup> site, and the *A*(2) site is coordinated by four O atoms, an X<sub>D</sub><sup>P</sup> anion and an H<sub>2</sub>O group at the *W<sub>A</sub>* site. There is a short distance *A*(1)–*W<sub>A</sub>* = 1.40 Å (Table 7) and hence the *A*(2) + *W<sub>A</sub>* sites and the *A*(1) site cannot all be locally occupied. The *A*(1) and *A*(2) sites are occupied by (□<sub>1.18</sub>K<sub>0.68</sub>Rb<sub>0.12</sub>Cs<sub>0.01</sub>Pb<sub>0.01</sub>) pfu (41% occupancy) and (Na<sub>1.18</sub>□<sub>0.82</sub>) pfu (59% occupancy), respectively (Table 8). As the *A*(1) site is occupied at 41%, the *W<sub>A</sub>* site can be occupied by H<sub>2</sub>O at 59%, i.e. by 1.18 H<sub>2</sub>O pfu which is in

accord with 1.18 Na apfu at the *A*(2) site (Table 8). A possible short-range-order arrangement of K and Na atoms where they fully occupy the *A*(1) and *A*(2) sites, respectively, is shown in Fig. 3b. The aggregate content of the *A* site is (Na<sub>1.18</sub>K<sub>0.68</sub>Rb<sub>0.12</sub>Cs<sub>0.01</sub>Pb<sub>0.01</sub>)<sub>Σ2</sub>, ideally Na<sub>2</sub> apfu. Note that the ideal composition of the *A* site, Na<sub>2</sub> apfu, (where it is fully occupied by Na) requires full occupancy of the *W<sub>A</sub>* site: (H<sub>2</sub>O)<sub>2</sub> pfu; otherwise the coordination of the Na atom is not complete. The [10]-coordinated *B* site is occupied by Na (Table 8), giving Na apfu.

Similar disorder at the *A* site was reported for the astrophyllite-group minerals bulgakite and nalivkitite (Agakhanov *et al.*, 2016) where the ideal composition of the *A* site is Li<sub>2</sub> apfu (Table 1) and nafertisite, ideally Na<sub>3</sub>Fe<sub>10</sub><sup>2+</sup>Ti<sub>2</sub>(Si<sub>6</sub>O<sub>17</sub>)<sub>2</sub>O<sub>2</sub>(OH)<sub>6</sub>F (H<sub>2</sub>O)<sub>2</sub> (Cámara *et al.*, 2014).



# DESCRIPTION AND CRYSTAL STRUCTURE OF HEYERDAHLITE

TABLE 7. Selected interatomic distances (Å) and angles (°) for heyerdahlite.

|   |          |                                       |          |                                       |          |
|---|----------|---------------------------------------|----------|---------------------------------------|----------|
| M(1)–(X <sub>D</sub> <sup>O</sup> )a    | 2.181(3) | M(2)–X <sub>A</sub> <sup>O</sup> (2)c | 2.134(5) | M(3)–O(1)                             | 2.139(5) |
| M(1)–O(3)                               | 2.185(4) | M(2)–O(4)                             | 2.135(3) | M(3)–X <sub>A</sub> <sup>O</sup> (1)  | 2.151(5) |
| M(1)–O(2)a                              | 2.186(5) | M(2)–X <sub>A</sub> <sup>O</sup> (2)b | 2.155(6) | M(3)–O(2)                             | 2.160(5) |
| M(1)–O(4)                               | 2.200(5) | M(2)–O(3)                             | 2.184(5) | M(3)–X <sub>A</sub> <sup>O</sup> (1)d | 2.195(5) |
| M(1)–X <sub>A</sub> <sup>O</sup> (2)    | 2.220(6) | M(2)–O(4)c                            | 2.281(5) | M(3)–X <sub>D</sub> <sup>O</sup>      | 2.230(5) |
| M(1)–O(1)                               | 2.226(5) | M(2)–X <sub>D</sub> <sup>O</sup>      | 2.289(5) | M(3)–O(3)                             | 2.230(3) |
| <M(1)–φ>                                | 2.200    | <M(2)–φ>                              | 2.196    | <M(3)–φ>                              | 2.184    |
| M(4)–X <sub>A</sub> <sup>O</sup> (1) x2 | 2.105(5) | T(1)–O(12)                            | 1.606(5) | T(2)–O(10)d                           | 1.612(4) |
| M(4)–O(1)b x2                           | 2.173(5) | T(1)–O(8)d                            | 1.608(5) | T(2)–O(2)d                            | 1.611(5) |
| M(4)–O(2) x2                            | 2.191(5) | T(1)–O(1)                             | 1.629(5) | T(2)–O(5)a                            | 1.636(5) |
| <M(4)–φ>                                | 2.156    | T(1)–O(10)d                           | 1.639(4) | T(2)–O(7)d                            | 1.639(5) |
|   |          | <T(1)–O>                              | 1.621    | <T(2)–O>                              | 1.625    |
| T(3)–O(3)d                              | 1.610(4) | T(4)–O(6)d                            | 1.609(5) | T(1)d–O(10)–T(2)d                     | 144.5(4) |
| T(3)–O(11)d                             | 1.618(5) | T(4)–O(9)                             | 1.609(5) | T(2)b–O(5)–T(3)                       | 140.8(3) |
| T(3)–O(5)                               | 1.641(5) | T(4)–O(4)e                            | 1.622(5) | T(2)d–O(7)–T(3)d                      | 140.5(3) |
| T(3)–O(7)d                              | 1.644(5) | T(4)–O(11)d                           | 1.639(4) | T(3)d–O(11)–T(4)d                     | 144.7(4) |
| <T(3)–O>                                | 1.628    | <T(4)–O>                              | 1.620    | <T–O–T>                               | 142.6    |
| D–X <sub>D</sub> <sup>O</sup>           | 1.810(3) | A(1)–O(9)h                            | 2.856(8) | A(2)–W <sub>A</sub> l                 | 2.15(1)  |
| D–O(9)g                                 | 1.953(5) | A(1)–O(8)k                            | 2.857(8) | A(2)–(X <sub>D</sub> <sup>O</sup> )l  | 2.344(5) |
| D–O(6)f                                 | 1.955(5) | A(1)–O(12)l                           | 2.869(7) | A(2)–O(9)h                            | 2.477(8) |
| D–O(8)h                                 | 1.965(5) | A(1)–O(6)                             | 2.886(8) | A(2)–O(8)k                            | 2.484(9) |
| D–O(12)                                 | 1.969(5) | A(1)–(X <sub>D</sub> <sup>O</sup> )l  | 3.097(4) | A(2)–O(12)e                           | 2.491(8) |
| D–X <sub>D</sub> <sup>O</sup>           | 2.118(1) | A(1)–O(11)                            | 3.464(8) | A(2)–O(6)                             | 2.498(9) |
| <D–φ>                                   | 1.962    | A(1)–O(11)b                           | 3.464(8) | <A(2)–φ>                              | 2.407    |
|   |          | A(1)–O(10)k                           | 3.513(9) |                                       |          |
| A(1)–A(2)                               | 0.754(4) | A(1)–O(10)m                           | 3.528(8) | B–O(6)c x2                            | 2.614(5) |
| A(1)–W <sub>A</sub> a                   | 1.40(1)  | A(1)–O(5)h                            | 3.680(7) | B–O(12) x2                            | 2.645(6) |
|   |          | A(1)–O(7)                             | 3.772(7) | B–O(9)g x2                            | 2.664(5) |
|   |          | A(1)–O(7)m                            | 3.806(7) | B–O(8)d x2                            | 2.664(6) |
|   |          | <A(1)–φ>                              | 3.316    | B–X <sub>D</sub> <sup>O</sup> x2      | 2.696(2) |
|   |          |                                       |          | <B–φ>                                 | 2.657    |

\*φ = O, OH, F.

Operators for generating equivalent atoms: a:  $x + 1, y, z$ ; b:  $x - 1, y, z$ ; c:  $-x + 1, -y, -z + 1$ ; d:  $-x + 1, -y + 1, -z + 1$ ; e:  $x, y + 1, z$ ; f:  $-x, -y, -z + 1$ ; g:  $x, y - 1, z$ ; h:  $-x, -y + 1, -z + 1$ ; k:  $-x, -y + 1, -z + 2$ ; ; l:  $x, y, z + 1$ ; m:  $-x + 1, -y + 1, -z + 2$ .

## The ideal formula of heyerdahlite

For the ideal structural formula of heyerdahlite of the form  $A_2BC_7D_2(T_4O_{12})_2X_{D2}^OX_{A4}^OX_{D}^PW_{A2}$  (Sokolova *et al.*, 2017a), we sum the ideal compositions of the following sites:  $C_7 = Mn_7$ ;  $D = [{}^6Ti_2]$ ;  $T_4 = Si_4$ ;  $A_2 = Na_2$ ;  $B = Na$ ;  $X_{D2}^O = O_2$ ;  $X_{A4}^O = (OH)_4$ ;  $X_D^P = F$ ,  $W_{A2} = (H_2O)_2$  (Table 8). Hence the ideal structural formula of heyerdahlite is  $Na_2NaMn_7Ti_2(Si_4O_{12})_2O_2(OH)_4F(H_2O)_2$ ,  $Z = 1$ ; the ideal formula of heyerdahlite is  $Na_3Mn_7Ti_2(Si_4O_{12})_2O_2(OH)_4F(H_2O)_2$ .

Heyerdahlite and kupletskite are related by the following substitution  ${}^A Na_2^{+} + {}^W (H_2O)_2 \leftrightarrow {}^A K_2^{+} + {}^W \square$ .

## Summary

Heyerdahlite, ideally  $Na_3Mn_7Ti_2(Si_4O_{12})_2O_2(OH)_4F(H_2O)_2$ , is a new mineral of the kupletskite group (astrophyllite supergroup). The formula of heyerdahlite is of the form  $A_2BC_7D_2(T_4O_{12})_2O_2(OH)_4X_{D}^PW_{A2}$ , where ideally  $C_7 = Mn_7$  at the *M* (1–4) sites;  $D_2 = Ti_2$ ;  $T_4 = Si_4$ ;  $A_2 = Na_2$ ;  $B = Na$ ;  $X_D^P = F$ ;  $W_{A2} = (H_2O)_2$ .

The heyerdahlite structure consists of HOH blocks which alternate with interstitial sites of the **I** block along [001]. The topology of the **I** block is the same as that in bulgakite and nalivkinite where Li is the dominant cation at the *A* site.

TABLE 8. Refined site-scattering values and assigned site-populations for heyerdahlite.

| Site*                       | Refined site-scattering (epfu) | Site population (apfu)  | Calculated site-scattering (epfu) | $\langle \text{Ct}-\varphi \rangle_{\text{obs.}} (\text{\AA})^{**}$ | Ideal composition (pfu)  |
|-----------------------------|--------------------------------|---|-----------------------------------|---|--------------------------|
| <b>Cations</b>              |                                |   |                                   |   |                          |
| <i>M</i> (1)                | 48.9(2)                        |   |                                   | 2.200   |                          |
| <i>M</i> (2)                | 48.9(3)                        | $\text{Mn}_{6.29}\text{Na}_{0.32}\text{Zn}_{0.23}\text{Mg}_{0.07}\text{Zr}_{0.04}\text{Fe}_{0.03}^{2+}$ |                                   | 2.196   |                          |
| <i>M</i> (3)                | 51.2(3)                        | $\text{Ca}_{0.01}$  |                                   | 2.184   |                          |
| <i>M</i> (4)                | 26.1(2)                        |   |                                   | 2.156   |                          |
| $\Sigma M$                  | 175.1                          | $\text{Mn}_{6.29}\text{Na}_{0.32}\text{Zn}_{0.23}\text{Mg}_{0.07}\text{Zr}_{0.04}\text{Fe}_{0.03}^{2+}$ | 171.09                            |   | $\text{Mn}_7$            |
| <i>D</i>                    | 47.4(2)                        | $\text{Ca}_{0.01}\text{Ti}_{1.78}\text{Nb}_{0.17}\text{Mg}_{0.03}\text{Zr}_{0.02}$                      | 47.29                             | 1.962   | $\text{Ti}_2$            |
| $^{[12]}A(1)$               | 18.73                          | $\square_{1.18}\text{K}_{0.68}\text{Rb}_{0.12}\text{Cs}_{0.01}\text{Pb}_{0.01}$                         | 18.73                             | 3.316   |                          |
| $^{[6]}A(2)$                | 12.98                          | $\text{Na}_{1.18}\square_{0.82}$  | 12.98                             | 2.656   |                          |
| $\Sigma A(1,2)$             | 31.71                          | $\text{Na}_{1.18}\text{K}_{0.68}\text{Rb}_{0.12}\text{Cs}_{0.01}\text{Pb}_{0.01}$                       | 31.71                             |   | $\text{Na}_2$            |
| $^{[10]}B$                  | 11.00                          | $\text{Na}_{1.00}$  | 11.00                             | 2.657   | $\text{Na}$              |
| <b>Anions</b>               |                                |   |                                   |   |                          |
| $\text{X}_D^{\text{O}}$     |                                | $\text{O}_{2.00}$   |                                   |   | $\text{O}_2$             |
| $^{[3]}X_A^{\text{O}}(1,2)$ |                                | $(\text{OH})_{3.92}\text{F}_{0.08}$   |                                   |   | $(\text{OH})_4$          |
| $^{[6]}X_D^{\text{F}}$      |                                | $\text{F}_{1.00}$   |                                   |   | $\text{F}$               |
| $\text{W}_A$                |                                | $(\text{H}_2\text{O})_{1.18}\square_{0.82}$   |                                   |   | $(\text{H}_2\text{O})_2$ |

\*coordination number is given for non-[6]-coordinated sites;

\*\*Ct = cation,  $\varphi$  = O, OH, F,  $\text{H}_2\text{O}$ .

TABLE 9. Hydrogen bonding in heyerdahlite.

| D—H...A   | D—H (Å) | H...A (Å) | D...A (Å) | $\angle \text{DHA} (^{\circ})$ |
|---|---------|-----------|-----------|--------------------------------|
| $\text{X}_D^{\text{O}}(1) - \text{H}(1) \cdots \text{O}(8)\text{a}$ | 0.98(1) | 2.98(7)   | 3.47(7)   | 113(5)                         |
| $\text{X}_A^{\text{O}}(1) - \text{H}(1) \cdots \text{O}(12)$        | 0.98(1) | 2.86(6)   | 3.53(8)   | 126(5)                         |
| $\text{X}_D^{\text{O}}(2) - \text{H}(2) \cdots \text{O}(6)\text{b}$ | 0.98(1) | 2.98(7)   | 3.53(8)   | 117(5)                         |
| $\text{X}_A^{\text{O}}(2) - \text{H}(2) \cdots \text{O}(9)\text{c}$ | 0.98(1) | 3.12(7)   | 3.51(8)   | 105(5)                         |

a:  $-x, -y+1, -z+1$ ; b:  $x+1, y, z$ ; c:  $-x+1, -y+1, -z+1$ .

TABLE 10. Selected bond-valence values\* for heyerdahlite.

| Atom**                     | M(1–4) | D                           | A(1)                        | A(2)                        | B                           | $\Sigma$ |
|----------------------------|--------|-----------------------------|-----------------------------|-----------------------------|-----------------------------|----------|
| $\text{X}_D^{\text{O}}$    | 0.99   | 0.90                        |                             |                             |                             | 1.89     |
| $\text{X}_A^{\text{O}}(1)$ | 1.11   |                             |                             |                             |                             | 1.11     |
| $\text{X}_A^{\text{O}}(2)$ | 1.05   |                             |                             |                             |                             | 1.05     |
| $\text{X}_D^{\text{F}}$    |        | $0.31 \times 2 \rightarrow$ | $0.04 \times 2 \rightarrow$ | $0.08 \times 2 \rightarrow$ | $0.09 \times 2 \rightarrow$ | 1.04     |

\* Bond-valence parameters (in valence units) are from Brown (1981).

\*\* M = Mn; D = Ti; A(1) = K, 50% occupancy; A(2) = Na, 50% occupancy; B = Na;  $\text{X}_D^{\text{O}}$  = O;  $\text{X}_A^{\text{O}}(1,2)$  = OH;  $\text{X}_D^{\text{F}}$  = F.

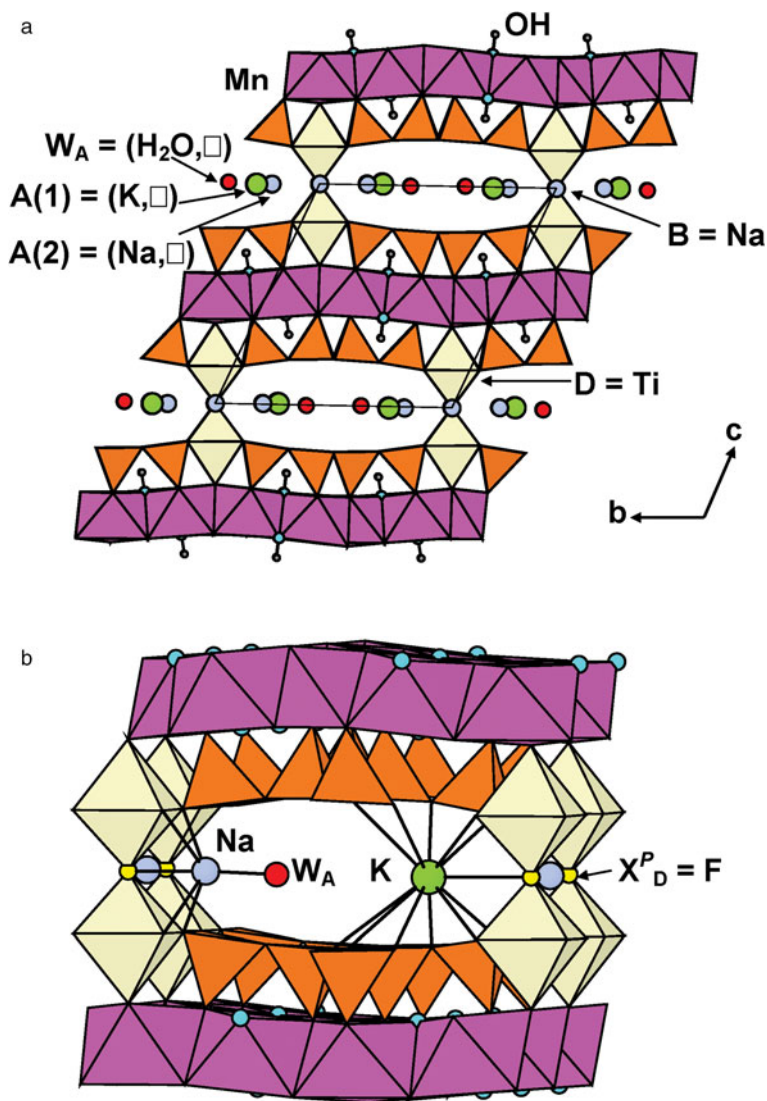


FIG. 3. The crystal structure of heyerdahlite: (a) general view; and (b) a possible short-range-order arrangement of K and Na atoms at the  $A(1)$  and  $A(2)$  sites, respectively. Mn-dominant and Ti-dominant octahedra are magenta and yellow, respectively; Si tetrahedra are orange; Na and K atoms at  $B$ ,  $A(2)$  and  $A(1)$  sites are shown as medium blue and large green spheres; F atoms [ $X_D^P$  site], O atoms of OH groups [ $X_A^O$  sites] and  $H_2O$  groups [ $W_A$  site] are shown as small yellow, small turquoise and medium red spheres, respectively; H atoms of OH groups are shown as small grey spheres, O–H bonds are shown as black lines; the unit cell is shown with thin black lines.

## Acknowledgements

We are grateful to Fernando Cámara and Henrik Friis for extremely thorough reviews and to Structure Editor Peter Leverett and Associate Editor Ed Grew for valuable comments. We thank Harald Folvik, Natural History Museum, University of Oslo, for the scanning

electron microscopy image of heyerdahlite crystals. We thank Mark A. Cooper, University of Manitoba, for collection of the single-crystal X-ray data for heyerdahlite. This work was supported by a Canada Research Chair in Crystallography and Mineralogy and by a Discovery grant from the Natural Sciences and Engineering Research Council of Canada to FCH,

and by Innovation Grants from the Canada Foundation for Innovation to FCH.

## Supplementary material

To view supplementary material for this article, please visit <https://doi.org/10.1180/minmag.2017.081.051>

## References

- Agakhanov, A.A., Pautov, L.A., Sokolova, E., Abdu, Y.A. and Karpenko, V.Yu. (2016) Two astrophyllite-supergroup minerals, bulgakite and nalivkinite: bulgakite, a new mineral from the Darai-Pioz alkaline massif, Tajikistan and revision of the crystal structure and chemical formula of nalivkinite. *The Canadian Mineralogist*, **54**, 33–48.
- Bartelmehs, K.L., Bloss, F.D., Downs, R.T. and Birch, J.B. (1992) EXCALIBUR II. *Zeitschrift für Kristallographie*, **199**, 185–196.
- Brown, I.D. (1981) The bond valence method: an empirical approach to chemical structure and bonding. Pp. 1–30 in: *Structure and Bonding in Crystals II* (M. O'Keeffe and A. Navrotsky, editors). Academic Press, New York, USA.
- Cámara, F., Sokolova, E., Abdu, Y. and Hawthorne, F.C. (2010) The crystal structures of niobophyllite, kupletskite-(Cs) and Sn-rich astrophyllite; revisions to the crystal chemistry of the astrophyllite-group minerals. *The Canadian Mineralogist*, **48**, 1–16.
- Cámara, F., Sokolova, E., Abdu, Y.A. and Hawthorne, F.C. (2014) Nafertisite,  $\text{Na}_3\text{Fe}_{10}^{2+}\text{Ti}_2(\text{Si}_6\text{O}_{17})_2\text{O}_2(\text{OH})_6\text{F}(\text{H}_2\text{O})_2$ , from Mt. Kukisvumchorr, Khibiny alkaline massif, Kola peninsula, Russia: Refinement of the crystal structure and revision of the chemical formula. *European Journal of Mineralogy*, **26**, 689–700.
- Dahlgren, S. (2010) The Larvik plutonic complex: the larvikite and nepheline syenite plutons and their pegmatites. Pp. 26–37 in: *The Langesundsfjord – History, Geology, Pegmatites, Minerals* (A.O. Larsen, editor). Bode Verlag, Salzhemmendorf, Germany.
- Kampf, A.R., Rossman, G.R., Steele, I.M., Pluth, J.J., Dunning, G.E. and Walstrom, R.E. (2010) Devitoite, a new heterophyllosilicate mineral with astrophyllite-like layers from eastern Fresno County, California. *The Canadian Mineralogist*, **48**, 29–40.
- Khomyskov, A.P., Cámara, F., Sokolova, E., Hawthorne, F.C. and Abdu, Y. (2011) Sveinbergeite,  $\text{Ca}(\text{Fe}_6^{2+}\text{Fe}^{3+})\text{Ti}_2(\text{Si}_4\text{O}_{12})_2\text{O}_2(\text{OH})_5(\text{H}_2\text{O})_4$ , a new astrophyllite-group mineral species from the Larvik plutonic complex, Oslo region, Norway: Description and crystal structure. *Mineralogical Magazine*, **75**, 2687–2702.
- Larsen, A.O. (2010) Renowned syenite pegmatite localities in the Larvik plutonic complex. Pp. 46–63 in: *The Langesundsfjord – History, Geology, Pegmatites, Minerals* (A.O. Larsen, editor). Bode Verlag, Salzhemmendorf, Germany.
- Larsen, A.O. (2013) Contributions to the mineralogy of the syenite pegmatites in the Larvik plutonic complex. *Norsk Bergverksmuseum, Skrift*, **50**, 101–109.
- Oberti, R., Boiocchi, M., Hawthorne, F.C. and Kristiansen, R. (2014) Ferri-fluoro-leakite: a second occurrence at Brathagen (Norway), with new data on Zn partitioning and the oxo component in Na amphiboles. *Mineralogical Magazine*, **78**, 861–869.
- Mandarino, J.A. (1981) The Gladstone-Dale relationship. IV. The compatibility concept and its application. *The Canadian Mineralogist*, **41**, 989–1002.
- Piilonen, P.C., Lalonde, A.E., McDonald, A.M. and Gault, R.A. (2000) Niobokupletskite, a new astrophyllite-group mineral from Mont Saint-Hilaire, Quebec, Canada: description and crystal structure. *The Canadian Mineralogist*, **38**, 627–639.
- Piilonen, P.C., McDonald, A.M. and Lalonde, A.E. (2001) Kupletskite polytypes from the Lovozero massif, Kola peninsula, Russia: kupletskite-1A and kupletskite-Ma2b2c. *European Journal of Mineralogy*, **13**, 973–984.
- Piilonen, P.C., Lalonde, A.E., McDonald, A.M., Gault, R.A. and Larsen, A.O. (2003) Insights into astrophyllite-group minerals. I. Nomenclature, composition and development of a standardized general formula. *The Canadian Mineralogist*, **41**, 1–26.
- Pouchou, J.L. and Pichoir, F. (1985) 'PAP' ( $\varphi\rho Z$ ) procedure for improved quantitative microanalysis. Pp. 104–106 in: *Microbeam Analysis* (J.T. Armstrong, editor). San Francisco Press, San Francisco, California, USA.
- Sheldrick, G.M. (2004) *CELL\_NOW*. University of Göttingen, Germany.
- Sheldrick, G.M. (2008) A short history of SHELX. *Acta Crystallographica*, **A64**, 112–122.
- Sokolova, E. (2012) Further developments in the structure topology of the astrophyllite-group minerals. *Mineralogical Magazine*, **76**, 863–882.
- Sokolova, E. and Cámara, F. (2008) Re-investigation of the crystal structure of magnesium astrophyllite. *European Journal of Mineralogy*, **20**, 253–260.
- Sokolova, E. and Hawthorne, F.C. (2016) The crystal structure of zircophyllite,  $\text{K}_2\text{NaFe}_7^{2+}\text{Zr}_2(\text{Si}_4\text{O}_{12})_2\text{O}_2(\text{OH})_4\text{F}$ , an astrophyllite-supergroup mineral from Mont Saint-Hilaire, Québec, Canada. *The Canadian Mineralogist*, **54**, 1539–1547.
- Sokolova, E., Cámara, F., Hawthorne, F.C. and Ciriotti, M.E. (2017a) The astrophyllite supergroup: nomenclature and classification. *Mineralogical Magazine*, **81**, 143–153.
- Sokolova, E., Cámara, F., Hawthorne, F.C., Semenov, E.I. and Ciriotti, M.E. (2017b) Lobanovite,  $\text{K}_2\text{Na}(\text{Fe}_4^{2+}\text{Mg}_2\text{Na})\text{Ti}_2(\text{Si}_4\text{O}_{12})_2\text{O}_2(\text{OH})_4$ , a new mineral of

## DESCRIPTION AND CRYSTAL STRUCTURE OF HEYERDAHLITE

- the astrophyllite supergroup and its relation to magnesioastrophyllite. *Mineralogical Magazine*, **81**, 175–181.
- Stepanov, A.V., Bekenova, G.K., Levin, V.L., Sokolova, E. V., Hawthorne, F.C. and Dobrovolskaya, E.A. (2012) Tarbagataite,  $(K, \square)_2(Ca, Na)(Fe^{2+}, Mn)_7Ti_2(Si_4O_{12})_2O_2(OH)_4(OH, F)$ , a new astrophyllite-group mineral species from the Verkhnee Espe deposit, Akjailyautas Mountains, Kazakhstan: description and crystal structure. *The Canadian Mineralogist*, **50**, 159–168.
- Wilson, A.J.C. (Editor) (1992) *International Tables for Crystallography. Volume C: Mathematical, Physical and Chemical Tables*. Kluwer Academic Publishers, Dordrecht, The Netherlands.