

THE OPTICAL ABSORPTION SPECTRA OF TOURMALINE: IMPORTANCE OF CHARGE-TRANSFER PROCESSES

G. H. FAYE*, P. G. MANNING**, J. R. GOSSELIN* AND R. J. TREMBLAY***

ABSTRACT

Optical absorption spectra resolved into Gaussian bands, Mössbauer spectra, and electron-microprobe analyses are collated for several tourmalines in the elbaite-schorl and dravite-schorl series. This work clarifies the scattered and previously puzzling information on spectral features that affect the colours and pleochroism of tourmaline.

Emphasis is placed on the identification and importance of the $O^{2-} \rightarrow Fe^{2+}$ (Fe^{3+}), $Fe^{2+} \rightarrow Fe^{3+}$, and $Fe^{2+} \rightarrow Ti^{4+}$ charge-transfer processes. These processes are mainly responsible for the dichroism of tourmaline. The metal-metal interactions are facilitated when the electric vector of incident light vibrates in the 0001 plane. Ultraviolet-centered $O^{2-} \rightarrow Fe^{2+}$ and $O^{2-} \rightarrow Fe^{3+}$ processes are intensified by the replacement of OH⁻ by O^{2-} , for example when Ti^{4+} substitutes into octahedral sites of tourmaline. The former process is important in the colouring of Ti-rich dravites whereas the latter strongly influences the spectrum of schorls. The resolved, visible-region spectra of blue and black tourmalines are qualitatively remarkably similar and both have a prominent absorption at $\sim 18,500\text{ cm}^{-1}$ which, through a heating experiment and Mössbauer measurements, has been identified as the $Fe^{2+} \rightarrow Fe^{3+}$ process. The brown colour of Ti-rich dravites is also influenced by strong $Fe^{2+} \rightarrow Ti^{4+}$ charge-transfer absorption at 22,000-24,000 cm^{-1} , and a weaker version of the band contributes to the green colour of elbaites.

The polarization properties of the Fe^{2+} *d-d* bands, which have maximum intensity in $E \perp c$ spectra of coloured varieties, arise from intensity borrowing from $O^{2-} \rightarrow Fe^{2+}$ charge-transfer. Near-infrared spectra of specimens in the elbaite-schorl series show, on curve-resolution, previously undiscovered bands that mark the presence of Fe^{2+} in the *c*-site. These "new" features are strong in the spectra of black (schorl) specimens but weak for specimens near the elbaite end of the elbaite-schorl join.

INTRODUCTION

Although the chemistry and structure of tourmaline are well-known, the optical absorption spectra continue to defy a satisfactory unified

interpretation. It is generally accepted that the two prominent absorptions at $\sim 9,000$ and $\sim 14,000\text{ cm}^{-1}$ in tourmaline spectra are components of the ${}^5T_2 \rightarrow {}^5E(D)$ transition in Fe^{2+} ions located principally in the brucite-type *b*-sites (Faye *et al.* 1968; Townsend 1970; Wilkins *et al.* 1969; Manning 1969a). However, it has been argued that the two bands arise from Fe^{2+} ions located in the *b*- and Al *c*-sites, respectively (Burns 1972; Burns & Simon 1973), but this seems improbable because the relative intensities of the two bands are remarkably constant for differently-coloured varieties.

The origin of the numerous dichroic absorption bands in the visible region spectra (~ 700 nm to ~ 400 nm) of tourmalines is poorly understood. Strongly-polarized broad bands at $\sim 22,000\text{ cm}^{-1}$ (450 nm) in spectra of green and brown varieties have been assigned to $Ti^{3+} \rightarrow Ti^{4+}$ intervalence charge-transfer in the 0001 plane (Manning 1969b; Faye *et al.* 1968). Townsend (1970) feels the dichroism of tourmalines arises partly from charge-transfer transitions between metal ions sharing octahedral edges, and cited the suggestion that a dichroic shoulder at $\sim 17,500\text{ cm}^{-1}$ in spectra of some blue-green varieties may well represent $Fe^{2+} \rightarrow Fe^{3+}$ interaction. On the other hand, Wilkins *et al.* (1969) attribute the colours of tourmalines to crystal-field transitions within Fe^{2+} , Fe^{3+} and Mn ions, but they ignored absorptions due to Ti and intervalence charge-transfer. Some of their assignments are suspect; for example, the prominent polarized band at 22,000 cm^{-1} in spectra of brown tourmalines is assigned to the field-independent transition ${}^6A_1 \rightarrow {}^4A_1, {}^4E(G)$ in Fe^{3+} , and yet the band half-width of 5,500 cm^{-1} is unacceptably large (Manning 1969b). Crystal-field transitions within Cr^{3+} and Mn^{3+} are responsible for the colours of some deep-green and pink tourmalines (Manning 1969a,b); these varieties are not considered here because their spectra are understood reasonably well.

The complex structure of tourmaline inevitably introduces a considerable speculative element into spectral interpretation. Crystal-field bands of Fe, Mn and Ti ions often present in two valence states and distributed over two different octahedral sites and possibly a tetrahedral site, are superimposed on strong interval-

*Research Scientists, and *** Technician, Mineral Sciences Division, Mines Branch, Department of Energy, Mines and Resources, 555 Booth Street, Ottawa, Canada; and **Research Scientist, Inland Waters Branch, Department of the Environment, 562 Booth Street, Ottawa, Canada, K1A 0G1.

TABLE 1. ELECTRON MICROPROBE ANALYSES AND CELL PARAMETERS OF TOURMALINES

Specimen	Locality	Colour	weight %			cell parameters	
			Fe	Ti	Mn	a (Å)	c (Å)
schorl	Villeneuve, Quebec	black	12.0	0.2	0.6	16.010 (7)*	7.172 (4)
elbaite TB1-1	Minas Gerais, Brazil	blue	6.4	<0.01	0.3	15.908 (6)	7.127 (5)
elbaite TGr-2	unknown	green	5.0	0.01	0.8	15.886 (6)	7.120 (4)
brown dravite no. 1	Gouverneur, New York	brown	1.1	0.7	0.05	15.966 (5)	7.204 (3)
brown tourmaline no. 2	unknown	yellow-brown	4.9	1.0	--	--	--
elbaite TZ - zone A	unknown	brownish-green	2.7	0.09	2.2	15.862 (5)	7.121 (3)
elbaite TZ - zone B	unknown	blue	2.8	0.02	2.0	15.857 (7)	7.129 (7)
elbaite TZ - zone D	unknown	brown	3.3	0.10	1.9	15.890 (7)	7.134 (5)
elbaite TZ - zone F	unknown	light green	2.0	0.04	1.7	15.832 (7)	7.129 (4)

*Figure in parenthesis gives the standard deviation of the last digit.

TABLE 2. MÖSSBAUER DATA FOR CERTAIN TOURMALINES

	isomer shift, mm/s (rel. to Fe powder)	quadrupole splitting, 2ε mm/s	line width at half-height, mm/s	relative inten- sities, %	oxidation state of Fe	Fe ²⁺ /Fe ³⁺	site distr. of Fe ²⁺ b:c
schorl	1.1	2.2	0.4	40	2+	3:1	8:7
	0.7	1.5	0.6	35	2+		
	0.3	0.8	0.5	25	3+		
elbaite TB1-1	1.0	2.4	0.4	90	2+	-24:1	-15:1
	1.0	1.4	0.4	6	2+		
	-	-	-	-4	3+		
elbaite TB1-1, heated	1.1	2.4	0.5	53	2+	2:1	9:2
	1.0	1.7	0.5	12	2+		
	0.3	0.9	0.5	23	3+		
	0.4	1.1	0.5	12	3+		
elbaite TGr-2	1.1	2.3	0.4	80	2+		
	1.3	2.2	0.4	20	2+		
	-	-	-	<2			

ence charge-transfer bands arising from different combinations of adjacent donor-acceptor metal ions (Fe²⁺ and Fe³⁺, Fe²⁺ and Ti⁴⁺, Ti³⁺ and Ti⁴⁺) located in *b-b* sites (absorption polarized $E_{\perp}c$), *b-c* sites (polarized $E_{\perp}c$) and *c-c* sites (maximum intensity $E_{\parallel}c$), as well as on oxygen → metal charge-transfer bands originating in the uv region. Insufficient attention has been paid to accurate curve-resolution of spectra in the optical region. Further, chemical analyses by electronmicroprobe do not yield metal valence states directly.

In the current work, the optical spectra of a suite of brown, green, blue, and black tourmalines and of a crystal zoned in most of the above colours, have been collated, resolved into component absorptions, and related to Fe and Ti content Mössbauer absorption and heating experiments are also described. A basis is presented for a unified theory of interpretation of spectra of tourmalines of the dravite-schorl series; charge-transfer processes are shown to be predominant.

EXPERIMENTAL DETAILS

Specimens

The tourmaline specimens were obtained through the courtesy of Mr. H. R. Steacy, curator of the reference series of the National Mineral Collection, Geological Survey of Canada.

The results of partial analysis by electron microprobe (D. R. Owens), and the cell dimensions of powdered samples, as measured by x-ray diffraction using a 114.6 mm Debye-Scherrer camera (J. M. Stewart) are given in Table 1.

The varietal names were selected according to the cell parameters and the nearest end-member in the elbaite-schorl or dravite-schorl series.

Mössbauer spectra

The Mössbauer spectra are shown in Figures 1 and 2; they were obtained at room temperature with a spectrometer having a velocity drive of the constant acceleration type, synchronized by a 512-channel analyzer. The source was ⁵⁷Co diffused in copper. The velocity scale was calibrated, using iron powder as a standard, immediately after the measurement of the spectrum of each sample. The linewidth from the calibration spectrum varied from 0.3 to 0.4 mm/sec, averaging 0.37 mm/sec.

The spectra were computer-fitted (D. W. Carson) to a selected number of Lorentzian line profiles by a least-squares method and correction was made for the parabolic background (intensity variations at the detector due to source motion). The typical linewidth resulting from these fits was appreciably larger than the calibration linewidth. This implies a spread in the Mössbauer parameters of the underlying spectra and this bears directly on the interpretations given here. Because the measurements were

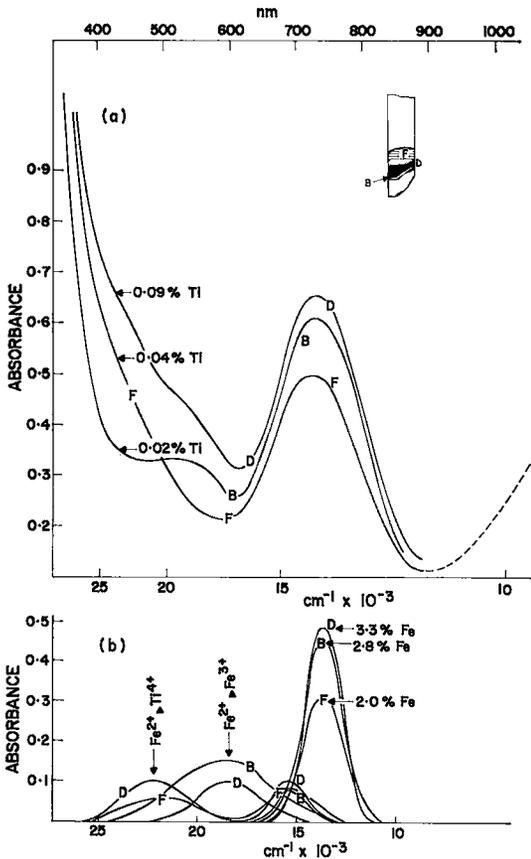


FIG. 5. Unpolarized spectra of zoned tourmaline TZ, specimen thickness 0.066 cm. (a) original unresolved spectra, non-linear energy scale, (b) resolved spectra, linear energy scale. Zone D 2.7% Fe, 0.09% Ti; Zone F 2.0% Fe, 0.04% Ti; Zone B 2.8% Fe, 0.02% Ti.

visually-judged background absorption, and then resolving the net spectra with a Dupont Model 310 curve resolver. Although this technique is somewhat subjective, it is considered that the position of the minor "hidden" features are probably accurate to within ± 300 cm^{-1} . Intensity values are subject to errors of approximately $\pm 25\%$.

DESCRIPTION AND DISCUSSION OF OPTICAL SPECTRA

The crystal-field bands of Fe²⁺ in tourmaline — evidence for Fe²⁺ in the c-site

Mössbauer measurements in this and other studies (Marfunin 1970; Burns 1972; Burns &

Simon 1973; Hermon *et al.* 1973) demonstrate that Fe²⁺ is present in both *b*- and *c*-sites of tourmalines in the dravite-schorl and elbaite-schorl series. The *b*:*c* occupancy ratio of Fe²⁺ varies from $\sim 1:1$ for the black Villeneuve specimen to $\sim 15:1$ for some elbaites (Table 2, Hermon *et al.* 1973).

Despite Mössbauer evidence for Fe²⁺ occupancy of the two sites, absorption spectra seem to show only the two commonly-observed near-infrared bands arising from components of the ${}^5T_2 \rightarrow {}^5E$ transition of Fe²⁺ in one distorted octahedral site. Because the average dimensions of the *c*-sites (Al-O = 1.93 Å) in dravites, for example, are substantially smaller than those of the *b*-sites (Mg-O = 2.05 Å) (Buerger *et al.* 1962), it is anticipated that additional bands that can be assigned to Fe²⁺ ions in the smaller *c*-sites should be seen at higher energy. Indeed Marfunin (1970) has suggested, from unresolved spectra of several black tourmalines, that a band at $\sim 12,000$ cm^{-1} is due to Fe²⁺ in the *c*-site having C_{3v} symmetry. As will be seen, such a band was not found in resolved spectra of the present work.

Resolution of the two envelopes centred at $\sim 13,800$ cm^{-1} (725 nm) and $\sim 8,600$ cm^{-1} (1160 nm) in spectra of the Villeneuve tourmaline (Fig. 6) reveals that each comprises two bands, at $\sim 13,200$ cm^{-1} and $\sim 14,500$ cm^{-1} in the former envelope, and at $\sim 7,900$ cm^{-1} and $\sim 9,500$ cm^{-1} in the latter. Pairing the components at 14,500 cm^{-1} and 9,500 cm^{-1} and those at 13,200 cm^{-1} and 7,900 cm^{-1} , and averaging the energies of the two components of each pair, it can be argued (Faye 1972) that the corresponding Fe²⁺-O distances in the *c*- and *b*-sites are respectively 2.03 to 2.05 Å and 2.09 to 2.11 Å. The two pairs are of approximately equal intensity, consistent with Mössbauer-derived (Table 2) Fe²⁺ *b*:*c* populations of $\sim 1:1$.

Burns & Simon (1973) have suggested that the bands near 14,000 cm^{-1} and 9,000 cm^{-1} are due to Fe²⁺ in the *c*- and *b*-sites respectively. However, this seems to be disproved by the present work in that the schorl spectrum in Figure 6 shows four crystal-field bands that must belong to Fe²⁺ in *b*- and *c*-sites, and Mössbauer spectra of TB1-1 shows a 15:1 ratio of Fe²⁺ in *b*:*c* and yet the 14,000:9,000 cm^{-1} absorbance ratio is not greatly different from that of schorl for which *b*:*c* = 8:7.

The band at $\sim 6,000$ cm^{-1} in Figure 6b is difficult to explain in terms of six-coordinate Fe²⁺. However, it could be due to a small amount of Fe²⁺ in tetrahedral or eight-fold cubic coordina-

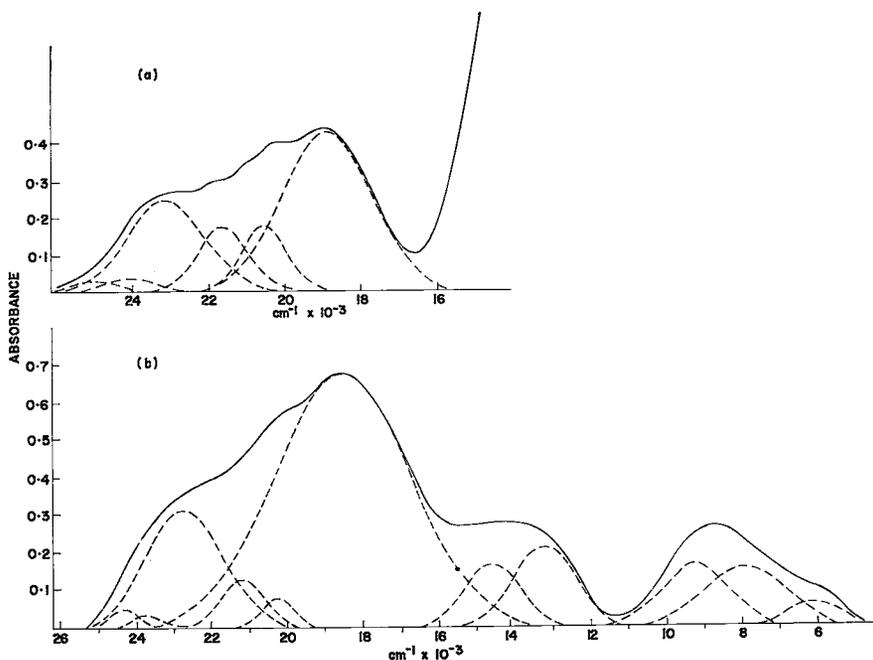


FIG. 6. Resolved unpolarized spectra of: (a) blue tourmaline TB1-1, specimen thickness 0.18 cm. (b) schorl, specimen thickness 0.011 cm.

tion; such species are known to absorb in the 6,000 cm^{-1} region (Burns 1970, pp. 60 and 85 respectively; White & Moore 1972).

Careful resolution of unpolarized and $E||c$ spectra ($E \perp c$ spectra are usually too intense to be resolved) of a number of elbaïtes indicates the presence of a weak band at 15,000–16,000 cm^{-1} that manifests itself only as a modest distortion from the symmetrical of the higher-energy Fe^{2+} band centered at $\sim 14,000 \text{ cm}^{-1}$ (Figs. 3, 4, and 5). There is less conclusive evidence for the presence of a second "hidden" band in elbaïte spectra at 9,500–10,500 cm^{-1} (Fig. 3). If these two "hidden" bands are paired, their average energies (12,000–13,000 cm^{-1}) are appropriate for Fe^{2+} -O c -site distances of 2.03–2.05 Å (Faye 1972). Mössbauer measurements of elbaïtes reveal relatively small amounts of Fe^{2+} ions in c -sites (Table 2). The intensities and energies of the "hidden" bands are uncertain because of difficulties in estimating the uv-centred background absorption. The lower energies of Fe^{2+} spectral bands in schorl compared with those of Fe^{2+} in elbaïtes are consistent with earlier observations (Burns 1970) that increasing Fe^{2+} substitution into relatively tight octahedral sites (*e.g.*, Mg) in ferromagnesian silicates causes an approximately linear decrease in Dq .

Effect of $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$ and $\text{O}^{2-} \rightarrow \text{Fe}^{3+}$ charge-transfer on dichroism

The dichroism of tourmalines has been explained (Townsend 1970) on grounds that metal \rightarrow metal ($\epsilon > 100$ –1000) and oxygen \rightarrow metal ($\epsilon > 1000$) charge-transfer processes are promoted when the electric vector vibrates in the 0001 plane, which plane contains overlapping t_{2g} lobes of adjacent edge-sharing octahedra. Crystal-field transitions ($\epsilon \sim 1$ –10) borrow intensity from charge-transfer transitions (Manning 1973) and here we wish to emphasize the degree to which uv-centred $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$ and $\text{O}^{2-} \rightarrow \text{Fe}^{3+}$ charge-transfer processes influence the dichroism in the visible and near-infrared regions. In ferromagnesian silicates, glasses, and aqueous solutions, the $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$ and $\text{O}^{2-} \rightarrow \text{Fe}^{3+}$ processes are centred at 50,000–55,000 cm^{-1} and 40,000–50,000 cm^{-1} , respectively. For a mineral section of given thickness, the intensity, peak-centre and breadth of the charge-transfer bands depend not only on cation concentrations but also on such factors as the composition of second-nearest neighbour sites (Manning 1973). Because $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$ absorption occurs at a higher energy than $\text{O}^{2-} \rightarrow \text{Fe}^{3+}$, and because the molar extinction coefficient for the former process is less than that for the latter (Steele & Douglas 1965) it follows that, for

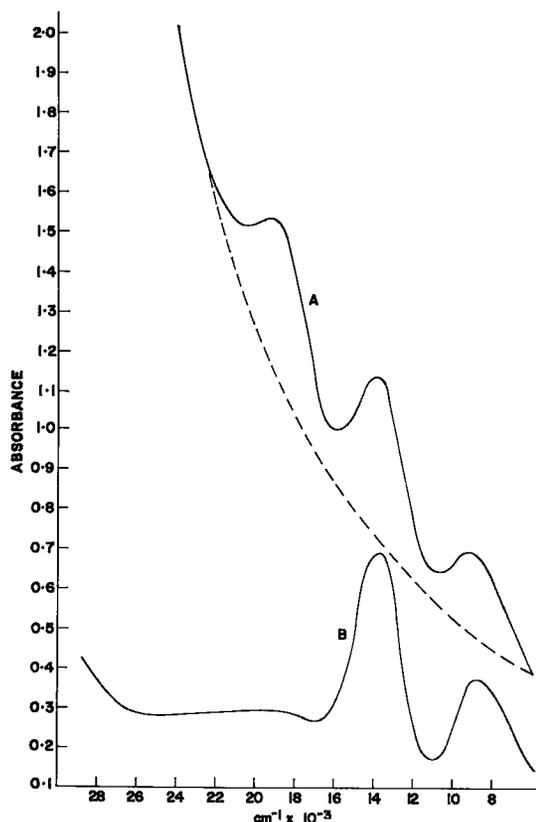


FIG. 7. $E||c$ spectra of TB1-1, specimen thickness, 0.046 cm. A—after heating for 20 hr at 800°C. B—before heating.

many iron-bearing materials, colour is influenced more by $O^{2-} \rightarrow Fe^{3+}$ than by $O^{2-} \rightarrow Fe^{2+}$ (e.g., see the spectrum of partly oxidized TB1-1 in Fig. 7).

In Figure 8 is plotted the $E_{\perp c}/E||c$ intensity ratio for the b -site Fe^{2+} band at 14,000 cm^{-1} against Fe^{2+} concentration for most of the specimens listed in Table 1 and also for a number of tourmalines described earlier (Wilkins *et al.* 1969). Ferrous ion populations for the Ville-neuve schorl are known from Mössbauer spectra (Table 2), whereas, for the other tourmalines, it is assumed that the Fe^{2+} concentration is the total-Fe concentration. We propose that the approximately linear relationship in Figure 8 reflects the degree of intensity-stealing from $O^{2-} \rightarrow Fe^{2+}$ charge-transfer processes. In support of this, we have observed that the intensity ratio $E_{\perp c}/E||c \approx 1$ for the colourless tourmaline listed in Table 1, in which material, quite obviously, energy overlap between charge-transfer transitions and crystal-field transitions is negligible.

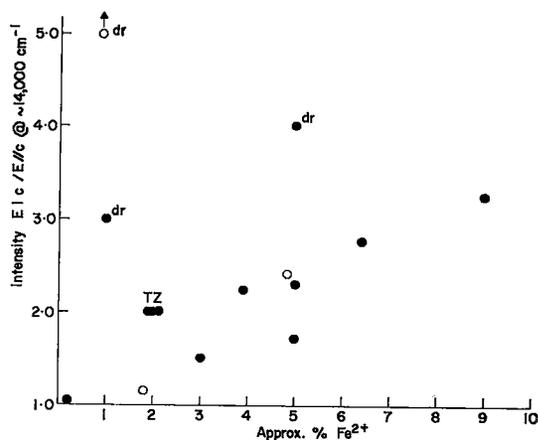


FIG. 8. Variation of intensity ratio $E_{\perp c}/E||c$ of Fe^{2+} band at 14,000 cm^{-1} with Fe^{2+} concentration. o = calculated from spectra measured by Wilkins, Farrell & Naiman (1969). ● = calculated from spectra measured by the authors. dr = brown titaniferous dravites. TZ = zoned tourmaline containing titanium.

$Fe^{2+} \rightarrow Fe^{3+}$ charge-transfer in tourmaline

Questions as to whether the $Fe^{2+} \rightarrow Fe^{3+}$ charge-transfer process is of measurable intensity in tourmalines and as to which of a number of dichroic absorption bands characterizes the process have yet to be resolved (Faye *et al.* 1968; Wilkins *et al.* 1969; Townsend 1970; Burns 1972). However, remarkable similarities in the net visible-region absorption spectra (Fig. 6) of blue and black tourmalines (after subtracting uv-centred background and the high-energy limb of the 14,000 cm^{-1} band), and ad-

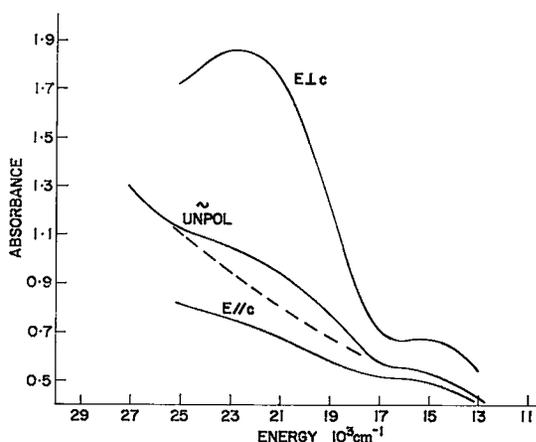


FIG. 9. Polarized spectra of brown dravite No. 1, specimen thickness 0.038 cm.

ditional similarities between the spectra of heated-blue (Fig. 7) and black (Manning 1969a, 1973) varieties, particularly in the 18,500 cm^{-1} region, indicate that the $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ charge-transfer band can be identified with confidence.

In most spectra presented in Figures 3, 4, and 5, absorptions at 17,500-19,000 cm^{-1} and 21,000-23,500 cm^{-1} can be recognized as metal-metal charge-transfer bands, firstly because they are clearly not part of the well-known crystal-field spectra of Fe^{3+} , Fe^{2+} or Mn^{2+} and, secondly, because the polarization properties (maximum intensity in $E \perp c$ spectra; see spectra of TB1-1 in Fig. 3 and of dravite in Fig. 9) are appropriate for M_b-M_b and M_b-M_c interaction. There is strong evidence that the 21,000-23,500 cm^{-1} band is associated with Ti (Manning 1969b; see also later text in current article). Therefore, the lower energy band is probably caused by $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ charge-transfer.

Spectra of blue (TB1-1) and black (Villeneuve) tourmalines

Figure 7 shows $E \parallel c$ spectra of TB1-1 before and after partial oxidation by heating in air at 800°C for 20 hours. The intensities of the absorption edge, probably caused by $\text{O}^{2-} \rightarrow \text{Fe}^{3+}$ charge-transfer, and of the 18,500 cm^{-1} band have increased dramatically on heating. Mössbauer measurements (Table 2) show that the $\text{Fe}^{2+}/\text{Fe}^{3+}$ ratio changes from $\sim 24:1$ to $\sim 2:1$. Significantly, spectra of the Villeneuve tourmaline show a strong absorption at 18,500 cm^{-1} (Fig. 6) that is superimposed on intense uv-centred background (Manning 1969a, 1973), and here also, Mössbauer spectra indicate a low $\text{Fe}^{2+}/\text{Fe}^{3+}$ ratio of $\sim 3:1$. It seems reasonable to conclude that the increased intensity of the 18,500 cm^{-1} band in spectra of heated-blue and of black tourmaline arises from an increased concentration of interacting Fe^{2+} - Fe^{3+} pairs, i.e., the band represents $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ charge-transfer. It is to be noted that completely oxidized material at the surface of the heated TB1-1 specimen may also contribute to spectrum A of Figure 7; therefore, the spectral change on heating gives semi-quantitative information at best.

The Villeneuve tourmaline contains $\sim 12\%$ wt.% Fe, and the $\text{Fe}^{2+}/\text{Fe}^{3+}$ ratio is $\sim 3:1$. Mössbauer spectra show that the Fe^{2+} is evenly distributed between the *b*- and *c*-sites (see Tables 1 and 2). Because of the low Ca content (0.11%) of the Villeneuve material, substitution of major amounts of Fe^{2+} into Al^{3+} *c*-sites requires parallel substitution of Fe^{3+} into M^{2+} *b*-sites; replacement of Na^+ by Ca^{2+} is unimportant.

Clearly, Fe^{3+} is localized for the most part on *b*-sites and $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ processes will occur in the 0001 plane ($E \perp c$). The polarization of the 18,500 cm^{-1} band for ($E \perp c$) is consistent with this expectation.

The five, possibly composite, bands in the 20,000-26,000 cm^{-1} range (Fig. 6) are difficult to assign, but the relatively small half-widths of most of them suggest that they mark spin-forbidden transitions in Fe^{2+} and Fe^{3+} ions which are only weakly field-dependent. The ϵ -values of the 22,500-23,500 cm^{-1} band, based on Fe^{3+} contents of TB1-1 and Villeneuve specimens, are 10 and 20, respectively. Corresponding values based on Fe^{2+} concentrations are 0.5 and 5. If this band is assigned to spin-forbidden transition in Fe^{2+} or Fe^{3+} , the ϵ -values indicate intensity-borrowing from $\text{O}^{2-} \rightarrow \text{Fe}^{2+}/\text{Fe}^{3+}$ charge-transfer transitions, caused possibly by replacement of covalent next-nearest neighbour cations by less-covalent ions, e.g., Si^{4+} by Al^{3+} or Fe^{3+} or, alternatively, by the conversion of OH^- to O^{2-} (Manning 1973). However, the uv-centred charge-transfer absorption in blue tourmaline spectra is not intense. Although the energy of the 22,500-23,500 cm^{-1} band is appropriate for the well-known transition ${}^6A_1 \rightarrow {}^4A_1E(G)$ in octahedral- Fe^{3+} , the band half-width (2,500-3,000 cm^{-1}) is too great for a field-independent transition, even allowing for the superimposition of two different Fe^{3+} spectra arising from two different next-nearest neighbour environments. The band could be similar to the 22,000-24,000 cm^{-1} band in spectra of green and brown tourmalines, the origin of which is discussed below.

It is noteworthy that Marfunin (1970) observed a band at $\sim 18,000$ cm^{-1} , in the spectra of several black tourmaline specimens, which he assigned to a spin-forbidden transition of Fe^{2+} .

$\text{Fe}^{2+} \rightarrow \text{Ti}^{3+}$ charge-transfer in certain tourmalines

An absorption, in the form of a discrete band or a shoulder, is observed at 22,000-24,000 cm^{-1} in spectra of TGr-2 (Fig. 4), brown dravite (Fig. 9) and zones A, D and F of specimen TZ (Fig. 5). The band is particularly prominent in spectra of dravites that are Ti-rich but, compared to other tourmalines, relatively Fe-poor. The polarization properties of the band (maximum intensity when $E \perp c$) suggest metal-metal charge-transfer, possibly $\text{Ti}^{3+} \rightarrow \text{Ti}^{4+}$ as has been argued earlier (Manning 1969b) rather than the ${}^2T_2 \rightarrow {}^2E(D)$ transition in octahedral- Ti^{3+} . The Ti dependence of the band is illustrated beautifully by the analytical and spectral correlations of Figure 5.

The ϵ -values of the "Ti-band" in unpolarized-light spectra, based on total-Ti concentrations, range from ~ 15 for brown dravites, to ~ 100 for TGr-2, and to ~ 1000 in $E \perp c$ spectra of TGr-2 (Fig. 4). Because of the great dilution of 0.01% Ti (~ 0.01 molar) in TGr-2, corresponding to an occupancy of 0.002 sites out of 3.0 b -sites and 6.0 c -sites, the effective concentration of $Ti^{3+} - Ti^{4+}$ pairs will be orders of magnitude less than 0.01 molar, from which the effective ϵ -value becomes unacceptably large ($> 10^4$) in $E \perp c$. Moreover, the absence of measurable $Ti^{3+} d-d$ absorption in dravites, one of which contained 1% Ti and 1% Fe, the presence of strong $Fe^{2+} d-d$ bands, and the expectation that ϵ -values of $Ti^{3+} d-d$ bands are greater than those of Fe^{2+} , suggest that essentially all Ti in tourmalines is Ti^{4+} . These observations indicate that the 22,000-24,000 cm^{-1} band in brown and green tourmalines arises from $Fe^{2+} \rightarrow Ti^{4+}$ charge-transfer. The 22,500-23,500 cm^{-1} bands in TB1-1 and Villeneuve spectra are considerably narrower than the "Ti band" of dravites, 2,500 cm^{-1} against 5,500 cm^{-1} and this, combined with the low Ti concentration ($< 0.01\%$) of TB1-1, makes assignment difficult. It has been suggested that $Fe^{2+} \rightarrow Ti^{4+}$

processes cause absorptions in visible-region spectra of biotites and phlogopites (Faye 1968), synthetic and natural sapphires (Townsend 1968; Ferguson & Fielding 1971), natural pyroxenes (Dowty & Clark 1973) and synthetic glasses (van der Graf *et al.* 1973). Also, charge-transfer between Ti^{4+} and various inorganic ions, including Fe^{2+} , occurs in aqueous solutions (Reynolds 1965).

Effect of Ti^{4+} on the intensity of $O^{2-} \rightarrow Fe^{2+}$ charge-transfer

Robbins & Strens (1972) have shown that the substitution of Ti into the brucite layer of trioctahedral micas causes chemically and electronically distinct configurations around adjacent Fe^{2+} ions, and that this "Ti-effect" in turn causes a broadening and intensification of $O^{2-} \rightarrow Fe^{2+}$ bands so that they encroach on the visible region and markedly influence the colour and pleochroism. We have shown earlier in this work that the relatively large $E \perp c/E \parallel c$ intensity ratios for the Fe^{2+} 14,000 cm^{-1} $d-d$ band in Ti-rich dravites (Fig. 8) arise through intensity-stealing from intensified $O^{2+} \rightarrow Fe^{2+}$ uv-centred absorption. The effect of Ti ions on the intensity of the $O^{2-} \rightarrow Fe^{2+}$ and $O^{2-} \rightarrow Fe^{3+}$ absorp-

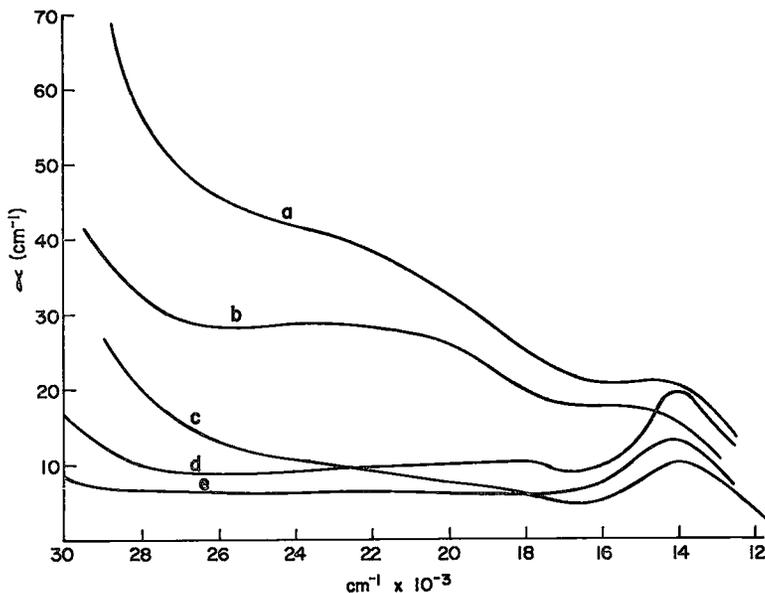


FIG. 10. Effect of titanium on intensity of uv charge-transfer (unpolarized spectra).

a = brown tourmaline	— 4.9% Fe, 0.96% Ti.
b = dravite No. 1	— 1.0% Fe, 0.70% Ti.
c = TZ (zone D)	— 3.3% Fe, 0.10% Ti.
d = TB1-1	— 6.0% Fe, $< 0.01\%$ Ti.
e = TGr-2	— 5.0% Fe, 0.01% Ti.

tion is shown in Fig. 10 for different varieties of tourmalines. Because the Fe^{2+} concentration in these tourmalines greatly exceeds that of Fe^{3+} , we feel that $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$ charge-transfer contributes the more to the absorption edge.

A "Ti-effect" has been observed from comparisons of spectra of green andradite and black schorlomite, garnets of respective composition $\text{Ca}_6(\text{Fe}^{3+}_{3.95}\text{Mn}_{0.05})\text{Si}_6\text{O}_{24}$ and $\text{Ca}_6(\text{Fe}^{3+}_{1.5}\text{Al}_{0.65}\text{Ti}^{4+}_{1.85})(\text{Si}_{4.5}\text{Fe}^{3+}_{0.95}\text{Al}_{0.39})\text{O}_{24}$, (Manning 1973). Oxygen $\rightarrow \text{Fe}^{3+}$ charge-transfer and Fe^{3+} d - d bands are intensified in schorlomite by replacement of adjacent covalent Si^{4+} ions by less-covalent Fe^{3+} and Al^{3+} ions. Similarly, the substitution of Ti^{4+} into the b - or c -sites of tourmaline requires parallel charge-compensation, and this may be accomplished by conversion of $\text{OH}^- \rightarrow \text{O}^{2-}$. The O^{2-} ion is probably larger than OH^- and more polarizable, thus facilitating oxygen \rightarrow metal charge-transfer. Cations in b -sites are normally bonded to two OH^- and those in c -sites to one OH^- . Significantly, $\text{O}(3)$ site occupancies for some specimens of Donnay & Barton (1972) are $(\text{OH})_{0.89}\text{O}_{0.11}$ in elbaïtes, $(\text{OH})_{0.85}\text{O}_{0.15}$ in dravites and $(\text{OH})_{0.16}\text{O}_{0.84}$ in very intensely absorbing buergerite.

CONCLUSIONS

Although previous workers have studied the optical absorption spectra of tourmalines in the elbaïte-schorl and dravite-schorl series, the important influence of charge-transfer processes on colour and dichroism has not been recognized. This work has shown that these properties are due mainly to $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$ (Fe^{3+}), $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ and $\text{Fe}^{3+} \rightarrow \text{Ti}^{4+}$ charge-transfer processes.

Blue and black tourmalines are strongly influenced by the $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ process at $\sim 18,500 \text{ cm}^{-1}$, and the latter also by strong uv-centred $\text{O}^{2-} \rightarrow \text{Fe}^{3+}$ charge-transfer. The brown colour of Ti-rich dravites, and some elbaïtes, is due to a combination of uv-centred $\text{O}^{2-} \rightarrow \text{Fe}^{2+}$, and $\text{Fe}^{2+} \rightarrow \text{Ti}^{4+}$ charge-transfer at $22,000$ - $24,000 \text{ cm}^{-1}$. The $\text{Fe}^{2+} \rightarrow \text{Ti}^{4+}$ absorption is relatively weak in green elbaïtes.

In general, the colour of a tourmaline, as determined by the intensity of the $\text{Fe}^{2+} \rightarrow \text{Fe}^{3+}$ band at $\sim 18,500 \text{ cm}^{-1}$, is a good indicator of the degree of oxidation of iron according to the sequence: green-brown elbaïtes \approx brown dravites $<$ blue elbaïtes \ll black schorls.

ACKNOWLEDGEMENTS

The authors thank Mr. D. R. Owens for microprobe analyses and Mr. J. M. Stewart for the measurement of cell parameters.

REFERENCES

- BUERGER, M. J., BURNHAM, C. W. & PEACOR, D. R. (1962): Assessment of the several structures proposed for tourmaline. *Acta Cryst.* 15, 583-590.
- BURNS, R. G. (1970): *Mineralogical Applications of Crystal Field Theory*. Cambridge University Press.
- (1972): Mixed valencies and site occupancies of iron in silicate minerals from Mössbauer spectroscopy. *Can. J. Spect.* 17, 51-59.
- & SIMON, H. F. (1973): Cation disorder in tourmalines. *Geol. Soc. Amer. Ann. Mtg. Dallas*, Abstr. 5, 563-4.
- DONNAY, G. & BARTON, R. (1972): Refinement of the crystal structure of elbaïte and the mechanism of tourmaline solid solution. *Tschermaks Min. Petr. Mitt.* 18, 273-286.
- DOWTY, E. & CLARK, J. R. (1973): Crystal structure refinement and optical properties of a Ti^{3+} fassaite from the Allende Meteorite. *Amer. Mineral.* 8, 230-242.
- FAYE, G. H. (1968): Optical absorption spectra of iron in six-coordinate sites in chlorite, biotite, phlogopite and vivianite. *Can. Mineral.* 9, 403-425.
- (1972): Relationship between crystal-field splitting parameter and $M_{\text{host-O}}$ bond distance as an aid in the interpretation of absorption spectra of Fe^{2+} -bearing materials. *Can. Mineral.* 11, 473-487.
- , MANNING, P. G. & NICKEL, E. H. (1968): An interpretation of the polarized optical absorption spectra of tourmaline, cordierite, chloritoid and vivianite. *Amer. Mineral.* 53, 1174-1201.
- FERGUSON, J. & FIELDING, P. E. (1971): Origin of the colours of yellow, green and blue sapphires. *Chem. Phys. Lett.* 10, 262-265.
- GOLDANSKII, V. I. (1964): *The Mössbauer Effect and Its Applications to Chemistry*. Consultants Bureau, New York.
- VAN DER GRAF, M. A. C. G., DE VRIES, K. J. & BURGGRAFF (1973): Influence of heat treatment on the optical absorption of glasses containing iron and titanium oxides. *Physics Chem. Glasses* 14, 53-59.
- HERMON, E., SIMKIN, D. J., DONNAY, G. & MUIR, W. B. (1973): The distribution of Fe^{2+} and Fe^{3+} in iron-bearing tourmalines: A Mössbauer study. *Tschermaks Min. Petr. Mitt.* 19, 124-132.
- MANNING, P. G. (1969a): Optical absorption spectra of chromium-bearing tourmaline, black tourmaline and buergerite. *Can. Mineral.* 10, 57-70.
- (1969b): An optical absorption study of the origin of colour and pleochroism in pink and brown tourmalines. *Can. Mineral.* 9, 678-690.
- (1973): Extinction coefficients of Fe^{3+} spectral bands in oxides and silicates as indicators of local crystal composition. *Can. Mineral.* 12, 120-123.
- MARFUNIN, A. C., MKRTCHYAN, A. R., NADZHARYAN, G. N., NYUSSIK, YA. M. & PLATONOV, A. N. (1970): Optical and Mössbauer spectra of iron in tourmalines. *Izv. Akad. Nauk SSSR, Ser. Geol.* 2, 146-150.

- REYNOLDS, M. L. (1965): Charge transfer from inorganic ions to titanium (IV). *J. Chem. Soc.* 2991-2995.
- ROBBINS, D. W. & STRENS, R. G. J. (1972): Charge-transfer in ferromagnesian silicates: the polarized electronic spectra of trioctahedral micas. *Mineral. Mag.* 38, 551-563.
- STEELE, F. N. & DOUGLAS, R. W. (1965): Some observations on the absorption of iron in silicate and borate glasses. *Phys. Chem. Glasses* 6, 246-252.
- TOWNSEND, M. G. (1968): Visible charge-transfer band in blue sapphire. *Solid State Commun.* 6, 81-83.
- _____ (1970): Dichroism of tourmaline. *J. Phys. Chem. Solids* 31, 2481-2488.
- WHITE, W. B. & MOORE, R. K. (1972): Interpretation of the spin-allowed bands of Fe²⁺ in silicate garnets. *Amer. Mineral.* 57, 1692-1710.
- WILKINS, R. W. T., FARRELL, E. F. & NAIMAN, C. S. (1969): The crystal-field spectra and dichroism of tourmaline. *J. Phys. Chem. Solids* 30, 43-56.
- Manuscript received March 1974, emended June 1974.*